AMERICAN NATIONAL STANDARD

Metric Slotted Hex Nuts

ANSI B18.2.4.3M - 1979

Government Key Words:
Nut, Slotted, Hex — Metric

REAFFIRMED 1995

FOR CURRENT COMMITTEE PERSONNEL
PLEASE SEE ASME MANUAL AS-11

REAFFIRMED 2006

FOR CURRENT COMMITTEE PERSONNEL
PLEASE E-MAIL CS@asme.org

SECRETARIAT

SOCIETY OF AUTOMOTIVE ENGINEERS
THE AMERICAN SOCIETY OF MECHANICAL ENGINEERS

PUBLISHED BY

THE AMERICAN SOCIETY OF MECHANICAL ENGINEERS

United Engineering Center 345 East 47th Street New York, N.Y. 10017

Date of Issuance: May 15, 1980

ERRATA

to

ANSI B18.2.4.3M-1979
METRIC SLOTTED HEX NUTS

Page 4, *in the standard shall be replaced with the second page of this Errata*

Page 7, *for* MATERIAL AND FINISH CODE A *and* B, *change* 0.005 mm *to read* 5.1 μm

THE AMERICAN SOCIETY OF MECHANICAL ENGINEERS
345 East 47 Street, New York, N.Y. 10017

M0119E

May 1981

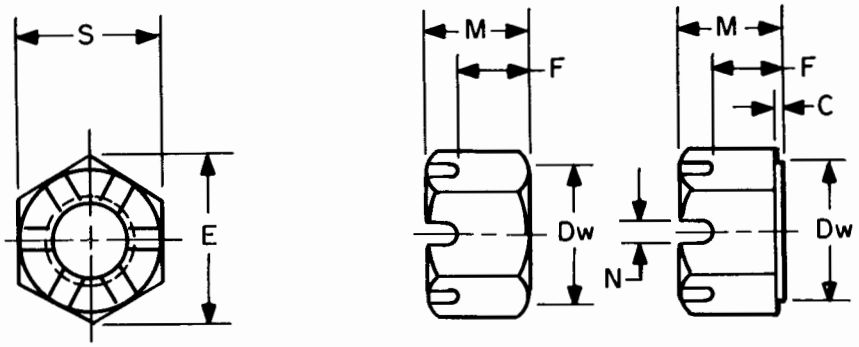

Table 1 Dimensions of Slotted Hex Nuts

Nominal Nut Dia and Thread Pitch	S		E		M		Dw	F		N		C		Total Runout of Bearing Surface FIM
	Width Across Flats		Width Across Corners		Thickness		Bearing Face Dia	Unslotted Thickness		Width of Slot		Washer Face Thickness		
	Max	Min	Max	Min	Max	Min	Min	Max	Min	Max	Min	Max	Min	Max
M5 x 0.8	8.00	7.78	9.24	8.79	5.10	4.80	6.9	3.2	2.9	2.0	1.4	–	–	0.30
M6 x 1	10.00	9.78	11.55	11.05	5.70	5.40	8.9	3.5	3.2	2.4	1.8	–	–	0.33
M8 x 1.25	13.00	12.73	15.01	14.38	7.50	7.14	11.6	4.4	4.1	2.9	2.3	–	–	0.36
M10 x 1.5	16.00	15.73	18.48	17.77	9.30	8.94	14.6	5.2	4.9	3.4	2.8	–	–	0.39
M12 x 1.75	18.00	17.73	20.78	20.03	12.00	11.57	16.6	7.3	6.9	4.0	3.2	–	–	0.42
M14 x 2	21.00	20.67	24.25	23.35	14.10	13.40	19.6	8.6	8.0	4.3	3.5	–	–	0.45
M16 x 2	24.00	23.67	27.71	26.75	16.40	15.70	22.5	9.9	9.3	5.3	4.5	–	–	0.48
M20 x 2.5	30.00	29.16	34.64	32.95	20.30	19.00	27.7	13.3	12.2	5.7	4.5	0.8	0.4	0.56
M24 x 3	36.00	35.00	41.57	39.55	23.90	22.60	33.2	15.4	14.3	6.7	5.5	0.8	0.4	0.64
M30 x 3.5	46.00	45.00	53.12	50.85	28.60	27.30	42.7	18.1	16.8	8.5	7.0	0.8	0.4	0.76
M36 x 4	55.00	53.80	63.51	60.79	34.70	33.10	51.1	23.7	22.4	8.5	7.0	0.8	0.4	0.89
Refer to Para.	4		7		5		6	10		10		6		6
*M10 x 1.5	15.00	14.73	17.32	16.64	10.0	9.6	13.6	5.7	5.4	3.4	2.8	0.6	0.3	0.39

*See Para. 2.2 in General Data.

FOREWORD

American National Standards Committee B18 for the standardization of bolts, screws, nuts, rivets and similar fasteners was organized in March 1922, as Sectional Committee B18 under the aegis of the American Engineering Standards Committee (later the American Standards Association, then the United States of America Standards Institute and, as of October 6, 1969, the American National Standards Institute, Inc.), with the Society of Automotive Engineers and the American Society of Mechanical Engineers as joint sponsors. Subcommitee 2 was subsequently established and charged with the responsibility for technical content of standards covering wrench head bolts and nuts.

At its meeting on December 4, 1974, Committee B18 authorized preparation of a series of standards for metric fasteners. Subcommittee 2 was assigned responsibility for developing standards for metric hex bolts, screws and nuts.

At a meeting on September 22, 1976, Subcommittee 2 organized the contents of a standard covering six different styles of hex nuts. Actual drafting was postponed until ISO/TC2 could reach final decisions relating to basic dimensions and characteristics of hex bolts, screws and nuts. At ISO/TC2 meetings held in April 1977, final actions were taken, Committee B18 affirmed the TC2 decisions at a meeting on June 29, 1977, and drafting of this standard was started.

In February 1978, Committee B18 established a cooperative program with the Department of Defense to draft American National Standards for metric fasteners in such a way that they could be used directly by the Government for procurement purposes. The Department of Defense requested that each of the six nut products be covered in separate standards, and Subcommittee 2 accepted this approach at its meeting on June 27, 1978.

This standard was approved by letter ballot of Committee B18 on July 2, 1979, and was subsequently approved by the secretariats and submitted to the American National Standards Institute for designation as an American National Standard. This was granted on December 6, 1979.

Intentionally left blank

AMERICAN NATIONAL STANDARDS COMMITTEE B18
STANDARDIZATION OF BOLTS, NUTS, RIVETS, SCREWS WASHERS AND SIMILAR FASTENERS

OFFICERS

R. P. Trowbridge, *Chairman*
J. B. Levy, *Vice Chairman*
H. G. Muenchinger, *Vice Chairman*
Richard McGinnis, *Secretary*

COMMITTEE PERSONNEL

AMERICAN CHAIN ASSOCIATION
L. E. Hampel, Moline Malleable Iron Company, St. Charles, Illinois

AMERICAN HARDWARE MANUFACTURERS ASSOCIATION
Donald Wanek, Wrought Washer Manufacturing Company, Milwaukee, Wisconsin

AMERICAN INSTITUTE OF INDUSTRIAL ENGINEERS
R. T. Kelly, Hitchcock Publishing Company, Wheaton, Illinois

AMERICAN SOCIETY OF AGRICULTURAL ENGINEERS
E. R. Friesth, Deere & Company, Moline, Illinois

AMERICAN SOCIETY OF MECHANICAL ENGINEERS, THE
A. R. Machell, Jr., Xerox Corporation, Rochester, New York
F. P. Tisch, Desert Hot Springs, California
R. P. Trowbridge, GM Technical Center, Warren, Michigan
C. R. Adams, Alternate, Newport News Shipbuilding & Dry Dock Co., Newport News, Virginia
K. E. McCullough, Alternate, SPS Technologies, Inc., Jenkintown, Pennsylvania

ANTI-FRICTION BEARING MANUFACTURERS ASSOCIATION
W. J. Derner, FMC Corporation, Indianapolis, Indiana

ENGINE MANUFACTURERS ASSOCIATION
K. F. Naylor, Cummins Engine Company, Columbus, Indiana

FARM & INDUSTRIAL EQUIPMENT INSTITUTE
E. R. Friesth, Deere & Company, Moline, Illinois

HAND TOOLS INSTITUTE
C. B. Ingersoll, J. H. Williams Company, Buffalo, New York

INDUSTRIAL FASTENERS INSTITUTE
R. B. Belford, Industrial Fasteners Institute, Cleveland, Ohio
A. R. Breed, The Lamson & Sessions Company, Cleveland, Ohio
D. A. Garrison, Russell, Burdsall & Ward Inc., Rock Falls, Illinois
R. W. Groover, Bethlehem Steel Company, Lebanon, Pennsylvania
E. J. Heldmann, Holo-Krome Company, West Hartford, Connecticut
Jack Shugart, Rockford Products Corporation, Rockford, Illinois
D. P. Wagner, Illinois Tool Works, Inc., Elgin, Illinois
D. D. Wheeler, Armco Steel Corporation, Kansas City, Missouri
N. W. Bellas, Alternate, Illinois Tool Works, Inc., Elgin, Illinois
R. M. Harris, Alternate, Bethlehem Steel Corporation, Lebanon, Pennsylvania
F. R. Ling, Alternate, Russell, Burdsall & Ward, Inc., Mentor, Ohio

METAL CUTTING TOOL INSTITUTE
Dino Emanuelli, Greenfield Tap & Die, Greenfield, Massachusetts

NATIONAL ELECTRICAL MANUFACTURERS ASSOCIATION
J. B. Levy, General Electric Company, Schenectady, New York
F. F. Weingruber, Westinghouse Electric Corporation, Pittsburgh, Pennsylvania
W. K. Gerrish, Alternate, National Electrical Manufacturers Association, Washington, D.C.

NATIONAL ELEVATOR INDUSTRY, INC.
R. J. Cummings, Otis Elevator Company, Mahwah, New Jersey

SOCIETY OF AUTOMOTIVE ENGINEERS
H. W. Ellison, General Motors Corporation, Warren, Michigan
S. E. Mallen, Ford Motor Company, Dearborn, Michigan
R. S. Piotrowski, Mack Trucks, Inc., Allentown, Pennsylvania
C. F. Schaening, GM Engineering Standards Section, Warren, Michigan
R. R. Sjoberg, International Harvester Company, Hinsdale, Illinois
D. W. Vial, Chrysler Corporation, Detroit, Michigan

TELEPHONE GROUP
R. A. Agnew, Western Electric Company, Chicago, Illinois
R. Morse, Bell Laboratories, Columbus, Ohio
H. Haefeli, Alternate, Bell Laboratory, Columbus, Ohio

TUBULAR AND MACHINE INSTITUTE
J. G. Zeratsky, National Rivet & Manufacturing Company, Waupun, Wisconsin

U.S. DEPARTMENT OF THE AIR FORCE
To be appointed

U.S. DEPARTMENT OF THE ARMY
M. E. Taylor, U.S. Army Armament R & D Command, Dover, New Jersey
Allen Herskovitz, Alternate, U.S. Army Armament R & D Command, Dover, New Jersey

U.S. DEPARTMENT OF DEFENSE
Eli Schwartz, Defense Industrial Supply Center, Philadelphia, Pennsylvania
Lewis Pieninck, Alternate, Defense Industrial Supply Center, Philadelphia, Pennsylvania

U.S. DEPARTMENT OF THE NAVY
J. R. Ruff, Department of the Navy, Washington, D.C.
M. S. Orysh, Alternate, Department of the Navy, Philadelphia, Pennsylvania

U.S. MACHINE CAP WOOD & TAPPING SCREW BUREAUS
S. C. Adamek, Pheoll Manufacturing Company, Chicago, Illinois
R. M. Byrne, U.S. Screw Service Bureaus, New York, New York
T. J. Ferry, E. W. Ferry Screw Products Company, Inc., Cleveland, Ohio
Casey Gordon, Parker-Kalon, Campbellsville, Kentucky
Herman Muenchinger, Continental Screw Company, New Bedford, Massachusetts
K. D. Ringland, Parker-Kalon Fastener Division, USM Corporation, Campbellsville, Kentucky
R. H. Seymour, Reed & Prince Manufacturing Company, Worcester, Massachusetts
Louis Zanin, Elco Industries, Inc., Rockford, Illinois
Paul Foytho, Alternate, Harvey Hubbel, Inc., Bridgeport, Connecticut

INDIVIDUAL COMPANIES
R. W. Bertoia, The Ohio Nut & Washer Company, Mingo Junction, Ohio
E. D. Cowlin, Canton, Ohio
J. E. Eaton, Jr., IBM Corporation, Boulder, Colorado
J. J. Naesset, Clark Equipment Company, Battle Creek, Michigan
J. F. Tornow, Microdot Incorporated, Troy, Michigan

INDIVIDUAL MEMBERS
E. R. Carter, Jr., The Allen Manufacturing Company, Hartford, Connecticut
C. O. Franklin, Valley Bolt Company, Marion, Iowa
F. E. Graves, Fairfield, Connecticut
Jack Trilling, Great Lakes Screw, Chicago, Illinois

PERSONNEL OF SUBCOMMITTEE NO. 2 – SQUARE AND HEX BOLTS AND NUTS

R. R. Sjoberg, Chairman, International Harvester Company, Hinsdale, Illinois
R. B. Belford, Secretary, Industrial Fasteners Institute, Cleveland, Ohio
S. C. Adamek, Pheoll Manufacturing Company, Chicago, Illinois
A. G. Baustert, Federal Screw Works, Detroit, Michigan
A. R. Breed, The Lamson & Sessions Company, Cleveland, Ohio
R. M. Byrne, U.S. Screw Service Bureaus, New York, New York
Art Clever, Deere & Company, Moline, Illinois
W. J. Derner, FMC Corporation, Indianapolis, Indiana
D. A. Garrison, Russell, Burdsall & Ward, Inc., Rock Falls, Illinois
F. E. Graves, Fairfield, Connecticut
R. M. Harris, Bethlehem Steel Corporation, Lebanon, Pennsylvania
J. B. Levy, General Electric Company, Schenectady, New York
D. T. Lipari, Bell Telephone Laboratories, Inc., Columbus, Ohio
A. R. Machell, Jr., Xerox Corporation, Rochester, New York
K. E. McCullough, SPS Technologies, Jenkintown, Pennsylvania
J. C. McMurray, Russell, Burdsall & Ward Inc., Mentor, Ohio
H. G. Muenchinger, Continental Screw Company, New Bedford, Massachusetts
J. J. Naesset, Clark Equipment Company, Battle Creek, Michigan
J. F. Nagy, Ford Motor Company, Dearborn, Michigan
K. F. Naylor, Cummins Engine Company, Columbus, Indiana
I. M. Park, The Steel Company of Canada, Ltd., Hamilton, Ontario, Canada
C. F. Schaening, General Motors Corporation, Warren, Michigan
Lou Strang, Caterpillar Tractor Company, East Peoria, Illinois
M. E. Taylor, U.S. Army Armament R & D Command, Dover, New Jersey
R. P. Trowbridge, General Motors Corporation, Warren, Michigan
P. A. Vacca, Defense Industrial Supply Center, Philadelphia, Pennsylvania
F. F. Weingruber, Westinghouse Electric Corporation, Pittsburgh, Pennsylvania
D. D. Wheeler, Armco Steel Corporation, Kansas City, Missouri
A. Herskovitz, Alternate, U.S. Army Armament R & D Command, Dover, New Jersey
Tony Nebesny, Alternate, FMC Corporation, Indianapolis, Indiana
L. Pieninck, Alternate, Defense Industrial Supply Center, Philadelphia, Pennsylvania

Intentionally left blank

CONTENTS

Intentionally left blank

AMERICAN NATIONAL STANDARD

METRIC SLOTTED HEX NUTS

GENERAL DATA

1. Scope

1.1 This standard covers the complete general and dimensional data for metric slotted hex nuts recognized as American National Standard.

1.2 The inclusion of dimensional data in this standard is not intended to imply that all of the nut sizes in conjunction with the various options described herein are stock items. Purchasers are requested to consult with manufacturers concerning lists of stock production slotted hex nuts.

1.3 Slotted hex nuts purchased for Government use shall conform to this standard, and additionally to the requirements of Appendix II.

2. Comparison with ISO standards

2.1 Slotted hex nuts as covered in this standard have been coordinated to the extent possible with draft ISO standards. The dimensional differences between this ANSI standard and the ISO draft standards are very few and relatively minor. None affect the functional interchangeability of nuts manufactured to the requirements of either.

2.2 At its meetings in Varna, May 1977, ISO/TC2 studied several technical reports analyzing design considerations influencing determination of the best series of width across flats for hex bolts, screws and nuts. A primary technical objective was to achieve a logical ratio between under head (nut) bearing surface area (which determines the magnitude of the compressive stress on the bolted members) and the tensile stress area of the screw thread (which governs the clamping force that can be developed by tightening the fastener). Table 1 lists the sizes selected by ISO/TC2 to be ISO standard.

M10 nuts with 15 mm width across flats are currently being produced and used in U.S.A. and many other countries of the world. This size, however, is not an ISO standard. Unless M10 nuts with 15 mm width across flats are specifically ordered, M10 nuts with 16 mm width across flats shall be furnished.

2.3 Letter symbols designating dimensional characteristics are in accord with those used in ISO standards, except capitals have been used for data processing convenience instead of lower case letters used in ISO standards.

3. Dimensions. All dimensions in this standard are in millimeters, unless otherwise stated.

4. Width Across Flats

4.1 The width across flats shall be the distance, measured perpendicular to the axis of the nut, between two opposite wrenching flats.

4.2 Regardless of nut material or manufacturing process, no transverse section through the nut between 25 and 75 percent of the actual nut thickness as measured from the bearing surface shall be less than the minimum width across flats specified in Table 1.

4.3 Maximum width across flats shall not be exceeded, except that for milled-from-bar nuts made of non-ferrous materials the specified maximum width across flats may be exceeded to conform with the commercial tolerances of cold finished bar stock material.

4.4 For milled-from-bar nuts, the nominal bar size used shall be the closest commercially available size to, but not greater than, the specified maximum width across flats of the nut.

5. Thickness. The nut thickness shall be the overall distance, measured parallel to the axis of the nut, from the top of the nut to the bearing surface, and shall include the thickness of the washer face where provided, but shall exclude raised identification markings, where they are permitted.

6. Tops and Bearing Surfaces

6.1 M16 and smaller nuts shall have a chamfered bearing surface. M20 and larger nuts, at the manufacturer's option, shall either have a chamfered or a washer faced bearing surface.

6.2 The diameter of the bearing surface shall not exceed the width across flats nor be less than the bearing face diameter specified in Table 1. For referee purposes, measurement of washer face diameter on washer faced nuts shall be taken at mid thickness of the washer face.

6.3 The bearing surface shall be flat and perpendicular to the axis of the thread within the total runout limit specified in Table 1.

6.4 The tops of nuts shall be flat and the diameter of the chamfer circle shall be equal to the maximum width across flats within a tolerance of minus 15 percent.

6.5 The length of chamfer at hex corners shall be from 5 to 15 percent of the nominal thread diameter. The surface of the chamfer may be slightly convex or rounded.

7. Corner Fill. A rounding or lack of fill at the junction of hex corners with the chamfer shall be permissible provided the width across corners is within specified limits at and beyond a distance equal to 17.5 percent of the nominal thread diameter from the chamfered face.

8. True Position of Tapped Hole. The axis of tapped hole shall be located at true position with respect to the axis of nut body within a tolerance zone having a diameter equivalent to 4 percent of the maximum width across flats, regardless of feature size.

9. Countersink. The tapped hole shall be countersunk on the bearing face and may be countersunk on the top. The countersink included reference angle shall be 90 deg to 120 deg. The maximum countersink diameter shall be the nominal thread diameter (major diameter) plus 0.75 mm for M8 and smaller nuts, and 1.08 times the nominal thread diameter for M10 and larger nuts. The minimum countersink diameter shall be the nominal thread diameter.

10. Slots. Slots shall be normal to nut flats. Contour of bottom of slots shall be at manufacturer's option. Requirements for gaging slots are given in Appendix I.

11. Threads

11.1 Threads shall be metric coarse threads with class 6H tolerances in accordance with ANSI B1.13M.

11.2 Nuts intended for use with externally threaded fasteners which are plated or coated with a plating or coating thickness (e.g., hot dip glavanized) requiring overtapping of the nut thread to permit assembleability shall have overtapped threads in conformance with requirements specified in ASTM A563M.

12. Material and Mechanical Properties

12.1 Carbon steel nuts, without specified heat treatment, shall conform to the material and mechanical property class 5 slotted hex nuts in ASTM A563M. Carbon steel nuts with specified heat treatment shall conform to the material and mechanical property requirements specified for property class 10 slotted hex nuts in ASTM A563M.

12.2 Nuts of other materials such as stainless steel, brass, bronze and aluminum alloys shall have properties as agreed upon by the manufacturer and purchaser. Properties of nuts of several grades of nonferrous materials are covered in ASTM F467M.

13. Finish. Unless otherwise specified, nuts shall be furnished with a natural (as processed) finish, unplated or uncoated.

14. Identification Symbols. Nuts shall be identified for property class and Manufacturing source as agreed between the manufacturer and purchaser.

15. Designation

15.1 Slotted hex nuts shall be designated by the following data, preferably in the sequence shown: product name, nominal diameter and thread pitch, steel property class or material identification, and protective coating if required. (NOTE: It is common practice in ISO standards to omit thread pitch from the product designation when screw threads are the metric coarse thread series, e.g., M10 is M10 x 1.5.)

Examples:

Slotted hex nut, M8 x 1.25, ASTM A563M class 10, zinc plated.

Slotted hex nut, M20 x 2.5, silicon bronze, ASTM F467M grade 651.

15.2 The Government part numbering system for metric slotted hex nuts is given in Appendix II. This system may be used by any user needing a definitive part numbering system.

16. Terminology. For definitions of terms relating to fasteners or component features thereof used in this standard, refer to American National Standard, Glossary of Terms for Mechanical Fasteners, ANSI B18.12.

17. Options. Options, where specified, shall be at the discretion of the manufacturer unless otherwise agreed between manufacturer and purchaser.

18. Workmanship. Nuts shall not contain an excess of surface imperfections which might affect their serviceability, such as burrs, seams, laps, loose scale and other irregularities.

19. Referenced Standards

19.1 Copies of referenced ASTM standards may be obtained from the American Society for Testing and Materials, 1916 Race Street, Philadelphia, Pennsylvania 19103.

19.2 Copies of referenced ANSI standards may be obtained from the American Society of Mechanical Engineers, 345 East 47th Street, New York, N.Y. 10017.

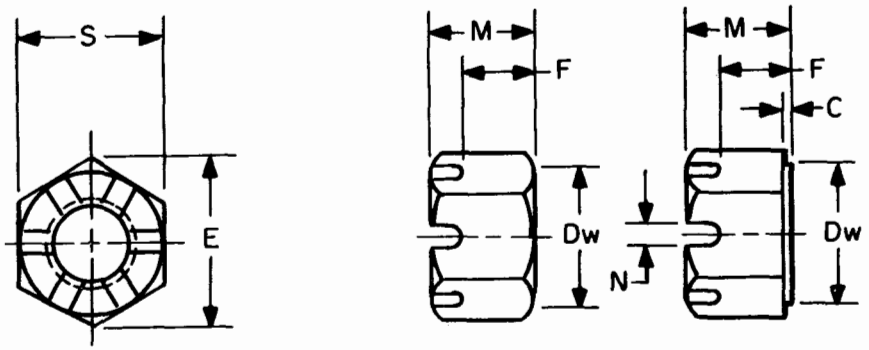

Table 1 Dimensions of Slotted Hex Nuts

Nominal Nut Dia and Thread Pitch	S		E		M		Dw	F		N		C		Total Runout of Bearing Surface FIM
	Width Across Flats		Width Across Corners		Thickness		Bearing Face Dia	Unslotted Thickness		Width of Slot		Washer Face Thickness		
	Max	Min	Max	Min	Max	Min	Min	Max	Min	Max	Min	Max	Min	Max
M5 x 0.8	8.00	7.78	9.24	8.79	5.10	4.80	7.0	3.2	2.9	2.0	1.4	—	—	0.30
M6 x 1	10.00	9.78	11.55	11.05	5.70	5.40	8.9	3.5	3.2	2.4	1.8	—	—	0.33
M8 x 1.25	13.00	12.73	15.01	14.38	7.50	7.14	11.6	4.4	4.1	2.9	2.3	—	—	0.36
M10 x 1.5	16.00	15.73	18.48	17.77	9.30	8.94	14.6	5.2	4.9	3.4	2.8	—	—	0.39
M12 x 1.75	18.00	17.73	20.78	20.03	12.00	11.57	16.6	7.3	6.9	4.0	3.2	—	—	0.42
M14 x 2	21.00	20.67	24.25	23.36	14.10	13.40	19.4	8.6	8.0	4.3	3.5	—	—	0.45
M16 x 2	24.00	23.67	27.71	26.75	16.40	15.70	22.4	9.9	9.3	5.3	4.5	—	—	0.48
M20 x 2.5	30.00	29.16	34.64	32.95	20.30	19.00	27.9	13.3	12.2	5.7	4.5	0.8	0.4	0.56
M24 x 3	36.00	35.00	41.57	39.55	23.90	22.60	32.5	15.4	14.3	6.7	5.5	0.8	0.4	0.64
M30 x 3.5	46.00	45.00	53.12	50.85	28.60	27.30	42.5	18.1	16.8	8.5	7.0	0.8	0.4	0.76
M36 x 4	55.00	53.80	63.51	60.79	34.70	33.10	50.8	23.7	22.4	8.5	7.0	0.8	0.4	0.89
Refer to Para.	4		7		5		6	10		10		6		6
*M10 x 1.5	15.00	14.73	17.32	16.64	10.0	9.6	13.6	5.7	5.4	3.4	2.8	0.6	0.3	0.39

*See Para. 2.2 in General Data.

APPENDIX I

SLOT GAGES AND GAGING FOR SLOTTED NUTS

The gages specified below shall be used to determine the acceptability of the alignment and bottom contours of the slots in slotted nuts in accordance with the following procedure:

The gaging for slot alignment provides for equal variations in the location of the cotter pin hole in bolt and the location of the slots in nut.

To inspect the nut, the slotted end of gage shall be inserted through the threaded hole from the bearing surface of the nut. The gage pin shall then be inserted into both the gage slot and the nut slots through three adjacent faces of nut, consecutively. Slot alignment shall be considered satisfactory if the gage pin fits into the slots without interference at all three gaging positions. The bottom contour shall be acceptable if the gage pin contacts the bottom surfaces of opposite slots during the alignment gaging at all three positions.

Some deviations from the specified gage plug diameters D may be necessary to compensate for variations in the nut thread minor diameter due to differences in manufacturing practices.

To insure adequate service life, gages and gage pins shall be suitably hardened.

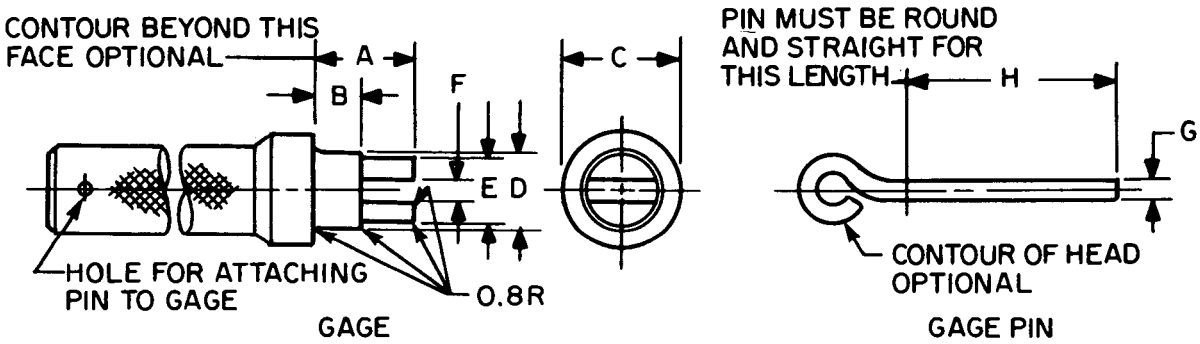

Dimensions of Slot Gages and Gage Pins

Nominal Nut Dia and Thread Pitch	A(2) Gage Pilot Length	B(2) Gage Plug Length	C Gage Face Diameter	D(1) Gage Plug Diameter	E Gage Pilot Diameter	F Gage Slot Width	G Gage Pin Diameter	H Gage Pin Length
	Min	Max	Min	+0.00 −0.03	±0.13	+0.05 −0.00	+0.00 −0.05	Min
M5 x 0.8	5.1	2.7	8.0	4.13	3.73	1.30	1.30	24.0
M6 x 1	5.7	3.0	9.0	4.91	4.51	1.70	1.70	26.0
M8 x 1.25	7.5	3.9	11.0	6.64	6.24	2.20	2.20	29.0
M10 x 1.5	9.3	4.7	13.0	8.37	7.97	2.70	2.70	32.0
M12 x 1.75	12.0	6.7	15.0	10.10	9.70	3.10	3.10	34.0
M14 x 2	14.1	7.8	20.0	11.83	11.43	3.40	3.40	37.0
M16 x 2	16.4	9.1	22.0	13.83	13.43	4.40	4.40	40.0
M20 x 2.5	20.3	12.0	28.0	17.29	16.89	4.40	4.40	46.0
M24 x 3	23.9	14.1	30.0	20.75	20.35	5.40	5.40	52.0
M30 x 3.5	28.6	16.6	39.0	26.21	25.81	6.90	6.90	62.0
M36 x 4	34.7	22.2	45.0	31.67	31.27	6.90	6.90	71.0

1. Gage plug diameters are equal to minimum minor diameters of metric coarse threads, class 6H, rounded down to two decimal places.
2. For M10 x 1.5 nuts with 15 mm width across flats, length A shall be 10.0 mm and length B shall be 5.2 mm.

APPENDIX II

PART NUMBERING SYSTEM COVERING STANDARD ITEMS FOR GOVERNMENT USE.

Note

The Government encourages the general use of this appendix to achieve maximum parts standardization.

This appendix establishes the standard items for Government application selected from the possible variations of items within the scope of the standard and provides a part numbering system for identification and application in engineering documents.

The following variations are standard:

a. Diameter/Thread Pitch – as specified in Table 2.

b. Material – Steel, Property Class 10.

c. Finish – Cadmium plating or zinc plating as coded in Part Numbering System.

The part number shall consist of the following element codes in the order shown:

a. Document Identifier – ANSI Standard Number less decimal points

b. Material and Finish

c. Nominal Diameter

d. Special M10 width across flats size

Quality Assurance Provisions: Quality assurance provisions shall be in accordance with FF-N-836, Nut: Square, Hexagon, Cap, Slotted, Castle.

Packaging: Packaging shall be in accordance with PPP-H-1581, Hardware (Fasteners and Related Items), Packaging and Packing for Shipment and Storage of.

APPENDIX II (Cont.)

PART NUMBERING SYSTEM COVERING STANDARD ITEMS FOR GOVERNMENT USE

NOTE: THE GOVERNMENT ENCOURAGES THE GENERAL USE OF THIS SYSTEM TO ACHIEVE MAXIMUM PARTS STANDARDIZATION.

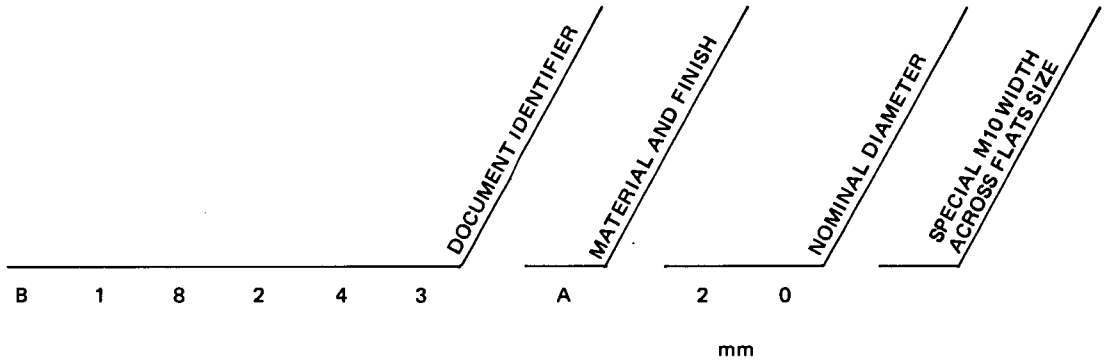

MATERIAL AND FINISH CODE

A — Steel w/Cadmium Plating per QQ-P-416, Type II, Class 3 (0.005mm Plating Thickness), Property Class 10.

B — Steel w/Zinc Plating per QQ-Z-325, Type II, Class 3 (0.005mm Plating Thickness), Property Class 10.

SPECIAL M10 WIDTH ACROSS FLATS SIZE CODE

F - 15mm Nominal

NOTE: The 16mm Hex Width Across Flats will be supplied unless Code F is designated.

EXAMPLE: B18243A20 indicates a Nut, Slotted, Hex-Metric, made of cadmium plated steel, property class 10 with M20 x 2.5 threads.

METRIC HEX SLOTTED NUTS

Table 2 Government Standard Items and Part Numbering System

NOMINAL NUT SIZE AND THREAD PITCH	STANDARD DIAMETER (PART NUMBER)
M5 x 0.8	05
M6 x 1	06
M8 x 1.25	08
M10 x 1.5	10
M12 x 1.75	12
M14 x 2	14
M16 x 2	16
M20 x 2.5	20
M24 x 3	24
M30 x 3.5	30
M36 x 4	36

Intentionally left blank