



Standard Practice for Steel Bars, Selection Guide, Composition, and Mechanical Properties¹

This standard is issued under the fixed designation A400; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope

1.1 This practice covers the selection of steel bars according to section and to the mechanical properties desired in the part to be produced. This is not a specification for the procurement of steel. Applicable procurement specifications are listed in Section 5.

1.2 Several steel compositions intended for various sections and mechanical property requirements are presented in **Tables 1-6**. The criteria for placing a steel composition in one of the three general class designations, Classes P, Q, and R (described in Section 4) are as follows:

1.2.1 *Classes P and Q* should be capable of developing the mechanical properties shown in **Tables 1-4** by liquid quenching from a suitable austenitizing temperature, and tempering at 800°F (427°C) or higher. A hardness indicated by tests made at a location shown in **Fig. 1**, A, B, or C, is taken as evidence that a composition is capable of meeting other equivalent mechanical properties shown in the tables. Normal good shop practices are assumed, with control of austenitizing and tempering temperatures, and mild agitation of the part in the quenching bath.

1.2.2 *Class R* should be capable of developing the mechanical properties shown in **Tables 5 and 6** as hot rolled, by cold drawing, or by cold drawing with additional thermal treatment. The locations for obtaining tension tests are described in **6.2**.

1.3 It is not implied that the compositions listed in the tables are the only ones satisfactory for a certain class and mechanical property requirement. Steels with lower alloy contents are often satisfactory through the use of special processing techniques.

1.4 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

¹ This practice is under the jurisdiction of ASTM Committee A01 on Steel, Stainless Steel and Related Alloys and is the direct responsibility of Subcommittee A01.15 on Bars.

Current edition approved March 1, 2012. Published April 2012. Originally approved in 1956. Last previous edition approved in 2006 as A400 – 69 (2006). DOI: 10.1520/A0400-69R12.

2. Referenced Documents

2.1 ASTM Standards:²

A108 Specification for Steel Bar, Carbon and Alloy, Cold-Finished

A304 Specification for Carbon and Alloy Steel Bars Subject to End-Quench Hardenability Requirements

A311/A311M Specification for Cold-Drawn, Stress-Relieved Carbon Steel Bars Subject to Mechanical Property Requirements

A322 Specification for Steel Bars, Alloy, Standard Grades
A633/A633M Specification for Normalized High-Strength Low-Alloy Structural Steel Plates

A675/A675M Specification for Steel Bars, Carbon, Hot-Wrought, Special Quality, Mechanical Properties

3. Significance and Use

3.1 If the desired mechanical properties are as described in **4.1.1** for material identified as Classes P-1 through P-7, or in **4.1.2** for material identified as Classes Q-1 through Q-7, the strength level desired can be based on hardness or the equivalent tensile or yield strength as shown in **Tables 1-4**. If the desired mechanical properties are as set forth in **4.1.3** for material identified as Classes R-1 through R-6, the strength level is based on yield strength as shown in **Tables 5 and 6**.

3.2 The user, after determining the mechanical property requirements of the critical section (that carrying the greatest stress) of the part, should select the composition or compositions from **Tables 1-6** that fulfills these requirements and is most suitable for processing.

4. Classification

4.1 Steel bar compositions under this practice are classified according to mechanical property requirements and the critical section size of the part to be produced, as follows:

4.1.1 *Classes P-1 through P-7* comprise bars for parts to operate under severe service conditions requiring high yield

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

TABLE 1 Steels for Moderately Quenched Parts—Classes P-1 Through P-7
(Applicable to oil-quenching or equivalent rate of heat-removal.)

NOTE 1—Steels listed as approved for a certain section or strength may be used for lighter sections and lower strengths.

NOTE 2—Steel composition numbers correspond to SAE, AISI, or ASTM designations. Those in italics are no longer considered standard grades due to decreased usage.

NOTE 3—An H-steel with the same grade designation as a standard SAE-AISI steel is capable of meeting the same section and strength requirements as the standard steel (see Specification **A304**), and is the preferred method of specification.

NOTE 4—Steels having a maximum carbon content of 0.40 % or over, or a hardness of HB 293 or over after heat-treating, are not recommended for applications involving welding.

Desired Minimum Hardness		Equivalent Tensile Strength, psi ^A	Equivalent Yield Strength, psi ^A	Minimum ^B As-Quenched Hardness		Class						
						P-1	P-2	P-3	P-4	P-5	P-6	P-7
						Diameter of Round (or Distance Between Faces of Square or Hexagonal) Sections, in. ^C						
						To ½, incl	Over ½ to 1, incl	Over 1 to 1½, incl	Over 1½ to 2, incl	Over 2 to 2½, incl	Over 2½ to 3, incl	Over 3 to 3½, incl
						Thickness of Flat Sections, in. ^C						
HB	HRC			HB	HRC	To 0.3, incl	Over 0.3 to 0.6, incl	Over 0.6 to 1, incl	Over 1 to 1.3, incl	Over 1.3 to 1.6, incl	Over 1.6 to 2.0, incl	Over 2.0 to 2.3, incl
229 to 293, incl	20 to 33, incl	110 000 to 145 000, incl	90 000 to 125 000, incl	388	42	1330 4130 5132 8630	50B30					
Over 293 to 341, incl	Over 33 to 38, incl	Over 145 000 to 170 000, incl	Over 125 000 to 150 000, incl	409	44	1335 3135 4042 5135	94B30	3140 4135 4640 8640 8740	4137	4142	9840	4337
Over 341 to 388, incl	Over 38 to 42, incl	Over 170 000 to 190 000, incl	Over 150 000 to 170 000, incl	455	48	1340 3140 4047 4135 5140 8637 TS14B50 50B40		4137 6145 8642 8645 8742	4140 TS4140 94B40	4145 9840	4147 4337 86B45	4340
Over 388 to 429, incl	Over 42 to 45, incl	Over 190 000 to 205 000, incl	Over 170 000 to 185 000, incl	496	51	1345 4063 4068 4140 4640 5145 5150 8640 8642	8645 8740 8742 9260 9261 TS4140 50B46 50B44 50B50	5147 5155 5160 6150 9262	4142 4145 4337 8650 8655 50B60 51B60 81B45	8660 9840	4147 4161 4340 86B45	4150 4161 TS4150 E4340 9850

^A 1 psi = 0.006895 MPa.

^B Minimum as-quenched hardness for obtaining desired hardness after tempering at 800°F (427°C) or higher.

^C 1 in. = 25.4 mm.

strength (90 000 psi (621 MPa) and over), good ductility, and relatively high notch toughness. The applicable section sizes, identified as Classes P-1 through P-7, are shown in **Table 7**. The steel compositions suitable for Classes P-1 through P-7 and for various desired mechanical properties are listed in **Tables 1 and 2**.

4.1.2 *Classes Q-1 through Q-7* comprise bars for parts operating under moderate service conditions requiring moderate to high yield strength (75 000 to 185 000 psi (517 to 1276 MPa)), corresponding tensile-strength levels, and good ductility. The applicable section sizes, identified as Classes Q-1 through Q-7, are shown in **Table 7**. The steel compositions suitable for Classes Q-1 through Q-7 and various desired mechanical properties are listed in **Tables 3 and 4**.

4.1.3 *Classes R-1 through R-6* comprise bars for parts requiring a lower yield strength (30 000 to 120 000 psi (207

to 827 MPa)), with fair to good ductility. The applicable section sizes, identified as Classes R-1 through R-6, are shown in **Table 7**. The steel compositions capable of developing the various desired mechanical properties are listed in **Tables 5 and 6**.

5. Applicable Procurement Specifications

5.1 For procurement of steel, it is recommended that the following ASTM specifications of latest issue be used: Specification **A108**, Specification **A304**, Specification **A311/A311M**, Specification **A322**, Specification **A633/A633M**, and Specification **A675/A675M**.

6. Location at Which Desired Properties Are Obtained

6.1 *Classes P-1 Through P-7 and Q-1 Through Q-7*—The mechanical properties shown in **Tables 1-4** are based on

TABLE 2 Steels for Drastically Quenched Parts—Classes P-1 Through P-7
(Applicable to water-quenching or equivalent rate of heat-removal — See Note 5)

NOTE 1—Steels listed as approved for heavier sections or higher strengths may be used in the same conditions for lighter sections and lower strengths.

NOTE 2—Steel composition numbers correspond to ASE, AISI, or ASTM designations. Those in italics are no longer considered standard grades due to decreased usage.

NOTE 3—An H-steel with the same grade designation as a standard SAE-AISI steel is capable of meeting the same section and strength requirements as the standard steel (see Specification **A304**), and is the preferred method of specification.

NOTE 4—Steels having a maximum carbon content of 0.40 % or over, or a hardness of HB 293 or over after heat-treating, are not recommended for applications involving welding.

NOTE 5—Parts made of steel with a carbon content of 0.33 % or higher, where the section is under 1 1/2 in. (38.1 mm) should not be quenched in water without careful exploration for quench-cracking.

Desired Minimum Hardness						Class															
						P-1		P-2		P-3		P-4		P-5		P-6		P-7			
						Diameter of Round (or Distance Between Faces of Square or Hexagonal) Sections, in. ^C															
						To ½ , incl		Over ½ to 1, incl		Over 1 to 1½, incl		Over 1½ to 2, incl		Over 2 to 2½, incl		Over 2½ to 3, incl		Over 3 to 3½, incl			
						Thickness of Flat Sections, in. ^C															
HB		HRC		HB		HRC		To 0.3, incl		Over 0.3 to 0.6, incl		Over 0.6 to 1.0, incl		Over 1.0 to 1.3, incl		Over 1.3 to 1.6, incl		Over 1.6 to 2.0, incl		Over 2.0 to 2.3, incl	
229 to 293, incl	20 to 33, incl	110 000 to 145 000, incl	90 000 to 125 000, incl	388	42	8625		4130	94B30												
						8627		5130													
								8630													
								50B30													
Over 293 to 341, incl	Over 33 to 38, incl	Over 145 000 to 170 000, incl	Over 125 000 to 150 000, incl	409	44	4032		1330	1335				1340 ^D			3140				4137	
						4037		5132	5135				3135 ^D			4135				4337	
						4130		94B30	5140				4640							9840	
						5130			50B40				8637 ^D								
						8630							8640								
						TS14B35							8740								
						508B30															

^A 1 psi = 0.006895 MPa.

^B Minimum as-quenched hardness for obtaining desired hardness after tempering at 800°F (427°C) or higher.

^C 1 in. = 25.4 mm.

^D These steels have insufficient hardenability for Class P-4, because of difference in test locations, but are satisfactory for other smaller sizes.

obtaining hardness test specimens from the locations shown in **Fig. 1**, A, B, and C. For bars, the location should be at least twice the diameter or minimum distance between faces from an end; and for flat sections, at least twice the thickness from an edge.

6.2 *Classes R-1 Through R-6*—The mechanical properties shown in **Tables 5 and 6** are based on obtaining tension test specimens from the following locations:

6.2.1 Center of bars or plates under 1 1/2 in. (38.1 mm) in diameter or in distance between parallel surfaces, and

6.2.2 Mid-radius or a quarter of the distance between parallel faces from the surface for larger sections.

7. Hardness Criteria for Quenched and Tempered Parts

7.1 *Classes Q-1 Through Q-7*—To obtain the properties stated in **4.1.2** at the locations shown in **Fig. 1**, A, B, and C, a microstructure containing a minimum of 50 % martensite is necessary.

8. Keywords

8.1 steel bars

**TABLE 3 Steels for Moderately Quenched Parts—Classes Q-1 Through Q-7**
(Applicable to oil-quenching or equivalent rate of heat-removal.)

NOTE 1—Steels listed as approved for heavier sections or higher strengths may be used in the same conditions for lighter sections and lower strengths.

NOTE 2—Steel composition numbers correspond to ASE, AISI, or ASTM designations. Those in italics are no longer considered standard grades due to decreased usage.

NOTE 3—An H-steel with the same grade designation as a standard SAE-AISI steel is capable of meeting the same section and strength requirements as the standard steel (see Specification **A304**), and is the preferred method of specification.

NOTE 4—Steels having a maximum carbon content of 0.40 % or over, or a hardness of HB 293 or over after heat-treating, are not recommended for applications involving welding.

Desired Minimum Hardness						Class													
						Q-1		Q-2		Q-3		Q-4		Q-5		Q-6		Q-7	
						Diameter of Round (or Distance Between Faces of Square or Hexagonal) Sections, in. ^C													
						To ½, incl		Over ½ to 1, incl		Over 1 to 1½, incl		Over 1½ to 2, incl		Over 2 to 2½, incl		Over 2½ to 3, incl		Over 3 to 3½, incl	
						Thickness of Flat Sections, in. ^C													
HB	HRC			HB	HRC	To 0.3, incl		Over 0.3 to 0.6, incl		Over 0.6 to 1.0, incl		Over 1.0 to 1.3, incl		Over 1.3 to 1.6, incl		Over 1.6 to 2.0, incl		Over 2.0 to 2.3, incl	
187 to 293, incl	91 (R _b) to 33, incl	95 000 to 145 000, incl	75 000 to 125 000, incl	388	42	1330 4130 5132	8630 <i>50B30</i>	8637		3140 8740		4140 <i>TS4140</i> 94B40		4142					
Over 293 to 341, incl	Over 33 to 38, incl	Over 145 000 to 170 000, incl	Over 125 000 to 150 000, incl	409	44	1335 <i>4042</i> 5135	<i>50B30</i> 3140 <i>4640</i> 8640 94B30	8740 <i>4135</i> <i>4640</i> 8640	8740	4137 <i>TS4140</i> 4140 8642 8645 <i>8742</i>	<i>TS4140</i> 81B45	4142	4145		4147 <i>4337</i> <i>9840</i> <i>86B45</i>				
Over 341 to 388, incl	Over 38 to 42, incl	Over 170 000 to 190 000, incl	Over 150 000 to 170 000, incl	455	48	1340 <i>3135</i> 3140 4047 <i>4135</i> 5140	8637 <i>TS14B50</i> <i>50B40</i> 5150 8642 8645	1345 4137 4140 50B50 5155 6150	<i>8742</i> <i>TS4140</i> 5147 50B50 5155 6150	4142 <i>94B40</i> 51B60	4145 8655 <i>9840</i>	4147 <i>4337</i> <i>86B45</i>	4150 4340 <i>TS4150</i>						
Over 388 to 429, incl	Over 42 to 45, incl	Over 190 000 to 205 000, incl	Over 170 000 to 185 000, incl	496	51	1345 4047 <i>4063</i> <i>4068</i> 4140 <i>4640</i> 5145 5150 8640 8642	8645 8740 <i>8742</i> 9260 <i>TS4140</i> <i>50B46</i> <i>50B44</i> <i>50B50</i>	4142 5147 5155 6150 <i>9261</i> <i>94B40</i> 50B60 51B60 81B45		4145 <i>4337</i> 5160 <i>8650</i> 8655 <i>9262</i>	<i>9840</i> 4147 4340 <i>8660</i> <i>86B45</i>	4150 <i>TS4150</i>	E4340 <i>9850</i>						

^A 1 psi = 0.006895 MPa.

^B Minimum as-quenched hardness for obtaining desired hardness after tempering at 800°F (427°C) or higher.

^C 1 in. = 25.4 mm.

**TABLE 4 Steels for Drastically Quenched Parts—Classes Q-1 Through Q-7**
(Applicable to water-quenching or equivalent rate of heat-removal—See **Note 5**)

NOTE 1—Steels listed as approved for heavier sections or higher strengths may be used in the same conditions for lighter sections and lower strengths.

NOTE 2—Steel composition numbers correspond to SAE, AISI, or ASTM designations. Those in italics are no longer considered standard grades due to decreased usage.

NOTE 3—An H-steel with the same grade designation as a standard SAE-AISI steel is capable of meeting the same section and strength requirements as the standard steel (see Specification **A304**), and is the preferred method of specification.

NOTE 4—Steels having a maximum carbon content of 0.40 % or over, or a hardness of HB 293 or over after heat-treating, are not recommended for applications involving welding.

NOTE 5—Parts made of steel with a carbon content of 0.33 % or higher, where the section is under 1½ in. (38.1 mm) should not be quenched in water without careful exploration for quench-cracking.

Desired Minimum Hardness						Class						
						Q-1	Q-2	Q-3	Q-4	Q-5	Q-6	Q-7
						Diameter of Round (or Distance Between Faces of Square or Hexagonal) Sections, in. ^C						
						To ½, incl	Over ½ to 1, incl	Over 1 to 1½, incl	Over 1½ to 2, incl	Over 2 to 2½, incl	Over 2½ to 3, incl	Over 3 to 3½, incl
						Thickness of Flat Sections, in. ^C						
HB	HRC			HB	HRC	To 0.3, incl	Over 0.3 to 0.6, incl	Over 0.6 to 1.0, incl	Over 1.0 to 1.3, incl	Over 1.3 to 1.6, incl	Over 1.6 to 2.0, incl	Over 2.0 to 2.3, incl
187 to 293, incl	91 (HRB) to 33, incl	95 000 to 145 000, incl	75 000 to 125 000, incl	388	42	1000 series, from 1024 to 1040, incl ^E	4037 to 4130	5135 94B30		5140 ^D 8637 50B40 ^D	4640	3140 8740
						8625 5132 8627	5132 8630 50B30					
Over 293 to 341, incl	Over 33 to 38, incl	Over 145 000 to 170 000, incl	Over 125 000 to 150 000, incl	409	44	1036 to 1045, incl ^E	1330 5046 4032 5135 8630	1335		1340 ^D 3135 ^D 3140 8637 ^D	4135 8640 8740	4137 4140 8642 8645 8742 TS4140
Over 341 to 388, incl	Over 38 to 42, incl	Over 170 000 to 190 000, incl	Over 150 000 to 170 000, incl	455	48	1335 4037 4130 5046 5130 5132 5135 8635	3135 TS14B354042 4047 50B30 94B30	1340 3140 4135 5140 8637 50B40		1345 50B44 ^D 4137 4640 ^D 5145 ^D 5150 8640 ^D 8642 8740 ^D	4140 8645 8742 TS4140	4142 4337 5147 6150 8650 9840 81B45 94B40
										50B50		

^A 1 psi = 0.006895 MPa.

^B Minimum as-quenched hardness for obtaining desired hardness after tempering at 800°F (427°C) or higher.

^C 1 in. = 25.4 mm.

^D These steels have insufficient hardenability for Class Q-4 parts because of different location of test specimens, but are satisfactory for smaller sections.

^E For these steels, the yield to tensile-strength ratio will usually be lower than 80 %.

TABLE 5 Steels for Parts Manufactured From Hot Rolled^A and Cold Drawn^{B,C} Bars—Classes R-1 Through R-6

NOTE 1—Steels listed as approved for heavier section or higher strengths may be used in the same conditions for lighter sections and lower strengths.

NOTE 2—Steel composition numbers correspond to ASE, AISI, or ASTM designations. Those in italics are no longer considered standard grades due to decreased usage.

Hot-rolled 1000 series steels with a maximum carbon content of 0.40 % only are approved for welding. Only cold-drawn 1000 series steels used in the strength level and section thickness for which hot-rolled steels of the same composition are approved may be welded, and in this case caution should be exercised to see that excessive grain growth does not occur in the heat-affected zone.

Desired Minimum Yield Strength, psi ^D	Class			
	R-1	R-2	R-3 and R-4	R-5 and R-6
	Diameters of Round or Approximately Round Sections, in. ^E			
	To ½ , incl	Over ½ to 1, incl	Over 1 to 2, incl	Over 2 to 3, incl
	Thickness of Flat Sections, in. ^E			
	To 0.3, incl	Over 0.3 to 0.6, incl	Over 0.6 to 1.3, incl	Over 1.3 to 2.0, incl
Over 30 000 to 35 000, incl	HR 1016 HR 1020 HR 1018 HR 1019	HR 1016 HR 1020 HR 1018 HR 1022 HR 1019	HR 1018 HR 1019 HR 1021	HR 1018 HR 1022 HR 1030
Over 35 000 to 40 000, incl	HR 1022 HR 1030	HR 1030 HR 1035	HR 1030 HR 1035	HR 1035
Over 40 000 to 45 000, incl	HR 1035	HR 1040	CD 1010 HR 1040	CD 1010 HR 1045 CD 1015 HR 1040
Over 45 000 to 50 000, incl	CD 1010 HR 1040 HR 1045	CD 1010 CD 1015 HR 1045	CD 1015 HR 1045 HR 1137	CD 1020 HR 1137 <i>CD 1115</i> HR 1050
Over 50 000 to 55 000, incl	CD 1015 HR 1050 HR 1137	CD 1020 HR 1137 <i>CD 1115</i> HR 1141 HR 1050	CD 1018 CD 1115 CD 1020 HR 1050 HR 1141 CD 1025 HR 1144	CD 1018 HR 1141 CD 1019 HR 1141 CD 1025
Over 55 000 to 60 000, incl	CD 1018 CD 1115 CD 1025 CD 1019 HR 1141 CD 1020 HR 1144	CD 1018 HR 1144 CD 1019 CD 1025	CD 1019 CD 1120 CD 1022 CD 1117	CD 1022 <i>CD 1120</i> CD 1117 CD 1118

^A Hot-rolled bars are indicated in table by prefix "HR."

^B Cold-drawn bars are indicated in table by prefix "CD." These bars are produced by normal practice in cold-drawing and with no stress relief. Bars cold-finished by turning, grinding, turning and polishing, etc., are not covered under cold-drawn bars, as such cold-finished bars have the properties of hot-rolled bars.

^C Classification of cold-drawn steels by size and yield-strength level in this table is based on yield-strength determinations at 0.2 % offset, or as determined by 0.005 in./in. elongation under load for yield strengths up to 90 000 psi, incl, and by 0.006 in./in. elongation under load for yield strengths above 90 000 psi.

^D 1 psi = 0.006895 MPa.

^E 1 in. = 25.4 mm.

**TABLE 6 Steels for Parts Produced From Cold-Drawn and Cold-Drawn Stress-Relieved Bars—Classes R-1 Through R-6^{A,B}**

NOTE 1—Steels listed as approved for heavier section or higher strengths may be used in the same conditions for lighter sections and lower strengths.

NOTE 2—Steel composition numbers correspond to ASE, AISI, or ASTM designations. Those in *italics* are no longer considered standard grades due to decreased usage.

NOTE 3—Steels in conditions listed in this table are not approved for applications involving welding.

Desired Minimum Yield Strength, psi ^C	Class			
	R-1	R-2	R-3 and R-4	R-5 and R-6
	Diameters of Round or Approximately Round Sections, in. ^D			
	To ½, incl	Over ½ to 1, incl	Over 1 to 2, incl	Over 2 to 3, incl
	Thickness of Flat Sections, in. ^D			
	To 0.3, incl	Over 0.3 to 0.6, incl	Over 0.6 to 1.3, incl	Over 1.3 to 2.0, incl
Over 60 000 to 65 000, incl	CD 1022 CD 1117 <i>CD 1120</i>	CD 1022 CD 1117 CD 1118 <i>CD 1120</i>	CD 1030 CD 1118	CD 1030
Over 65 000 to 70 000, incl	CD 1030 CDT 1040 CD 1118	CD 1030 CD 1035 CDT 1045	CD 1035 CDT 1137 CDT 1040 CDT 1050	CD 1035 CD 1050 CDT 1141 CDT 1045
Over 70 000 to 75 000, incl	CD 1035 CDT 1045	CDT 1137 CDT 1040 CDT 1050	CD 1040 CDT 1141 CDT 1045	CD 1045 CDT 1040 CDT 1144 CDT 1137 CDT 1050
Over 75 000 to 80 000, incl	CDT 1137 CDT 1040 CDT 1050	CD 1040 CDT 1141 CDT 1045	CD 1045 CDT 1040 CDT 1144 CDT 1137 CDT 1050	CD 1137 CDT 1045 CDT 1040 CDT 1141 CD 1050
Over 80 000 to 85 000, incl	CD 1040 CDT 1141 CDT 1045	CD 1045 CDT 1040 CDT 1144 CDT 1137 CDT 1050	CD 1137 CDT 1045 CDT 1040 CDT 1141 CD 1050	CD 1141 CDT 1137 CDT 1045 CDT 1040 CDT 1144 CDT 1050
Over 85 000 to 90 000, incl	CD 1045 CDT 1040 CDT 1144 CDT 1137 CDT 1050	CD 1137 CDT 1045 CDT 1040 CDT 1141 CD 1050	CD 1141 CDT 1137 CDT 1145 CDT 1040 CDT 1144 CDT 1050	CD 1144 CDT 1141 CDT 1137 CDT 1045 CDT 1050
Over 90 000 to 95 000, incl	CD 1137 CDT 1045 CDT 1040 CDT 1141 CD 1050	CD 1141 CDT 1137 CDT 1045 CDT 1050 CDT 1144 CDT 1050	CD 1144 CDT 1141 CDT 1137 CDT 1045 CDT 1050	CDT 1144 CDT 1141 CDT 1137 CDT 1050
Over 95 000 to 100 000, incl	CD 1141 CDT 1137 CDT 1045 CDT 1040 CDT 1144 CDT 1050	CD 1144 CDT 1141 CDT 1137 CDT 1045 CDT 1050	CDT 1144 CDT 1141 CDT 1137 CDT 1050	CDT 1144 CDT 1141
Over 100 000 to 105 000, incl	CD 1144 CDT 1141 CDT 1137 CDT 1045 CDT 1050	CDT 1144 CDT 1141 CDT 1137 CDT 1050	CDT 1144 CDT 1141	CDT 1144
Over 105 000 to 110 000, incl	CDT 1144 CDT 1141 CDT 1137 CDT 1050	CDT 1144 CDT 1141	CDT 1144	
Over 110 000 to 115 000, incl	CDT 1144 CDT 1141	CDT 1144		
Over 115 000 to 120 000, incl	CDT 1144			

^A Conditions and treatments of bars are indicated in this table by the symbols shown below. Bars cold-finished by turning, grinding, turning and polishing, etc., are not covered, as such bars have the properties of hot-rolled bars.

“CD” = Bars produced by normal practice in cold-drawing, and with no stress relief.

“CDT” = Cold-drawn bars with subsequent thermal treatment. Heavier than normal drafts may be required.

^B Classification of cold-drawn steels by size and yield-strength level in this table is based on yield-strength determinations at 0.2 % offset or as determined by 0.005 in./in. elongation under load for yield strengths up to 90 000 psi, and by 0.006 in./in. elongation under load for yield strengths above 90 000 psi.

^C 1 psi = 0.006895 MPa.

^D 1 in. = 25.4 mm.

TABLE 7 Applicable Classes for Critical Section Size

Round, Square, Hexagonal, etc., Sections, Diameter or Dimension Between Opposite Faces, in. ^A		Flat Sections, Thickness, in. ^A		Applicable Class
Over	To and Including	Over	To and Including	
...	1/2	...	0.3	P-1, Q-1, or R-1
1/2	1	0.3	0.6	P-2, Q-2, or R-2
1	1 1/2	0.6	1.0	P-3, Q-3, or R-3
1 1/2	2	1.0	1.3	P-4, Q-4, or R-4
2	2 1/2	1.3	1.6	P-5, Q-5, or R-5
2 1/2	3	1.6	2.0	P-6, Q-6, or R-6
3	3 1/2	2.0	2.3	P-7 or Q-7

^A 1 in. = 25.4 mm.

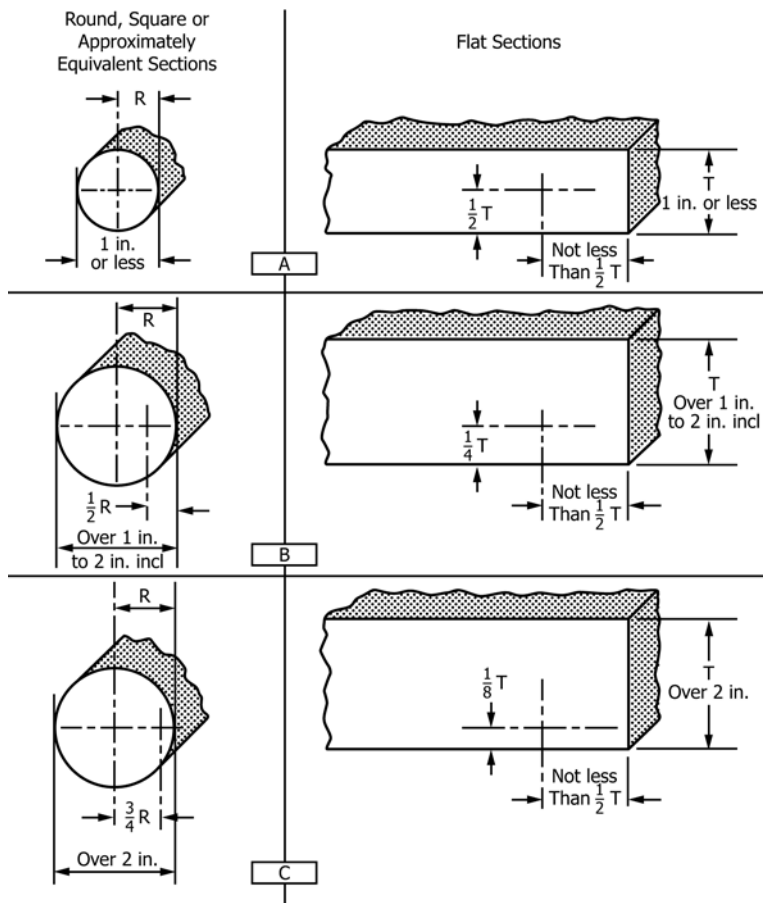


FIG. 1 Locations in Typical Cross Sections of Steel Bars at Which Desired Properties Are Obtained

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the ASTM website (www.astm.org/COPYRIGHT/).