



# Standard Test Method for Measuring Consistency of Self-Flowing Castable Refractories<sup>1</sup>

This standard is issued under the fixed designation C1446; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This test method covers the determination of the consistency (degree of self-flow) and working time of self-flowing castable refractories. This test may optionally be used to determine working time of self-flowing castables.

1.2 The values stated in inch-pound units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

C71 Terminology Relating to Refractories

C230/C230M Specification for Flow Table for Use in Tests of Hydraulic Cement

C860 Test Method for Determining the Consistency of Refractory Castable Using the Ball-In-Hand Test

C862 Practice for Preparing Refractory Concrete Specimens by Casting

C1445 Test Method for Measuring Consistency of Castable Refractory Using a Flow Table

E177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods

E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

## 3. Terminology

3.1 *Definitions of Terms Specific to This Standard:*

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee C08 on Refractories and is the direct responsibility of Subcommittee C08.09 on Monolithics.

Current edition approved July 1, 2011. Published August 2011. Originally approved in 1999. Previous edition approved in 2007 as C1446 – 07. DOI: 10.1520/C1446-11.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3.1.1 *consistency of self-flowing castable refractories*—the degree of mobility (self-flow) of the refractory castable under its own weight as described in this test method at the specified times after adding liquid to the mixer.

3.1.2 *working time of self-flowing castable refractories*—the elapsed time from the first addition of liquid during mixing until the mix will only achieve 25 % self-flow using the procedure described in this test method.

## 4. Summary of Test Method

4.1 The castable refractory is mixed with a tempering liquid and the percentage of self-flow is measured. Self-flow is the percent increase in the diameter of the sample after removing the Specification C230/C230M cone mold and allowing the specimen to flow (spread) under its own weight for 120 s. The consistency is measured 10 min after water addition. Working time may optionally be determined by repeating the self flow test at regular time intervals.

## 5. Significance and Use

5.1 This test method is used to measure the consistency (degree of self-flow) that a castable refractory demonstrates at a given level of tempering liquid at specified time intervals after the liquid is added. A self-flow of 25 % has been selected as the minimum at which a mix can be poured into typical molds or forms in normal practice.

5.2 Castable refractories which are self-flowing at one level of tempering liquid will require vibration for placement at some lower level of tempering liquid. At the tempering liquid levels which require vibration or tamping for placement, the castable refractory should be characterized using test methods which are appropriate for castable refractories designed for vibration placement, such as Test Method C1445.

5.3 This test method is not appropriate for determining the pumpability of castable refractories.

## 6. Interferences (Factors Known to Affect Results)

6.1 During method development, a ruggedness evaluation was performed using a castable comprised of 5 % cement, 17 % reactive alumina, and 78 % tabular alumina. Several

factors were found to cause statistically significant effects on the measured results. See ASTM Research Report No. C08–1016.

**6.1.1 Amount of Mixing Liquid**—The amount of mixing liquid affects the measured results for typical self-flowing castable refractories unless added by weight to within  $\pm 0.002$  lb ( $\pm 1$  g) of the target weight for a 16.52-lb (7500-g) sample weight. The target liquid level is a percentage of the dry weight of the batch.

**6.1.2 Temperature**—During ruggedness testing the effect of temperature was evaluated. The test mix, tempering liquid, and room temperature were controlled to the same targets. When the temperature was raised by 3.5°F (70.3 to 73.8°F) working time was found to be reduced by an average of 10 min. While the degree of this effect may be castable-formulation-dependent, it is accepted that temperature will affect the working time for all typical self-flowing castables.

**6.1.3 Mold Filling Level**—During ruggedness testing it was found that filling the mold to a level of  $\frac{1}{32}$  in. below the top of the mold reduced the measured flow at 10 min after adding liquid to the mixer by approximately 5.5 % for a mix with an average flow of approximately 115 % at this elapsed time.

**6.1.4 Mold Lifting Technique**—During ruggedness testing it was found that the technique for lifting the mold from the sample affected the results. The techniques compared were lifting the mold straight up and twisting the mold approximately 45° as it was lifted off the sample. Twisting the mold while lifting resulted in an appropriate 4.5 % increase in the measured self-flow at 10 min after adding liquid to the mixer.

**6.2** Factors which were found to be rugged during method development for percentage self-flow at 10 min after adding tempering liquid to the mixer were (1) ambient temperature when varied from 70°F to 74°F, (2) tempering liquid when varied by 0.1 %, (3) holding time from filling the mold to lifting the mold when varied from 20 to 60 s, and (4) lubricating the flow surface and wiping clean prior to placing the specimen on the flow surface as compared to no lubrication on a clean metal surface.

**6.3** Factors which were found to be rugged during method development for working time were (1) holding time from filling the mold to lifting the mold when varied from 20 to 60 s, (2) lubricating the flow surface and wiping clean prior to placing the specimen on the flow surface as compared to no lubrication on a clean metal surface, (3) returning the castable to the storage container after each flow measurement when compared to discarding the castable used for each flow measurement, and (4) storing the castable in a covered mixing bowl when compared to storing in a sealed container.

## 7. Apparatus

**7.1 Cone Mold**—The mold used to form the specimen is in accordance with Specification C230/C230M.

**7.2 Measuring Caliper**—Either a caliper in accordance with Specification C230/C230M which reads directly in percent flow or a standard caliper that can be read to within  $\pm 0.004$  in. ( $\pm 0.1$ -mm) accuracy can be used.

**7.3 Flow Surface**—A metal plate shall be used as the flow surface for the sample. It shall be thick enough to remain flat

in use,  $\frac{1}{8}$ -in. thickness is recommended. The surface shall be level and confirmed with a leveling device. It shall have a smooth mill finish with any minor imperfections ground smooth. The surface shall not have any circumferential markings, either permanent or temporary. Radial lines scribed lightly at 45° intervals are recommended to aid in measuring the sample after flow. The surface must be kept clean and free from oxidation. A galvanized or stainless steel or other non-oxidizing metal is recommended. If the flow surface is an oxidizing metal, a lightweight oil can be used to prevent oxidation. The surface must be wiped clean prior to use with an absorbent cloth or clean sponge.

**7.4 Mixed Castable Storage Container**—The mixed castable may either be stored in the mixer bowl between flow intervals or transferred to a container for storage. Independent of the storage container used, it must be sealed airtight to prevent evaporation and must be constructed of a nonporous material. The container size should minimize the air space volume above the stored mixed castable. No more than double the volume of the stored castable is recommended.

**7.5 Castable Mixer**—The castable mixing equipment shall be in accordance with Practice C862. Care must be exercised to ensure the appropriate size mixing bowl is chosen. A motor-driven mixer is highly recommended as many self-flowing castable refractories require high-energy mixing to achieve their self-flowing consistency at the specified liquid levels.

**7.6 Stopwatch/Timer**, capable of being read to 1 s.

**7.7 Balance**, accurate to 0.002 lb (1 g).

**7.8 Light Mold Release Oil or Vegetable Oil Cooking Spray**.

**7.9 Absorbent Cloth or Clean Sponge**.

## 8. Procedure

**8.1** All times, amounts, and conditions are to be in accordance with this practice unless others are specified by the castable manufacturer/mix provider. Any deviations will be included in the test report, see Section 10.

**8.2** Ensure all materials and testing equipment that come in contact with the castable are within 2°F (1°C) of the ambient temperature. During the test, the ambient temperature should not be allowed to change more than 2°F. (see 6.1.2). Whenever possible, the ambient temperature during the test should be in the 68 to 75°F (20 to 24°C) range. Record the actual ambient, dry castable, and mixing liquid temperatures.

**8.3** Ensure all equipment is clean and dry. Remove any oxidation from the flow plate; lightly lubricate and wipe dry the flow plate and flow mold. Lubricate with a light lubricating oil or a vegetable oil cooking spray. No further lubrication of the flow plate shall be done until the testing is completed for the day.

**8.4** Weigh out the mixing liquid to within  $\pm 0.002$  lb ( $\pm 1$  g) of that specified (see 6.1.1).

**8.5** Dry mix the batch for 30 s.

**8.6** Start the timer/stopwatch and add all mixing liquid within 10 s while the mixer is running. Use care that none of the liquid or dry mix is lost. Mixing time and speed shall be as

recommended by the refractory manufacturer. After 1 min of wet mixing, stop the mixer, check for dry material in the bottom of the bowl, stir in any dry material by hand if needed, and resume mixing.

8.7 At the end of wet mixing, place the mixed castable sample in the storage container and measure the castable temperature. The mixed castable may be stored in either the mixer bowl or another container. The mixed castable sample must be protected from moisture loss by sealing the storage container. See 7.4.

8.8 Approximately 1 min prior to each self-flow determination, place the cone mold on the center of the flow plate with the large end down. Hand-mix the stored castable sample lightly with a spatula and pour into the mold. Do not vibrate the material into the mold. The mold must be filled flush with the top. Either overfilling or underfilling will affect the percent flow results (see 6.1.3). If any material is spilled onto the flow plate, clean and wipe the plate dry.

8.9 At the scheduled time, lift the mold from the specimen using care not to twist or pull the mold to the side (see 6.1.4). Wipe any castable adhering to the mold with a finger and place it gently in the middle of the sample. Lightly lubricating the cone with a lightweight oil will prevent material from adhering to the mold. Rubber or latex gloves should be worn when handling the castable to minimize the loss of fines which adhere to hands. Record the actual stored castable temperature.

8.10 Allow the specimen to flow for 120 s then measure and record the sample patty diameter or the percentage self-flow (see 8.11). The flow should be measured quickly as self-flow with some castables may still be proceeding. Measure the flow 10 min after the water addition.

8.11 Measure the diameter of the specimen at 4 places approximately 45° apart. If there are localized irregularities in the specimen diameter, the measurement may be taken in an adjacent area which better represents the average flow diameter. If the Specification C230/C230M caliper is used for measurement, record the four individual readings. The sum of the four individual readings is the percent flow. If a standard caliper is used, record the four individual measurements. Calculate and record the average diameter from the 4 measurements (see 9.1).

8.12 As soon as the flow readings are recorded, return the castable to the storage container and mix into the remaining castable sample with a spatula. Wash the flow plate clean and wipe dry.

8.13 If working time is desired measure flow at 20 and 30 min after liquid addition to the mixer and then every 15 min. Continue running and recording the remaining self-flow checks (see 8.10) until the result is found to be less than 25 % self-flow. Dispose of the castable and clean all equipment.

8.14 If appropriate, lightly lubricate the flow surface to prevent oxidation.

## 9. Calculation

9.1 *Percentage Self-Flow*—When a standard caliper is used to measure the sample patty, use the following formula to

calculate percent self-flow.

$DF$  = final average diameter  
 $Di$  = initial diameter (4 in. for the Specification C230/C230M mold)

$$\text{Percent self flow} = [D_f - D_i] * 100 / D_i \quad (1)$$

$$= [D_f - 4] * 100 / 4 \quad (2)$$

9.2 *Optional Working Time Calculation*—Plot the percentage self-flow as the y scale on a graph versus the elapsed time after adding liquid to the mixer as the x scale. Both the y and the x scales are linear. Connect each of the sequential points on the time scale with a straight line. Where the line crosses the 25 % flow scale, draw a vertical line down to the time scale. Record this point as the working time of the castable refractory.

9.3 See Table 1 and Fig. 1 as examples of the flow readings recorded and the calculation of working time from those readings.

## 10. Report

10.1 Report the following information in the test results:

10.1.1 Date test was run,

10.1.2 Castable/product name or other description of the castable tested,

10.1.3 The dry batch weight for the test, lb (g),

10.1.4 Identification and amount of any additives used (optional),

10.1.5 Mixing liquid used as a percent of the dry sample weight, (%),

10.1.6 Mixing liquid range specified as being acceptable for the product/castable tested (optional),

10.1.7 Mixing liquid type (potable, deionized, distilled, other),

10.1.8 Mixing time (minutes),

10.1.9 Ambient temperature at the time of mixing, dry mix temperature, and liquid temperature, °F (°C),

10.1.10 Final castable temperature, °F (°C),

10.1.11 Description of the container used to store the castable between self-flow intervals,

10.1.12 Percent self-flow at 10 min,

10.1.13 *Optional* percent self-flow at each time interval.

10.1.14 *Optional* ambient temperature at the time when each self-flow was evaluated, °F (°C),

10.1.15 *Optional* working time as calculated in 9.2 (minutes),

10.1.16 Any deviations from Practice C862 in mixing the castable other than those specified in this method. Deviations of particular interest are mixing time, mixing method, and use of materials (liquid, dry castable components, and so forth) at other than room temperature.

TABLE 1 Recorded Flow Readings

Minutes	% Flow
10	119.0
20	120.0
30	120.5
45	124.5
60	123.5
75	96.0
90	16.5

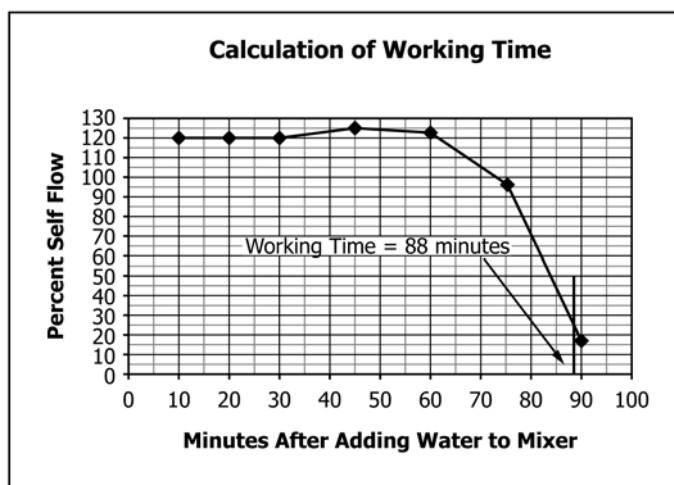


FIG. 1 Calculation of Working Time

10.1.17 Any deviations from conditions specified in this test method.

## 11. Precision and Bias<sup>3</sup>

11.1 The precision of this test method is based on an interlaboratory study of ASTM C1446-07 conducted in 2010. While a total of eight laboratories tested two different weight castable products, only five of the laboratories produced data that could be utilized in the determination of the precision for the method as written. Every test result represents an individual determination. Three test results were reported by every laboratory, and conforming data were analyzed in order to determine the precision statistics listed below. Practice E691 was followed for the design and analysis of the data; the details are given in Research Report RR:C08-1021.<sup>3</sup>

<sup>3</sup> Supporting data have been filed at ASTM International Headquarters and may be obtained by requesting Research Report RR:C08-1021. Contact ASTM Customer Service at service@astm.org.

11.1.1 *Repeatability Limit (r)*—Two test results obtained within one laboratory shall be judged not equivalent if they differ by more than the  $r$  value for that material;  $r$  is the interval representing the critical difference between two test results for the same material, obtained by the same operator using the same equipment on the same day in the same laboratory.

11.1.1.1 Repeatability limits are listed in Table 2.

11.1.2 *Reproducibility Limit (R)*—Two test results shall be judged not equivalent if they differ by more than the  $R$  value for that material;  $R$  is the interval representing the critical difference between two test results for the same material, obtained by different operators using different equipment in different laboratories.

11.1.2.1 Reproducibility limits are listed in Table 2.

11.1.3 The terms *repeatability limit* and *reproducibility limit* are used as specified in Practice E177.

11.1.4 Any judgment in accordance with 11.1.1 and 11.1.2 would normally have an approximate 95% probability of being correct, however the precision statistics obtained in this interlaboratory study (ILS) must not be treated as exact mathematical quantities that are applicable in all circumstances and uses. The limited number of materials tested and laboratories reporting results guarantees that there will be times when differences greater than predicted by the ILS results will arise, sometimes with considerably greater or smaller frequency than the 95% probability limit would imply. The repeatability limit and the reproducibility limit should be considered as general guides, and the associated probability of 95% as only a rough indicator of what can be expected.

11.2 *Bias*—At the time of the study there was no accepted reference material suitable for determining the bias for this test method, therefore no statement on bias is being made.

11.3 The precision statement was determined through statistical examination of 30 results, from five laboratories, on two castable products.

## 12. Keywords

12.1 castable; consistency; refractories; self-flowing; self leveling; working time

TABLE 2 Self-Flow at 10 min, %

Material	Average, $\bar{x}$ <sup>a</sup>	Repeatability Standard Deviation, $S_r$	Reproducibility Standard Deviation, $S_R$	Repeatability Limit, $r$	Reproducibility Limit, $R$
Medium Weight Self Flow Refractory Castable, 148 to 154 lb/ft <sup>3</sup> (2.37 to 2.47 g/cm <sup>3</sup> )	81.20	8.10	12.81	22.67	35.86
Heavy Weight Self Flow Refractory Castable, 176 to 181 lb/ft <sup>3</sup> (2.82 to 2.90 g/cm <sup>3</sup> )	98.87	6.40	11.50	17.91	32.20

<sup>a</sup> The average of the laboratories' calculated averages.

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or [service@astm.org](mailto:service@astm.org) (e-mail); or through the ASTM website ([www.astm.org](http://www.astm.org)). Permission rights to photocopy the standard may also be secured from the ASTM website ([www.astm.org/COPYRIGHT/](http://www.astm.org/COPYRIGHT/)).*