



# Standard Test Method for Determining Wicking of Fibrous Glass Blanket Insulation (Aircraft Type)<sup>1</sup>

This standard is issued under the fixed designation C1559; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This test method covers a laboratory procedure for evaluating the tendency of, aircraft type, fibrous glass blanket insulation to wick water.

1.2 The wicking characteristics of materials can be affected by environmental conditions such as temperature and humidity. Values obtained as a result of this test method does not adequately describe the wicking characteristics of materials subject to conditions other than those indicated in the test method. (See Specification C800.)

1.3 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

C168 Terminology Relating to Thermal Insulation

C390 Practice for Sampling and Acceptance of Thermal Insulation Lots

C800 Specification for Fibrous Glass Blanket Insulation (Aircraft Type)

E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

## 3. Terminology

3.1 *Definitions*—Terminology C168 shall be considered as applying to the terms used in this specification.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee C16 on Thermal Insulation and is the direct responsibility of Subcommittee C16.33 on Insulation Finishes and Moisture.

Current edition approved March 1, 2015. Published June 2015. Originally approved in 2003. Last previous edition approved in 2009 as C1559 – 04(2009). DOI: 10.1520/C1559-15.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3.1.1 *wicking*—the infiltration of a wetting liquid into a fibrous glass blanket by capillary attraction.

## 4. Summary of Test Method

4.1 The insulation is suspended in de-ionized or distilled water so that the bottom of the specimen is submerged to one inch below the water surface; distance of wicking is noted every 24 h for 96 h and then again at the end of 168 h.

## 5. Significance and Use

5.1 The tendency of the insulation toward wicking can result in an increase in weight and a resultant potential degradation in the properties of the insulation.

## 6. Apparatus

6.1 As described in the Procedure section of this test method.

6.2 *Steel Rule*, accurate to  $\pm 0.05$  in. (1 mm).

## 7. Sampling, Test Specimens, and Test Units

7.1 Six specimens shall be tested for each procedure, cut with the axis parallel to the length and six cut with the axis perpendicular to the length from a representative package. (See Practice C390.)

7.2 The specimens shall be 1- by 6-in. (25.4- by 152.4-mm) by full sample thickness.

7.3 The insulation shall be tested without facing or jacketing.

## 8. Conditioning

8.1 As described in the Procedure section of this test method.

## 9. Procedure A—Wicking as Received

9.1 Condition specimens for at least 24 h at  $73 \pm 4^\circ\text{F}$  ( $23 \pm 2^\circ\text{C}$ ) and  $50 \pm 5\%$  relative humidity.

9.2 With fine wire, fasten loosely six specimens (three cut with the axis parallel to the length and three cut with the axis

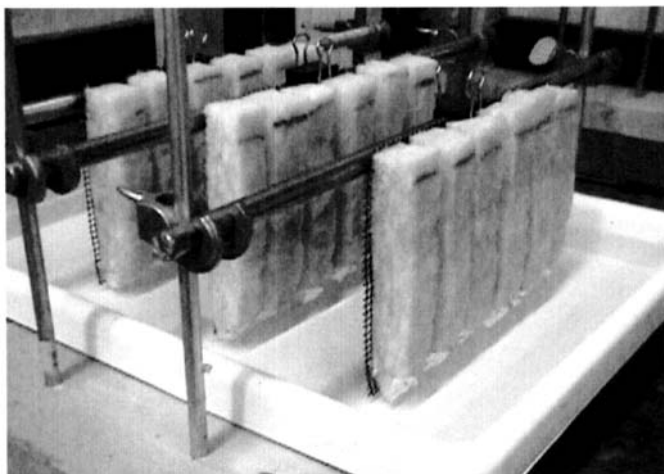


FIG. 1 Typical Specimen Mounting for Wicking Test

perpendicular to the length)<sup>3</sup> to a grease-free 0.025 to 0.035 in. (0.64 to 0.89 mm) 8 by 8 mesh stainless steel wire screen. Position this assembly in an upright position so the ends of the specimens touch the bottom of the container. The 6-in. sample dimension is in a perpendicular direction to the water surface. The specimens must not touch each other or the sides of the container (Fig. 1).

9.3 Pour de-ionized (or distilled) water into the container to a height of 1-in. (25-mm) (Optional: add dye<sup>4</sup> to the water—1 to 2 drops per liter to the water to facilitate marking the extent of wicking). The water shall be at  $68 \pm 4^\circ\text{F}$  ( $20 \pm 2^\circ\text{C}$ ).

9.4 Position the remaining six specimens similarly in another container. Pour de-ionized (or distilled) water into this container to a height of 1-in. (25-mm), again adding dye. Maintain the temperature of this water at  $120 \pm 5^\circ\text{F}$  ( $50 \pm 2^\circ\text{C}$ ) by using a hot plate.

9.5 Note distance of wicking above water surface with steel rule every 24 h in each container for the first 96 h. Then note again after 168 h. Replenish the water daily to maintain water level.

## 10. Procedure B—Wicking after Aging

10.1 Condition a sample of insulation 8- by 14-in. (203- by 356-mm) in a forced air circulating oven at  $160 \pm 5^\circ\text{F}$  ( $71 \pm 3^\circ\text{C}$ ) for two weeks or at least 336 h. The aged specimen shall be tested according to procedure outlined in 9.2 – 9.5.

## 11. Procedure C—Wicking after Leaching

11.1 Condition a sample of insulation 8- by 14-in. (203- by 356-mm) by submerging in an immersion tank of de-ionized (or distilled) water maintained at a temperature of 80 to 85°F (27 to 29°C) for a period of at least 24 h. The tank shall be of such a shape and size that the specimen can be submerged therein with all surfaces of the specimen having full access to

the water. Ratio of specimen to water shall not be less than 1 to 100 by weight. A continuous flow of water shall be supplied to the bottom of the container at the above temperature at a rate of five changes per hour. At the end of the leaching period, the specimen shall be removed from the water, air dried to a constant weight and weighed. The leached specimen shall be tested according to procedure outlined in 9.2 – 9.5.

## 12. Calculation or Interpretation of Results

12.1 Determine the amount of wicking by measurement with a steel rule as described in 6.2.

12.2 Wetting of the submerged portion of the wicking specimens is permissible. Wicking is the distance of wetting above the water surface (average value of center-point measurements of three sides of the wicking specimen-side adjacent to screen surface should not be measured).

12.3 Beads of water are not to be construed as a condition of wetting. The formation of beads of water on the insulation surface indicates water repellency.

12.4 Surface wetting is not considered wicking, but cannot be greater than 1 in. (25.4 mm) when measured from the water line.

## 13. Report

13.1 The report shall include the following:

- 13.1.1 Name and any additional identification of the material tested,
- 13.1.2 Thickness of the material,
- 13.1.3 Number of specimens tested, and
- 13.1.4 The average wicking height according to each condition.

## 14. Precision and Bias

14.1 *Inter-laboratory Test Program*—An inter-laboratory study was run in which randomly selected test specimens of one material (0.42 pcf by 1 in.) were tested for wicking in each of five laboratories with each laboratory testing three specimens per configuration. Practice E691 was followed for the design and analysis of the data. A single laboratory provided all of the test specimens. The details are given in ASTM Research Report RR: RR:C16-1028<sup>5</sup>.

14.2 *Test Result*—The precision information shown below in units of measurement noted is for the comparison of one material and based on an average of 3 tests.

14.3 *Precision*—See Table 1.

14.4 *Bias*—No information can be presented on the bias of the procedure in Test Method C1159 for measuring wicking, because no material having an accepted reference value is available.

## 15. Keywords

15.1 aircraft; aircraft insulation; fibrous glass insulation; wicking

<sup>3</sup> An alternative attachment method would be to attach the specimens to the wire mesh using a hot melt adhesive (at approximately ½ in. below and above the water line, and approximately ½ in. from the top of the specimen).

<sup>4</sup> Dye should be tested to insure that the surface tension of water is not reduced (approximately 72 dynes/cm).

<sup>5</sup> Supporting data have been filed at ASTM International Headquarters and may be obtained by requesting Research Report RR: RR:C16-1028.

**TABLE 1 Water Repellency Round Robin Statistical Results  
Using Standard E691**

Cell Average	Standard Deviation of the Cell Averages	Repeatability Standard Deviation	Reproducibility Standard Deviation	Repeatability Limit <sup>A</sup>	Reproducibility Limit <sup>B</sup>
$\bar{X}$	$S_x$	$S_r$	$S_R$	$r$	$R$
0.22 in.	0.11	0.07	0.11	0.18	0.30

<sup>A</sup> 95 % confidence =  $2.8 \cdot S_r$

<sup>B</sup> 95 % confidence =  $2.8 \cdot S_R$

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or [service@astm.org](mailto:service@astm.org) (e-mail); or through the ASTM website ([www.astm.org](http://www.astm.org)). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>