



Standard Guide for Characterization of Radioactive and/or Hazardous Wastes for Thermal Treatment¹

This standard is issued under the fixed designation C1571; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This guide identifies methods to determine the physical and chemical characteristics of radioactive and/or hazardous wastes before a waste is processed at high temperatures, for example, vitrification into a homogeneous glass, glass-ceramic, or ceramic waste form. This includes waste forms produced by ex-situ vitrification (ESV), in-situ vitrification (ISV), slagging, plasma-arc, hot-isostatic pressing (HIP) and/or cold-pressing and sintering technologies. Note that this guide does not specifically address high temperature waste treatment by incineration but several of the analyses described in this guide may be useful diagnostic methods to determine incinerator off-gas composition and concentrations.

The characterization of the waste(s) recommended in this guide can be used to (1) choose and develop the appropriate thermal treatment methodology, (2) determine if waste pre-treatment is needed prior to thermal treatment, (3) aid in development of thermal treatment process control, (4) develop surrogate waste formulations, (5) perform treatability studies, (6) determine processing regions (envelopes) of acceptable waste form composition, (7) perform pilot scale testing with actual or surrogate waste, and/or (8) determine the composition and concentrations of off-gas species for regulatory compliance.

The analyses discussed in this standard can be performed by a variety of techniques depending on equipment availability. For example, Gas Chromatograph Mass Spectrometry (GC/MS) can be used to measure the amount and type of off-gas species present. However, this standard assumes that such sophisticated equipment is unavailable for radioactive or hazardous waste service due to potential contamination of the equipment. The analyses recommended are, therefore, the simplest and least costly analyses that can be performed and still be considered adequate

1.2 This guide is applicable to radioactive and/or hazardous wastes including but not limited to, high-level wastes,² low-level wastes,³ transuranic (TRU) wastes, hazardous wastes, mixed (hazardous and radioactive) wastes, heavy metal contaminated wastes, and naturally occurring or accelerator produced radioactive material (NARM or NORM) wastes. These wastes can be in the physical form of wet sludges, dried sludges, spent waste water filter aids, waste water filter cakes, incinerator ashes (wet or dry), incinerator blowdown (wet or dry), wastewaters, asbestos, resins, zeolites, soils, unset or unsatisfactory cementitious wastes forms in need of remediation, lead paint wastes, etc. and combinations of the above. This guide may not be applicable to piping, duct work, rubble, debris waste or wastes containing these components.

1.3 This guide references applicable test methods that can be used to characterize hazardous wastes, radioactive wastes, and heavy metal contaminated process wastes, waste forms, NARM or NORM wastes, and soils.

1.4 These test methods must be performed in accordance with all quality assurance requirements for acceptance of the data.

1.5 *This standard may involve hazardous materials, operations, and equipment. This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:⁴

- C92 Test Methods for Sieve Analysis and Water Content of Refractory Materials
- C146 Test Methods for Chemical Analysis of Glass Sand
- C162 Terminology of Glass and Glass Products

² High level waste (HLW) is used as a generic term that includes high level liquid waste (HLLW) and high level radioactive waste (HRW).

³ Low level waste (LLW) is used as a generic term that includes low level liquid waste (LLLW), low level radioactive waste (LLRW) and low activity waste (LAW).

⁴ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

¹ This guide is under the jurisdiction of ASTM Committee C26 on Nuclear Fuel Cycle and is the direct responsibility of Subcommittee C26.07 on Waste Materials.

Current edition approved Jan. 1, 2012. Published January 2012. Originally approved in 2003. Last previous edition approved in 2003 as C1571-03. DOI: 10.1520/C1571-03R12.

- C169** Test Methods for Chemical Analysis of Soda-Lime and Borosilicate Glass
- C242** Terminology of Ceramic Whitewares and Related Products
- C859** Terminology Relating to Nuclear Materials
- C1109** Practice for Analysis of Aqueous Leachates from Nuclear Waste Materials Using Inductively Coupled Plasma-Atomic Emission Spectroscopy
- C1111** Test Method for Determining Elements in Waste Streams by Inductively Coupled Plasma-Atomic Emission Spectroscopy
- C1168** Practice for Preparation and Dissolution of Plutonium Materials for Analysis
- C1317** Practice for Dissolution of Silicate or Acid-Resistant Matrix Samples (Withdrawn 2001)⁵
- C1463** Practices for Dissolving Glass Containing Radioactive and Mixed Waste for Chemical and Radiochemical Analysis
- D1129** Terminology Relating to Water
- D4327** Test Method for Anions in Water by Suppressed Ion Chromatography

2.2 Other Documents:

- US EPA Standard SW846**, Test Methods for Evaluating Solid Waste
Resource Conservation and Recovery Act (RCRA), 40CFR 240-271, November 21, 1976
- DOE Methods for Evaluating Environmental and Waste Management Samples**, March, 1993, DOE.EM-0089T, Rev. 1
- Radioanalytical Technology for 10 CFR Part 61 and Other Selected Radionuclides**, Literature Review, C. W. Thomas, V. W. Thomas, and D. E. Robertson, PNNL-9444, March, 1996

3. Terminology

3.1 Definitions:

3.1.1 *analysis (physical or chemical)*—the determination of physical or chemical properties or composition of a material. **C859**

3.1.2 *byproduct material*—the tailings or wastes produced by the extraction or concentration of uranium or thorium from any ore processed primarily for its source material content, including discrete surface wastes, resulting from uranium solution extraction processes. Underground ore bodies depleted by such solution extraction operations do not constitute “byproduct material.” **10 CFR Part 40**

NOTE 1—A supplementary definition can be found in 10 CFR Part 20; any radioactive material (except special nuclear material) yielded in, or made radioactive by, exposure to the process of producing or utilizing special nuclear material.

3.1.3 *calcine*—to fire or heat a granular or particulate solid at less than, fusion temperature but sufficient to remove most of its chemically combined volatile matter (for example, H₂O, CO₂) and otherwise to develop the desired properties for use.⁶

3.1.4 *debris waste*—solid material exceeding a 60mm particle size that is intended for disposal and that is: a manufactured object; or plant or animal matter; or natural geologic material.⁷

3.1.5 *devitrification*—crystallization of glass. **C162**

3.1.6 *drying*—removal by evaporation, of uncombined water or other volatile substances from a ceramic raw material or product, usually expedited by low-temperature heating. **C242**

3.1.7 *geologic mill tailings*—common rock leftover from mining or oil well drilling operations that may contain hazardous or radioactive constituents, can include natural occurring radioactive material (NORM).

3.1.8 *glass ceramic*—solid material, partly crystalline and partly glass. **C162**

3.1.9 *hazardous waste*—(a) in a broad sense, any substance or mixture of substances having properties capable of producing adverse effects on the health or safety of a human (see also RCRA hazardous waste); (b) any waste that is “listed” in 40CFR Parts 261.31-261.33 or exhibits one or more of the characteristics identified in 40CFR Parts 261.20–261.24, is a mixture of hazardous and nonhazardous waste, or is determined to be hazardous waste by the generator.

3.1.10 *heavy metal contaminated waste*—a common hazardous waste; can damage organisms at low concentrations and tends to accumulate in the food chain. Examples are lead, chromium, cadmium, and mercury.

3.1.11 *high-level liquid waste (HLLW)*—the radioactive aqueous waste resulting from the operation of the first cycle extraction system, or equivalent concentrated wastes from subsequent extraction cycles, or equivalent wastes from a process not using solvent extraction, in a facility for processing irradiated reactor fuels.

3.1.12 *high-level radioactive waste (HLRW or HLW)*—(a) the highly radioactive material resulting from the reprocessing of spent nuclear fuel, including liquid waste produced directly in reprocessing and any solid material derived from such liquid waste that contains fission products (U.S. Code Title 42, Section 10101); (b) liquid wastes resulting from the operation of the first cycle solvent extraction system, or equivalent, and the concentrated wastes from subsequent extraction cycles, or equivalent, in a facility for reprocessing irradiated reactor fuel.

3.1.13 *homogeneous glass*—(1) an inorganic product of fusion that has cooled to a rigid condition without crystallizing (see Terminology **C162**); (2) a noncrystalline solid or an amorphous solid.⁸

3.1.14 *incidental waste*—wastes that are not classified as HLW. NRC has defined three criteria that must be met for a waste to be called incidental waste: (1) wastes that have been processed (or will be further processed) to remove key radionuclides to the maximum extent that is technically and economically practical; (2) wastes that will be incorporated in a solid physical form at a concentration that does not exceed the

⁵ The last approved version of this historical standard is referenced on www.astm.org.

⁶ Perkins, W. W., (Ed.), *Ceramic Glossary*, The American Ceramic Society, 1984.

⁷ *Code of Federal Regulations Title 40*, Volume 19, Part 268.

⁸ Varshneya, A. K., “Fundamentals of Inorganic Glasses,” Academic Press, Boston, MA, 1994.

applicable concentrations for Class C low-level waste; and (3) wastes that are to be managed pursuant of the Atomic Energy Act, so that safety requirements comparable to the performance objectives set out in 10 CFR Part 61, Subpart C are satisfied.

3.1.15 *infrared incinerator*—any enclosed device that uses electric powered resistance heaters as a source of radiant heat followed by an afterburner using controlled flame combustion and which is not listed as an industrial furnace **EPA 40 CFR 260.10**

3.1.16 *incineration*—(1) controlled flame combustion and neither meets the criteria for classification as a boiler, sludge dryer, or carbon regeneration unit, nor is listed as an industrial furnace; or (2) meets the definition of infrared incinerator or plasma arc incinerator **EPA 40 CFR 260.10**

3.1.17 *Joule heating*—heating of glass by passing an electric current through it, the powerful stirring effect of the convection currents created by electric heating causes uniformity of temperature throughout the body of glass and makes it physically homogeneous.⁹

3.1.18 *loss-on-heating (LOH)*—the percent loss in weight of a material at a constant temperature $\geq 105^{\circ}\text{C}$, and for a time long enough, to achieve constant weight, expressed as a percent of the initial weight of the dry material; The fractional or percentage weight loss of a material on heating in air from an initial defined state (usually, dried) to a specified temperature, such as 1000°C , and holding there for a specified period, such as 1 hour. Fixed procedures are designed, usually, such that LOH represents the loss of combined H_2O , CO_2 , certain other volatile inorganics, and combustible organic matter.⁶

3.1.19 *low-activity waste*—the low-activity portion of HLLW that is separated from the HLLW so that it can be classified as LLW and be disposed of as “incidental waste.”

3.1.20 *low-level radioactive waste (LLRW or LLW)*—(a) LLRW is waste that satisfies the definition of LLRW in the Radioactive Waste Policy Amendments Act of 1985; radioactive material that is not high-level radioactive waste, spent nuclear fuel, or byproduct material as given in the Atomic Energy Act of 1954; (b) Low level wastes are also not transuranic wastes as given in the Low Level Radioactive Waste policy Amendments Act and 10 CFR Part 61; (c) waste that (1) is not high-level radioactive waste, spent nuclear fuel, or byproduct material (as defined in section II(e)(2) of the Atomic Energy Act of 1954, (42 U.S.C. 2014(e)(2))); and waste that (2) the NRC, consistent with existing law and in accordance with paragraph (a), classifies as low-level radioactive waste. Low-level radioactive waste (LLW) is a general term for a wide range of wastes. Industries, hospitals and medical, educational, or research institutions; private or government laboratories; and nuclear fuel cycle facilities (for example, nuclear power reactors and fuel fabrication plants) using radioactive materials generate low-level wastes as part of

their normal operations. These wastes are generated in many physical and chemical forms and levels of contamination **10 CFR Part 61**

3.1.21 *mixed waste*—waste that contains both hazardous waste and source special nuclear or byproduct material subject to the Atomic Energy Act (AEA) of 1954;¹⁰ The “radioactive component” refers only to the actual radionuclides dispersed or suspended in the waste substance.¹¹

3.1.22 *mixed waste glass*—a glass comprised of glass forming additives and hazardous waste that contains radioactive constituents.

3.1.23 *natural accelerator produced radioactive materials (NARM)*—radioactive materials not covered under the Atomic Energy Act of 1954 that are naturally occurring or produced by an accelerator. Accelerators are used in sub-atomic particle physics research. These materials have been traditionally regulated by States. NARM waste with more than 2 nCi/g of ^{226}Ra or equivalent is commonly referred to as discrete NARM waste; below this threshold, the waste is referred to as diffuse NARM waste. NARM waste is not covered under the Atomic Energy Act, it is not a form of LLW, and it is not regulated by Nuclear Regulatory Commission.

3.1.24 *naturally occurring radioactive materials (NORM)*—NORM refers to materials not covered under the Atomic Energy Act whose radioactivity has been enhanced (radionuclide concentrations are either increased or redistributed where they are more likely to cause exposure to man) usually by mineral extraction or processing activities. Examples are exploration and production wastes from the oil and natural gas industry and phosphate slag piles from the phosphate mining industry. This term is not used to describe or discuss the natural radioactivity of rocks and soils, or background radiation, but instead refers to materials whose radioactivity is technologically enhanced by controllable practices. Note this definition is sometimes called technically enhanced NORM or TENORM.

3.1.25 *plasma arc incinerator*—any enclosed device using a high intensity electrical discharge or arc as a source of heat followed by an afterburner using controlled flame combustion and which is not listed as an industrial furnace. **EPA 40 CFR 260.10**

3.1.26 *radioactive*—of or exhibiting radioactivity;¹² a material giving or capable of giving off, radiant energy in the form of particles or rays, as alpha, beta, and gamma rays, by the disintegration of atomic nuclei; said of certain elements, such as radium, thorium, and uranium, and their products.¹³

3.1.27 *radioactivity*—spontaneous nuclear disintegration with emission of corpuscular or electromagnetic radiation, or both. **D1129**

3.1.28 *radioactive waste*—solid, liquid, and gaseous materials from nuclear operations that are radioactive or become

¹⁰ *Federal Facilities Compliance Act*, 1992, (RCRA Section 1004 (41,42,USC 6903)41)).

¹¹ *DOE Order 5400.3*.

¹² *The American Heritage Dictionary*, Houghton Mifflin, 2nd Edition, The World Publishing Co., New York, 1973.

¹³ *Webster's New Twentieth Century Dictionary*, 1973.

⁹ Meigh, E., “Electric Melting in the Glass Industry,” Chapter 7, A.G. Pincus and G.M. Kiken, Books for Industry, New York, NY, 1976.

radioactive and for which there is no further use. Wastes are generally classified as high-level (having radioactivity concentrations of thousands of curies per gallon or cubic foot), low-level (on the order of 1 microcurie per gallon or cubic foot), or intermediate level (between these extremes). **10 CFR**

Parts 60 and 61

3.1.29 *residual radioactive material*—(1) waste (which the secretary of energy determines to be radioactive) in the form of tailings resulting from the processing of ores for the extraction of uranium and other valuable constituents of the ore; and (2) other waste (which the secretary of energy determines to be radioactive) at the processing site which relates to such processing, including any residual stock of unprocessed ores or low grade-materials. This term is used only with respect to materials at sites subject to remediation under Title I of the Uranium Mill Tailings Radiation Control Act of 1978, as amended. **10 CFR Part 40**

3.1.30 *RCRA hazardous waste*—a solid waste that exhibits a characteristic of a hazardous waste or is, or contains a listed hazardous waste. A RCRA solid waste may be a solid, liquid, or gas. **40 CFR Part 261.3**

3.1.31 *RCRA listed waste*—a solid waste that has been listed by EPA by virtue of its toxicity characteristics or because of the industrial process from which it is derived. **40 CFR Part 261.11**

3.1.32 *simulated waste glass*—a glass comprised of glass forming additives with simulants of, and/or actual chemical species in radioactive wastes, mixed wastes, or heavy metal wastes.

3.1.33 *slag*—glass that contains crystalline material including metal inclusions upon exiting a thermal treatment unit (see also *glass-ceramic*).

3.1.34 *sludge*—any solid, semi-solid, or liquid waste generated from a municipal, commercial, or industrial waste water treatment plant, water supply treatment plant, or air pollution control facility exclusive of the treated effluent from a wastewater treatment plant. **40 CFR 260.10**

3.1.35 *speciation*—a calculation of the chemical species (for example, oxides, hydroxides carbonates, sulfates in wt%) present in a waste based upon the elemental analyses of a waste (in wt%) in order to predict the fractionation of each species into the final wasteform or into the off-gas.

3.1.36 *treatability study*—a study in which a hazardous waste is subjected to a treatment process to determine (1) whether the waste is amenable to the treatment process, (2) what pretreatment is required, (3) optimal process conditions, (4) efficiency of a treatment process, and (5) characteristics and volumes of residuals. **40 CFR 260.10**

3.1.37 *TRU waste*—waste containing more than 100 nanocuries of alpha-emitting transuranic isotopes, with half-lives greater than twenty years, per gram of waste, except for (1) high-level radioactive waste; (2) wastes that DOE has determined, with the concurrence of EPA, do not need the degree of isolation required by EPA's high level waste rule (40 CFR 191); or (3) has approved for disposal on a case-by-case basis in accordance with NRC's radioactive land disposal

regulation (10 CFR Part 61). TRU is not generally found outside the DOE complex and is mainly produced from the reprocessing of spent nuclear fuel, nuclear weapons production, and reactor fuel assembly. TRU wastes mainly emit alpha particles as they break-down. DOE categorizes TRU as either Contact Handled (CH) or Remote Handled (RH) with RH being the more radioactive of the two.

3.1.38 *uranium milling*—any activity that results in the production of byproduct material.

3.1.39 *uranium mill tailings*—see *byproduct material* and/or *residual radioactive material*.

3.1.40 *vitrification*—the process of fusing waste or simulated waste with glass making chemicals at elevated temperatures to form a waste glass or a simulated waste glass. **C162**

3.1.41 *waste*—any residue containing radioactive or hazardous materials not currently considered useful or economically recoverable. **C859**

3.1.42 *waste characterization*—sampling, monitoring, and analysis activities to determine the extent and nature of a waste.

3.1.43 *waste form*—the waste materials and any encapsulating or stabilizing matrix/materials.

3.1.44 *weight percent solids*—the percent weight remaining after a material has been dried (see also *drying*) at 105°C, for a time long enough, to achieve constant weight, expressed as a percent of the initial weight of the material, for example, the initial weight of the material minus the amount of water or other volatiles lost upon drying at 105°C.

4. Significance and Use

4.1 This guide identifies methods to determine the physical and chemical characteristics of a variety of hazardous and/or radioactive wastes including heavy metal contaminated wastes. These wastes can be in the physical form of sludges (wet or dry), spent waste water filter aids, waste water filter cakes, incinerator ashes (wet or dry), incinerator blowdown (wet or dry), asbestos, resins, zeolites, soils, unset or unsatisfactory cementitious waste forms in need of remediation, lead paint wastes, radioactively or non-radioactively contaminated asbestos, geologic mill tailings (also known as byproduct materials) and other naturally occurring or accelerator produced radioactive materials (NORM and NARM), etc. and combinations of the above. This guide may not be applicable to piping, duct work, rubble, debris waste or wastes containing these components.

4.1.1 This guide identifies the physical and chemical characteristics useful for developing high temperature thermal treatment methodologies for a variety of hazardous and/or radioactive process wastes and soils including heavy metal contaminated wastes. The waste characteristics can be used to (1) choose and develop the thermal treatment methodology, (2) determine if waste pretreatment is needed, (3) aid in development of thermal treatment process control, (4) develop surrogate waste formulations, (5) perform treatability studies, (6) determine processing regions (envelopes) of acceptable waste form composition, and/or (7) perform pilot scale testing with

actual or surrogate waste, and/or (8) determine the composition and concentrations of off-gas species for regulatory compliance.

4.2 This guide identifies applicable test methods that can be used to measure the desired characteristics of the hazardous and/or radioactive wastes described in 4.1. The analyses discussed in this standard can be performed by a variety of techniques depending on equipment availability. For example, Gas Chromatograph Mass Spectrometry (GC/MS) can be used to measure the amount and type of off-gas species present. However, this standard assumes that such sophisticated equipment is unavailable for radioactive or hazardous waste service due to potential contamination of the equipment. The analyses recommended are, therefore, the simplest and least costly analyses that can be performed and still considered adequate. Not every characteristic given in this guide is necessary for every waste (see Fig. 1). Cation analysis is necessary for every waste in order to determine whether the final waste form will be a homogeneous glass, a glass-ceramic, or a slag (see Appendix X1).

4.2.1 Waste Analysis Method A is applicable when it is desired to know the amount and type of volatiles to be expected during thermal treatment and their compatibility with the thermal treatment and off-gas unit materials of construction and design capacity. These methods may be used to determine incinerator off-gas composition and concentrations.

4.2.2 Waste analysis Method A is applicable when it is necessary to know the amount of organics in the waste independently of the amount of other volatile constituents present for safety concerns. These methods may be used to determine incinerator off-gas composition and concentrations.

4.2.3 Waste analysis Method A is applicable when it is necessary to know if molten salt formation and accumulation in a thermal treatment unit in the presence of water vapor may be a safety concern.

4.2.4 Waste Analysis Methods B and C are applicable when it is desired to only know the amount of volatiles to be expected during thermal treatment, for example, when speciation of the volatiles and potential molten salt formation is not of concern. These methods may be used to determine the total concentration of incinerator off-gases.

4.3 Data from these tests may form part of the larger body of data that are necessary in the logical approach to development of high temperature treatment and/or pretreatment methodologies for a variety of hazardous and/or radioactive wastes as described in 4.1.

5. Summary of Waste Characteristics

5.1 Table 1 lists the waste characteristics that should be considered before a waste is processed in a high temperature thermal treatment apparatus. Table 1 describes the rationale for considering each characteristic.

5.2 Test Method A provides analysis of the weight percent solids, identification of the constituents and their concentrations that will vaporize during thermal treatment, identification of problematic anions that can attack materials of construction and/or form hazardous molten salt layers, and identification of

the waste constituents and their concentrations that will be incorporated into the final glass, glass-ceramic, or slag.

5.3 Test Methods B and C can be used to determine total wt% LOH but not the LOH speciation. Test Methods B and C will also not provide organic analyses, anion analyses, and reduction/oxidation analyses.

6. Test Method A

NOTE 2—Note Method C should be used rather than Method B when the waste is very refractory.

6.1 Waste analysis Method A uses wastes that have been dried at $105 \pm 2^\circ\text{C}$. The waste analysis strategy for Method A is given in Fig. 2. Method A provides analysis of the weight percent solids, identification of the constituents and their concentrations that will vaporize during thermal treatment, identification of problematic anions that can attack materials of construction and/or form hazardous molten salt layers, and identification of the waste constituents and their concentrations that will be incorporated into the final glass, glass-ceramic, or slag.

6.2 *Weight Percent Solids/Loss-on-Heating*—Weigh empty crucible. Weigh waste plus crucible before drying. Dry waste in crucible at 105°C until a constant weight is achieved to determine the weight percent (wt%) solids and Loss-On-Heating (wt% LOH) of water, if any, at this temperature. X-ray diffraction (XRD) analysis of the dried waste determines what phases are present. If hydroxide and/or carbonate species are identified in XRD analysis, additional Loss-on-Heating analyses at 300°C and 1000°C will be necessary (see 6.8 and 6.9). Calculate the wt% solids and wt% LOH at 105°C by the following:

$$\text{wt\% solids} = \{(W_3 - W_1)_{105^\circ\text{C}} / (W_2 - W_1)_{\text{rt}}\} \cdot 100 \quad (1)$$

$$(\text{wt\% LOH})_{105^\circ\text{C}} = \{(W_2 - W_1)_{\text{rt}} - (W_3 - W_1)_{105^\circ\text{C}}\} / \{(W_2 - W_1)_{\text{rt}}\} \cdot 100$$

$$\text{wt\% solids} + (\text{wt\% LOH})_{105^\circ\text{C}} = 100\%$$

where:

W_1 = weight of the crucible,

W_2 = weight of crucible and waste prior to drying, and

W_3 = weight of crucible and waste after drying at 105°C .

6.2.1 The weight % solids and the wt% (LOH) $_{105^\circ\text{C}}$ should sum to 100 %.

6.3 *Cation Analyses*—Dissolution using fuming perchloric acid as used in the commercial glass industry (see Methods C169) is not recommended for radioactive samples as the fumes can cause radioactive species to become airborne and present inhalation and radionuclide uptake hazards to the user. Alternative dissolution methodologies are given in 6.3.1 – 6.3.5.

6.3.1 *HF/HNO₃ Microwave Dissolution (ASTM C1463)*—This methodology may be used to dissolve waste(s) but the user is cautioned that this dissolution methodology must be coupled with other dissolution methodologies in order for a complete analysis to be achieved. The HF in this dissolution methodology compromises analysis of elements such as Si which form SiF₄ colloids which precipitate from the dissolution extract before Inductively Coupled Plasma Atomic Emission Spectroscopy (ICP-AES), Atomic Absorption (AA)

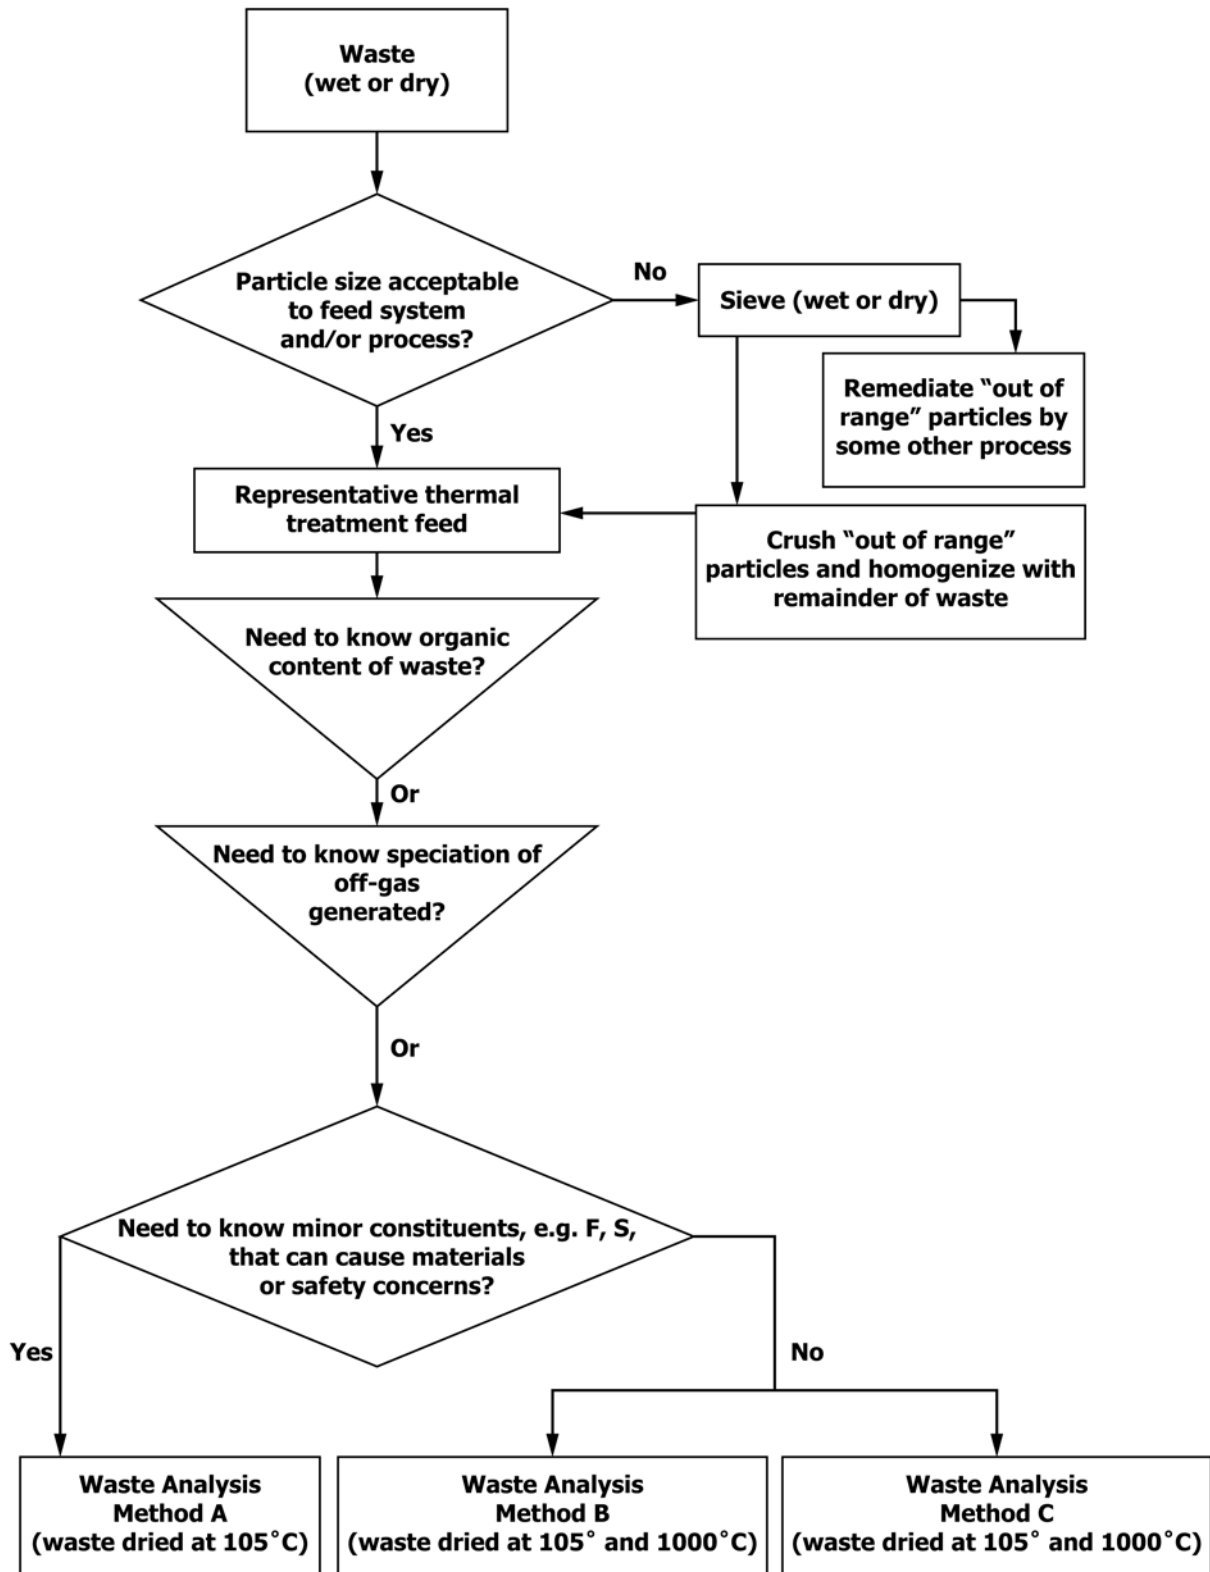


FIG. 1 Choice of Test Methods

TABLE 1 Waste Characteristics to be Considered Prior to High Temperature Thermal Treatment

Waste Attribute	Rationale
Particle Size	Determination of adequacy of feed system, mixing system, and homogeneity of final waste form, for example, large (≥ 2.5 cm) dense particles like pebbles may not vitrify. See Test Methods C92
Homogeneity	Determination of number of replicate waste analyses that need to be performed; to design process control system to handle waste variability; determination of whether additional process vessels for homogenization of waste are necessary
Total Loss-On-Heating (LOH) at Treatment Temperature in wt%	Sizing of off-gas system to handle total volume of volatiles, for example, steam (H_2O , OH^\cdot), CO_2 , SO_x , NO_x that are generated during thermal processing, for example, can range from 1 to 98 % or evaluation of potential waste loading.
LOH speciation	Adequacy of off-gas system components and materials of construction to handle the types of off-gas anticipated, for example, acid gasses (NO_x as HNO_3 vapor, SO_x as H_2SO_4 vapor), F, Cl, etc.; design adequate filtration.
Total Radioactivity	Hazards analysis, for example, shielding and safety concerns; design of adequate filtration to achieve desired decontamination factors (DF's) before off-gas is quenched and/or released to the atmosphere.
Radionuclide or Hazardous Constituent Speciation	Choice of thermal treatment temperature, for example, radionuclides as Cs-137 and Tc-99 are volatile at $\geq 1150^\circ C$, to ensure that radionuclides are retained in the vitrified waste form
Volatile Constituent Speciation	Choice of thermal treatment temperature for minimization or elimination of volatilization (secondary waste generation) of hazardous components such as Se, As, Tc-99, Cs-137. Determination of whether SO_x will be liberated as SO_3 , SO_2 or S_2 depending on treatment temperature and oxidation state of the waste, for example, at $1150^\circ C$ ~50 % SO_4^{2-} is volatilized while at ~1500°C about 90 % is volatilized.
Organics (TC = Total Carbon and TOC = Total Organic Carbon) in wt%	Safety concerns, >5 wt% organics can cause safety concerns in certain types of thermal treatment units; design pretreatment methods to limit organics to <5 wt%.
Anions (in wt%)	wt% LOH speciation, for example, SO_x , NO_x , F, and Cl specifically; needed to know potential for molten salt (for example, (K,Na,Cs)Cl, (K, Na,Cs)F, (K,Na, Cs) $_2SO_4$) as a secondary phase in the vitrified waste form, for example, molten salt layers can cause steam explosions in certain types of thermal treatment units; needed to know for potential attack on materials of construction of thermal treatment unit, for example, electrodes and refractories; needed to know if velocity in off-gas line is adequate to prevent pluggage from molten salt accumulations. ⁴
Cations (in wt%)	Determination of glass forming or slagging system of choice (see Appendix X1); to maximize waste loading; choice of glass additives; potential attack on materials of construction of thermal treatment unit, for example, electrodes and refractories
Reduction/Oxidation (REDOX) Potential	Choice of pretreatment; addition of oxidizers as glass formers to prevent formation of metallic and/or sulfide phases which can cause certain thermal treatment units with metallic electrodes to short and/or attack materials of construction; design of pretreatment.

⁴ Jantzen, C. M., Choi, A.S., Randall, C. T., "Glass Melter Off-gas System Pluggages: Cause, Significance, and Remediation," *Proceedings of the 5th International Symposium on Ceramics in Nuclear Waste Management*, G. G. Wicks, D. F. Bickford, and R. Bunnell (Eds.), American Ceramic Society, Westerville, OH, 621-630 (1991); Jantzen, C. M., "Characterization of Off-Gas System Pluggages, Significance for DWPF and Suggested Remediation," *U.S. DOE Report WSRC-TR-90-205*, 1991, p. 72; Jantzen, C. M., Choi, A. S., and Randall, C. T., "Remediation of Off-Gas System Deposits in a Radioactive Waste Glass Melter," *High Level Radioactive Waste and Spent Fuel Management*, Vol 2, S. C. Slate, L. C. Oyen, K. J. Lee, and W. Z. Oh (Eds.), Korean Nuclear Society, Seoul, Korea, 1991, pp. 21-32.

Spectroscopy, Atomic Emission (AE) spectroscopy, and/or ICP Mass Spectroscopy (ICP-MS) analysis can be completed.

6.3.2 Na_2O_2 or KOH Fusion/HCl Dissolution (ASTM C1317 and C1463)—This dissolution methodology may be used to dissolve waste(s) but the user is cautioned that these methods cannot be used for analysis of Na^+ , K^+ and other alkalis that may be major components or impurities in the starting Na_2O_2 or KOH. The sample is fused with Na_2O_2 or KOH at elevated temperature and the fused residue dissolved in water and then acidified with HCl. Dissolutions with HCl uptake give excellent reproducible extracts that can be analyzed by Inductively Coupled Plasma Atomic Emission Spectroscopy (ICP-AES), Atomic Absorption (AA) Spectroscopy, and/or ICP Mass Spectroscopy (ICP-MS) for most elements including Si, Al, B, and radionuclides.

6.3.3 Aqua Regia Dissolution¹⁴— This dissolution methodology may be used to dissolve waste(s) and is extremely aggressive to minor hazardous and heavy metal constituents. The analytic extract can be analyzed by Inductively Coupled

Plasma Atomic Emission Spectroscopy (ICP-AES), Atomic Absorption (AA) Spectroscopy, and/or ICP Mass Spectroscopy (ICP-MS).

6.3.4 Alkali Metaborate Dissolution (ASTM C1463)¹⁵— This dissolution methodology may be used to dissolve waste(s) and is extremely aggressive. The sample is fused with $LiBO_2$ or $NaBO_2$ at elevated temperature ($900^\circ C$) for 15 min in a platinum crucible. The user is cautioned that this method prohibits analysis of B^{+3} and Na^+ or Li^+ depending on which alkali metaborate is chosen as a fusion flux. However, if waste is known not to contain Li^+ or B^{+3} this method can be used for all other cations and radionuclides. The bottom of the crucible is quenched in water and the fused material is dissolved in 4 % HNO_3 and diluted as necessary. The analytic extract can be analyzed by Inductively Coupled Plasma Atomic Emission Spectroscopy (ICP-AES), Atomic Absorption (AA) Spectroscopy, and/or ICP Mass Spectroscopy (ICP-MS).

¹⁴ Coleman, C. J., "Aqua Regia Dissolution of Sludge for Elemental Analysis," *WSRC-RP-90-371*, 1990.

¹⁵ Crow, R. F., and Connolly, J. D., "Atomic Absorption Analysis of Portland Cement and Raw Mix Using Lithium Metaborate Fusion," *Jour. Test. Evaluation*, Vol. 1, 1973, pp. 382-393.

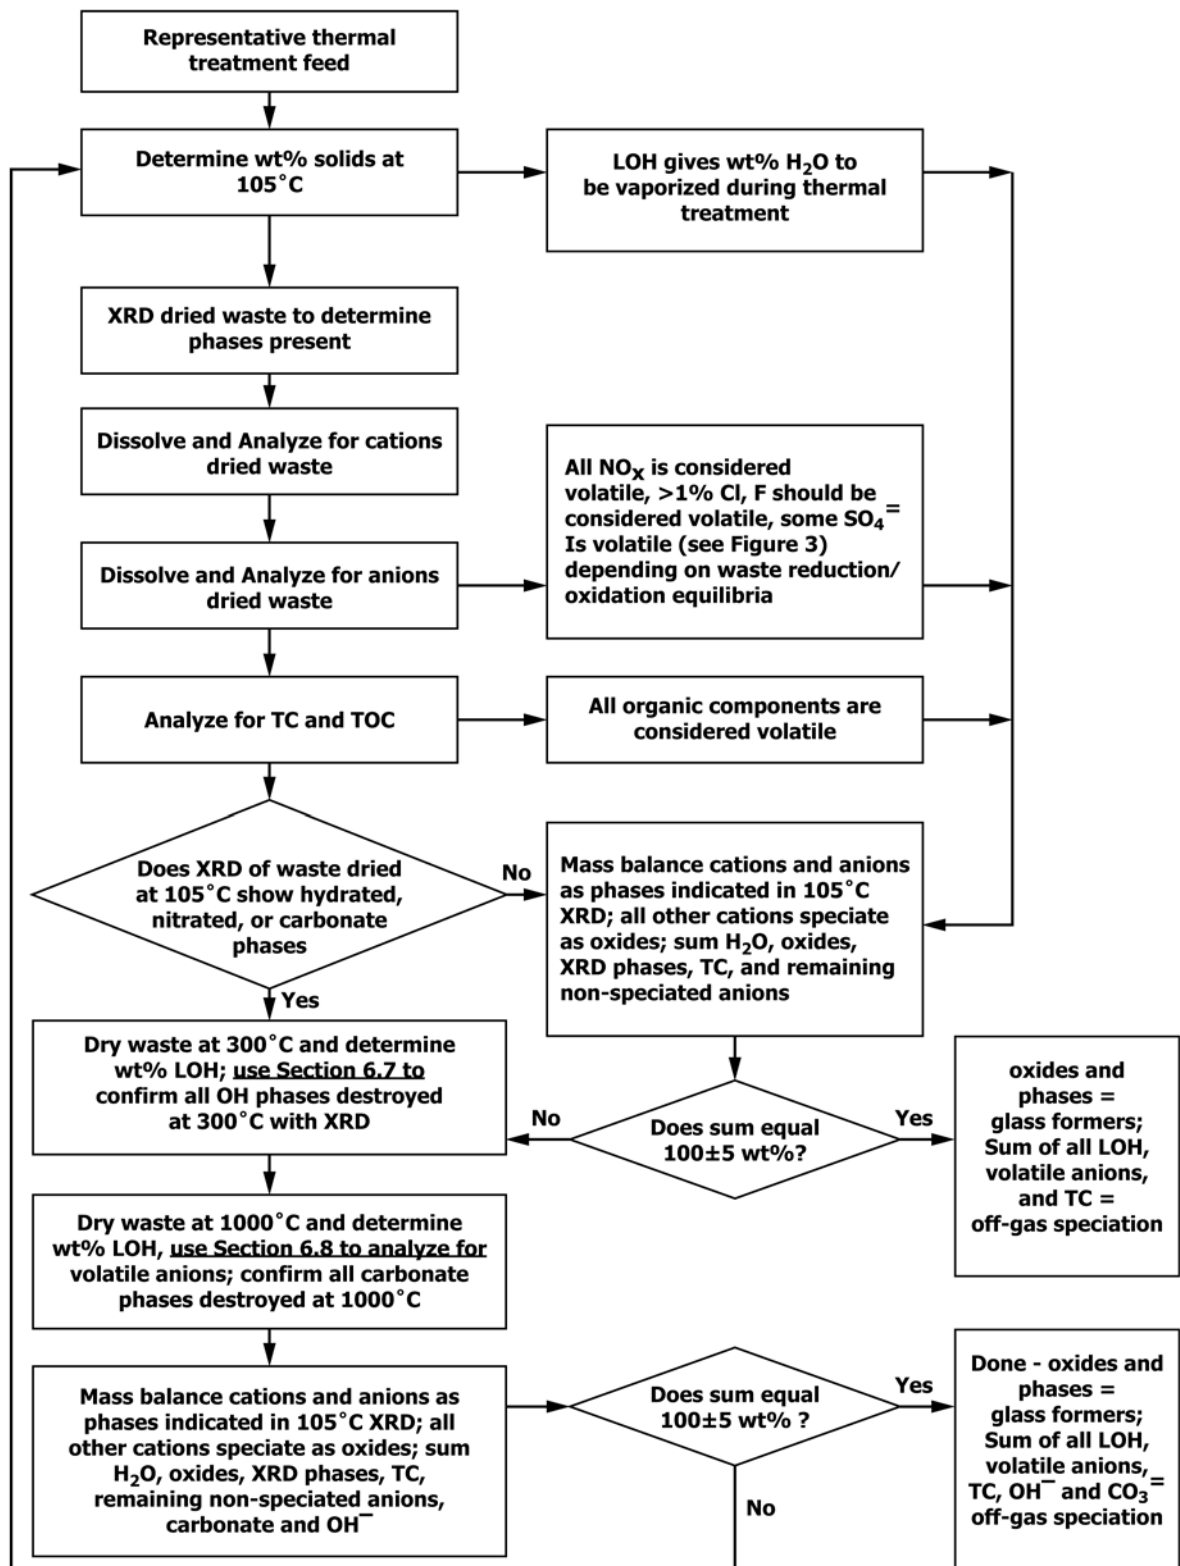


FIG. 2 Waste Analysis Method A

6.3.5 EPA SW-846 Method 3050 Dissolution—This methodology may be used to dissolve waste(s) for analysis but the user is cautioned that this dissolution is primarily an extract of elements which are soluble in nitric acid from the waste matrix. This methodology, and other wet digestions that either do not incorporate HF, or do not fuse the sludge or soil in a flux before dissolution, may not lead to dissolution of the metals incorporated into aluminosilicate matrices (for example, soils, sediment, ashes, sludges, asbestos, etc.) and thus may underestimate constituents of potential interest (for example, Si) to the application of a given treatment technology.^{16,17} The leachate can be analyzed by Inductively Coupled Plasma Atomic Emission Spectroscopy (ICP-AES), Atomic Absorption (AA) Spectroscopy, and/or ICP Mass Spectroscopy (ICP-MS).

6.4 Anion Analysis:

6.4.1 Na₂O₂ Fusion/H₂O Dissolution (ASTM C1317)—A sample of waste is fused with Na₂O₂ or KOH at elevated temperature and the fused residue dissolved in water. The residue is NOT dissolved in HCl per Practice C1317. Dissolutions with H₂O provide analytic extracts which can be analyzed by Ion Chromatography (IC) see Test Method D4327 or Ion Selective Electrode (ISE) for wt% anions of concern.

6.5 Radiochemical Analysis—or radionuclides which are not dissolved by the above methodologies, and cannot be measured by ICP-AES or ICP-MS consult “DOE Methods for Evaluating Environmental and Waste Management Samples” (March, 1993, DOE-EM-0089T, Rev. 1), and/or EPA SW846, and/or Radioanalytical Technology for 10 CFR Part 61 and Other Selected Radionuclides, Literature Review, C. W. Thomas, V. W. Thomas, and D. E. Robertson, PNNL-9444 (March, 1996), and/or Practice C1168.

6.6 Carbon Analysis—Typically knowledge of the amounts of Total Carbon (TC) and Total Inorganic Carbon (TIC) is sufficient for determination of the appropriate thermal treatment option. Total Organic Carbon (TOC) is determined as the difference between TC and TIC (refer to EPA SW846). If detailed speciation of organics is deemed necessary consult “DOE Methods for Evaluating Environmental and Waste Management Samples” (March, 1993, DOE-EM-0089T, Rev. 1), and/or EPA SW846.

6.7 Fe⁺²/Fe⁺³ or Fe⁺²/ΣFe Analysis—For wastes containing large concentrations of iron the colorimetric analysis by Baumann¹⁸ or Goldman,¹⁹ or Mossbauer Spectroscopy are the preferred methodologies. In the Baumann methodology, shown

to be the simplest to perform remotely on highly radioactive wastes,¹⁸ the waste dried at 105°C is dissolved by H₂SO₄/HF in the presence of NH₄VO₃ and the amount of Fe⁺² is measured colorimetrically. All of the iron is reduced to the Fe⁺² state by ascorbic acid and the total iron (ΣFe) measured. From these two measurements either the Fe⁺²/Fe⁺³ or Fe⁺²/ΣFe ratios can be calculated. Alternatively, Test Methods C146 can be used when the iron concentrations are expected to be less than ~1 wt% (Test Methods C146). The iron redox ratios serve as an indicator of the oxidation/reduction equilibria expected in the thermal treatment unit and in the final vitrified product. Known²⁰ electro-motive-forces (EMF) can be used to determine the oxidation state of other species, S versus SO₄²⁻ once the indicator iron redox ratios are known.

6.8 Calculation of OH⁻ Content of the Waste—Weigh empty crucible. Weigh waste plus crucible before drying. Dry waste at ~300°C until a constant weight is achieved to determine the Loss-on-Heating at 300°C. Perform phase analysis by x-ray diffraction on the dried sample. Examine the XRD pattern to determine if the hydroxide phases identified in 6.2 have been destroyed by the 300°C heat treatment. Calculate the wt% LOH at 300°C by the following:

$$(\text{wt\% LOH})_{300^{\circ}\text{C}} = \left\{ \left\{ (W_2 - W_1)_{\text{H}_2\text{O}} - (W_3 - W_1)_{300^{\circ}\text{C}} \right\} / (W_2 - W_1)_{\text{H}_2\text{O}} \right\} \cdot 100 \quad (2)$$

where:

W_1 = weight of the crucible,
 W_2 = weight of crucible and waste prior to heating, and
 W_3 = weight of crucible and waste after drying at 300°C.

6.8.1 The difference between the (wt% LOH)_{105°C} and the (wt% LOH)_{300°C} is a good approximation of the sum of the weight percent of structurally bound OH⁻ in the waste species, for example, Al(OH)₃, Fe(OH)₃, etc. and the Total Organic Carbon (TOC).

6.8.2 Calculate the OH⁻ contribution of the waste by the following:

$$\text{OH}^- (\text{wt\%}) \approx (\text{wt\% LOH})_{300^{\circ}\text{C}} - (\text{wt\% LOH})_{105^{\circ}\text{C}} - \text{TOC} \quad (3)$$

6.9 Calculation of CO₃⁼ Content (wt%) of the Waste—Ideally, the amount of CO₃⁼ can be measured by Gas Chromatography and Mass Spectrometry (GC/MS). However, for applications where a GC/MS is not available and/or the waste is highly variable, the following estimations on a larger bulk sample are sufficient to determine if a waste is a candidate for thermal treatment, the approximate volume reduction that will be achieved, and the needed capacity for the off-gas treatment.

6.9.1 Weigh empty crucible. Weigh waste plus crucible before drying. Dry waste at ~1000°C until a constant weight is achieved to determine the Loss-on-Heating at 1000°C. Perform phase analysis by x-ray diffraction on the dried sample. Examine the XRD pattern to determine if any carbonate phases identified in 6.2 have been destroyed by the 1000°C heat treatment.

6.9.2 Calculate the wt% LOH at 1000°C by the following:

¹⁶ Gao, D., and Silox, G. D., “The Effect of Treatment Temperature on Metal Recovery from a Porous Silica Sorbent by EPA Method 3050 and by an HF-Based Methodology,” *Air & Waste*, Vol. 43, 1993, p. 1004.

¹⁷ Bostick, W. D., Hoffmann, D. P., Stevenson, R. J., Richmond, A. A., and Bickford, D. F., “Surrogate Formulations for Thermal Treatment of Low-Level Mixed Waste, Part IV: Wastewater Treatment Sludges,” *U.S. DOE Report DOE/MWIP-18*, Martin Marietta Energy Systems, Inc., January, 1994.

¹⁸ Baumann, E. W., “Colorimetric Determination of Iron (II) and Iron (III) in Glass,” *Analyst*, Vol 117, 1992, pp. 913-916. “Colorimetric Determination of Iron (II) and Iron (III) in Glass,” *Analyst*, Vol 117, 1992, pp. 913-916.

¹⁹ Goldman, D. S., “Investigation of Potential Analytical Methods for Redox Control of the Vitrification Process,” *USDOE Report PNL-5581*, Battelle-Pacific Northwest Laboratory, Richland, WA, November 1985.

²⁰ Schreiber, H. D., and Hockman, A. L., “Redox Chemistry in Candidate Glasses for Nuclear Waste Immobilization,” *J. Am. Ceram. Soc.*, 70 [8], 1987, pp. 591-594.

$$(\text{wt\% LOH})_{1000^{\circ}\text{C}} = \quad (4)$$

$$\{(W_2 - W_1)_{\text{rt}} - (W_3 - W_1)_{1000^{\circ}\text{C}}\} / \{(W_2 - W_1)_{\text{rt}}\} \cdot 100$$

where:

W_1 = weight of the crucible,

W_2 = weight of crucible and waste at room temperature (rt), and

W_3 = weight of crucible and waste after drying at 1000°C.

6.9.3 The difference between the (wt% LOH)_{300°C} and the (wt% LOH)_{1000°C} is a good approximation of the weight percent CO₃⁼ in the waste species, for example, CaCO₃, and the nitrate (wt% NO₃⁻) and nitrite (wt% NO₂⁻) content. Since the nitrate (wt% NO₃⁻) and nitrite (wt% NO₂⁻) content have been measured in 6.4, the CO₃⁼ wt% contribution of the waste can be calculated by the following:

$$\text{CO}_3^{\text{=}}(\text{wt\%}) \approx \quad (5)$$

$$(\text{wt\% LOH})_{1000^{\circ}\text{C}} - (\text{wt\% LOH})_{300^{\circ}\text{C}} - (\text{wt\% NO}_2^-) - (\text{wt\% NO}_3^-)$$

6.9.4 CO₃⁼ wt% can also be obtained from the Total Inorganic Carbon (wt% TIC) as defined in 6.6.

6.10 *Complete Waste Analysis After Drying at 105°C*—In order to obtain a complete waste analysis, waste should be dried at 105°C and dissolved by more than one of the methods given in 6.3 and 6.4: no one dissolution methodology gives all of the major cations of concern. Combinations of the dissolution methodologies and analytic methodologies given above need to be employed as in the following example:

6.10.1 Dissolution by LiBO₂ fusion with an HNO₃ uptake:

6.10.1.1 ICP (see Test Methods C1109 and/or Test Method C1111)—Typically cations such as Al, Ca, Fe, Mg, Mn, Si, Cr, Ni, Na, Zr, Sr, Ti, P, Ba, Pb, Mo, Zn, Cu, U are obtained. See 6.5 for radiochemical analyses of concern.

6.10.1.2 AA—Typically cations such as Ni, Na, K, Si are obtained. Note that this is one of the few methods available for the determination of potassium (K).

6.10.2 Dissolution by Na₂O₂ fusion with an HCl uptake:

6.10.2.1 ICP (see Test Methods C1109 and/or Test Method C1111)—Typically cations such as Al, B, Ca, Fe, Mg, Mn, Si, Cr, Li, Sr, Ti, P, Ba, Pb, Mo, Zn, Cu, U are obtained. Na cannot be determined with this method. If a zirconia crucible is used for the fusion, then Zr cannot be determined by this method. If a nickel crucible is used for the fusion, then Ni cannot be determined by this method. See 6.5 for radiochemical analyses of concern.

6.10.3 Dissolution by Na₂O₂ with a H₂O uptake:

6.10.3.1 IC for SO₄⁼, NO₃⁻, NO₂⁻, PO₄⁼

6.10.3.2 ISE for Cl⁻ and F⁻

6.10.4 Loss-On-Heating up to ~1000°C:

6.10.4.1 $\Sigma \approx \text{OH}^- + (\text{CO}_3^{\text{=}}) + (\text{NO}_2^-) + (\text{NO}_3^-) + \text{TOC}$

6.11 *Analysis Accuracy by Mass Balance for Method A:*

6.11.1 *Cations*—All of the cation element weight percents determined in 6.3 should be converted to equivalent oxide concentrations in weight percent since thermally treated waste forms are primarily oxide based (Table 2). The relative amounts of FeO and Fe₂O₃ shown in Table 2 are derived from the redox analyses. All of the Mn will be present as MnO if there is any FeO or Fe⁺² component in the waste.

6.11.2 *Volatile Anions*—For the purpose of mass balance, the wt% NO₂⁻ and wt% NO₃⁻ anionic species need not be associated with their respective cations, for example, NaNO₃, since the wt% NaNO₃ component is broken down in the mass balance calculation to wt% Na₂O in the waste form and wt% NO₃⁻ + wt% NO₂⁻ in the off-gas. Nitrates may enter the off-gas as NO_x species, N₂ or HNO₃ depending on temperature, redox, and the presence of water vapor. For the purpose of mass balance calculations, speciation as wt% NO₃⁻ and wt% NO₂⁻ is sufficient. The wt% CO₃⁼ anionic species should be calculated as wt% CO₂ since waste species such as CaCO₃ is represented in the mass balance as wt% CaO in the waste form plus wt% CO₂ in the off-gas by the following relationship:

$$\text{wt\% CO}_2 \text{ gas} = \text{CO}_3^{\text{=}}(\text{wt\%}) \cdot 44/60 \quad (6)$$

where the ratio of 44/60 is the ratio of the molecular weights of CO₂/CO₃⁼.

6.11.3 *Semi-Volatile Anions*—For the purpose of mass balance, fluoride, chloride and sulfate can be associated as the alkali species present in the waste, for example, (Na,Cs,K)F, CaF₂, (Na,Cs,K)Cl, (Na,Cs,K)₂SO₄ (if known), since they may be semi-volatile as NaF, NaCl, Na₂SO₄ depending on the thermal treatment temperature, the waste form composition, and the off-gas line temperature (see Table 1 and footnote A). At thermal treatment temperatures of ≤1150°C and small concentrations (≈1 wt%),^{21,22} NaF, NaCl, and Na₂SO₄ may be retained in the vitrified waste form. At temperatures >1150°C, NaF and NaCl will speciate as Na₂O in the waste form and F₂, Cl₂, HF, or HCl vapors in the off-gas: F₂ and Cl₂ will form if dry waste is being processed and HF or HCl will form if water vapor is present. Sulfates such as (Na,Cs,K)₂SO₄ are favored if oxidized conditions exist in the thermal treatment unit. For the example given in Table 1 with high ZnO content, the sulfate species may well be ZnSO₄. Reducing conditions in the thermal treatment unit will favor decomposition of SO₄⁼ anionic species to SO₃ gas and/or SO₂ gas and/or H₂SO₄ generation depending on the absence or presence of water vapor. Highly reduced conditions will favor S₂ or H₂S generation, the latter of which is highly toxic. Since the anion analyses are done on wastes dried only to 105°C, the semi-volatile anions are included in the analysis. In order to simplify the mass balance calculation, it is convenient to express the fluoride, chloride and sulfate as anions that may vaporize upon thermal treatment, for example, F⁻, Cl⁻ and SO₄⁼, recognizing that these anions partition to the off-gas depending on thermal treatment temperature, waste form composition, presence of water vapor, and the reduction/oxidation equilibria in the thermal treatment unit. This will be discussed in more detail in 6.13.

²¹ Bickford, D. F., Applewhite-Ramsey, A., Jantzen, C. M., and Brown, K. G., "Control of Radioactive Waste Glass Melters: I, Preliminary General Limits at Savannah River," *J. Am. Ceram. Soc.*, 73 [10], 1990, pp. 2896-2902.

²² Cozzi, A. D., Jantzen, C. M., Brown, K. G., and Cicero-Herman, C. A., "Process Control for Simultaneous Vitrification of Two Mixed Waste Streams in the Transportable Vitrification System (TVS)," *Environmental Issues and Waste Management Technologies in the Ceramic and Nuclear Industries*, Vol IV, Ceramic Transactions, v. 93, J. Marra and D. K. Peeler (Eds.), American Ceramic Society, Westerville, OH, 1999, pp. 97-105

TABLE 2 Method A Analysis of a Sludge After Drying at 105°C to Remove Water and the Conversion of the Sludge Analysis to a Calcine or Oxide Forming Basis

Cations and Anions	Waste Analysis (Element Wt%)		Oxides and Anions	Major Components to be Considered for Waste Form Development (Wt%)		
	Replicate A	Replicate B		Replicate A	Replicate B	Average
Al	3.66	3.69	Al ₂ O ₃	6.92	6.97	6.94
B	<0.01	<0.01	B ₂ O ₃	---	---	---
Ba	<0.01	<0.01	BaO	---	---	---
Ca	5.00	5.02	CaO	7.00	7.02	7.01
Cd	0.107	0.109	CdO	0.12	0.12	0.12
Cr	<0.07	<0.07	Cr ₂ O ₃	---	---	---
Cu	1.41	1.42	Cu ₂ O	0.79	0.80	0.80
	---	---	CuO	0.88	0.89	0.89
Fe	13.9	14.1	Fe ₂ O ₃	18.78	19.05	18.92
	---	---	FeO	0.98	0.99	0.99
K	<0.15	<0.15	K ₂ O	---	---	---
Li	0.012	0.017	Li ₂ O	0.03	0.04	0.03
Mg	3.14	2.99	MgO	5.21	4.96	5.08
Mn	9.5 5	9.58	MnO	12.33	12.37	12.35
Mo	<0.01	<0.01	MoO	---	---	---
Na	0.182	0.183	Na ₂ O	0.25	0.25	0.25
Ni	<0.02	<0.02	NiO	---	---	---
PO ₄	<0.1	<0.1	P ₂ O ₅	---	---	---
Pb	<0.06	<0.06	PbO	---	---	---
Sb	<0.03	<0.033	Sb ₂ O ₃	0.04	0.04	0.04
Si	4.04	3.94	SiO ₂	8.64	8.43	8.54
Sr	<0.01	<0.01	SrO	---	---	---
Ti	<0.01	<0.01	TiO ₂	---	---	---
Zn	20.5	20.7	ZnO	25.52	25.77	25.64
Zr	<0.02	<0.02	ZrO ₂	---	---	---
SO ₄ ⁼	4.84	4.74	SO ₄ ⁼	4.84	4.74	4.79
F ⁻	0.342	0.322	F ⁻	0.342	0.322	0.332
Cl ⁻	0.696	0.791	Cl ⁻	0.696	0.791	0.744
NO ₂ ⁻	<0.01	<0.01	NO ₂ ⁻	---	---	---
NO ₃ ⁻	0.486	0.505	NO ₃ ⁻	0.486	0.505	0.496
			LOH ^A _{>105°C}	2.2	2.2	2.2
			SUMS	96.05	96.26	96.16

^A wt% LOH_{>105°C} = OH⁻ and CO₂ and TOC = 1.5 + 0.8 · (44/60) + 0 = 2.09

6.11.4 Total Mass Balance—The cations converted to a wt% oxide basis, plus the individual anions (F⁻, Cl⁻, SO₄⁼, NO₃⁻, and NO₂⁻), plus the volatile OH⁻ and CO₂ determined in **6.8** and **6.9**, plus the TOC should sum to 100 ± 5 wt%. The summation of all of these species serves as an accurate assessment of the overall measured composition using Method A.

6.12 Calculation of Waste Loading and Treatment Basis:

6.12.1 Calculation of the Calcined Oxide Basis—The treatment basis and waste loading are defined on an oxide or calcine basis. The calcine basis is normally taken to be ~1000°C so that all the water (steam) plus volatile species (wt% OH⁻, CO₂, NO_x) have been vaporized. Then the amount of the semi-volatile anions being vaporized, or alternatively, the amount of the semi-volatiles being retained in the waste form, at a particular thermal treatment temperature can be determined. In the example shown in **Table 2**, the wt% OH⁻, CO₂, TOC, NO₂⁻, and NO₃⁻ would completely volatilize at treatment temperatures ≤1000°C while partial volatilization of Cl⁻, F⁻, and SO₄⁼ depends on the treatment temperature, the amount of the species present, the form that it is present in the waste, and the oxidation state of the melt. For example, if a treatment temperature of 1150°C is used, then Cl⁻ and F⁻ can be retained in the waste form up to a few wt% as NaF or NaCl. Under oxidizing melt conditions at the treatment temperature of 1150°C, about 37 % of the SO₄⁼ is vaporized according to the

relationship between SO₄⁼ vaporization and thermal treatment temperature given in **Fig. 3**.²³ Therefore, 37 % of the SO₄⁼ is removed from the analysis in **Table 2** as well, and the entire table is renormalized to an oxide or calcine basis. If the thermal treatment conditions are reducing, for example, when large concentrations of organics are present, and/or if a thick cold cap of feed blankets the melt pool in the thermal treatment unit, then varying amounts of SO₄⁼ can be retained other than those indicated by **Fig. 3**. This provides the calcine basis for determining the glass forming potential of the waste (see **Appendix X1**) and the waste loading (see **6.12.2**).

6.12.2 The calcine oxide analysis in **Table 4** can be used to determine the glass or ceramic forming potential of the waste via phase diagrams such as those given in the examples in **Appendix X1**. Alternatively, the glass or ceramic forming potential of a waste may be limited by certain hard to stabilize constituents that can degrade the performance of the waste form. For example, if a Joule heated melter is being slurry fed, formation of a molten salt layer composed of Na₂SO₄ that floats on the melt pool could cause steam accumulations under the salt layer and pose a safety hazard. If operating at a melt

²³ Jantzen, C. M., Schumacher, R. F., and Pickett, J. B., "Mining Industry Waste Remediated for Recycle by Vitrification," *Environmental Issues and Waste Management Technologies VI*, D. R. Spearing, G. L. Smith, and R. L. Putnam (Eds.), American Ceramic Society, Westerville, OH, 2001, pp. 65-74.

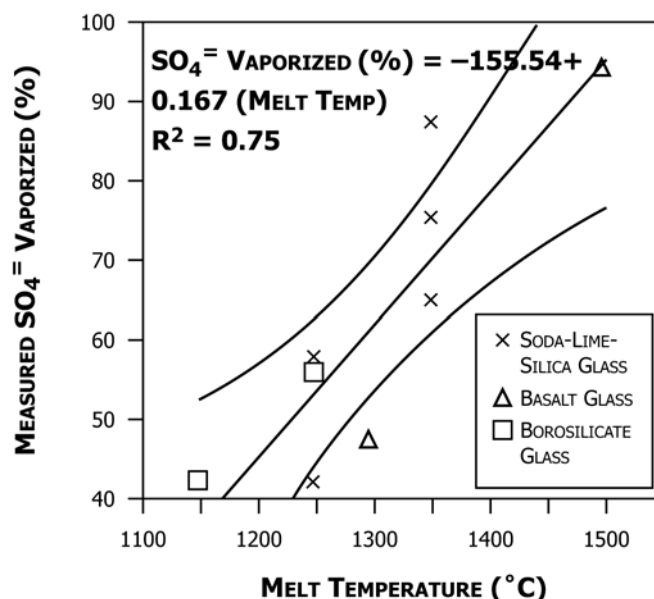


FIG. 3 Example of the Relationship of $\text{SO}_4 = \text{Vaporization}$ to Melt Temperature Under Oxidizing Conditions where wt% LOH is the Loss-on-Heating at the Anticipated Thermal Treatment Temperature

TABLE 3 Method A—Analysis of a Sludge After Drying at Various Temperatures

Drying Temperature (°C)	wt% Solids	wt% Loss-On-Ignition	Major Phases Present by X-Ray Diffraction
105	13.3	86.7	CaCO_3 $\text{Al}(\text{OH})_3$ ZnFeCrO_4
300	11.8	88.2	CaCO_3 ZnMnO_3
1000	10.5	89.5	ZnMnO_3

temperature of 1150°C under oxidizing conditions with a waste of the composition similar to Table 4, the amount of sulfate allowable in the waste form would be $\sim 0.7 \text{ SO}_4^{=}$ (equivalent to 1 wt% Na_2SO_4).²³ Therefore, waste loading could be limited to $(3.29/0.7) \cdot 100 = 21 \text{ wt\%}$ for safety considerations unless a reductant were used to enhance $\text{SO}_4^{=}$ vaporization, or higher temperatures were used to enhance $\text{SO}_4^{=}$ vaporization, or the waste contained no water to create steam.

6.12.3 Waste loading is defined as:

$$\text{Waste loading (wt\%)} = \quad (7)$$

$$\frac{\{\text{Wt of calcine}_{(>1000)}\}}{\{\text{Wt of calcine}_{(>1000^\circ\text{C})} + \text{Wt Glass Formers}\}}$$

6.13 *Estimation and Identification of Off-Gases for Thermal Treatment*—Ideally, the types and volumes of off-gas species liberated from a given waste upon thermal treatment can be measured by gas chromatography and mass spectrometry (GCMS). However, for applications where a GCMS is not available and/or the waste is highly variable, estimations using the data determined in 6.2 through 6.10 are sufficient to determine if a waste is a candidate for thermal treatment, the approximate volume reduction that will be achieved, and the needed capacity for the off-gas treatment.

6.13.1 Tables 2 and 3 give an example of analytic data for a waste-water treatment sludge dried at 105°C and analyzed

TABLE 4 Conversion of the Waste Analysis in Table 2 to a Calcine or Oxide Forming Basis

Oxides and Anions	Waste Analysis from Table 2 Accounting for Vaporization at the Thermal Treatment Temperature (Oxide Wt%)	Waste Analysis from Table 2 on a Calcine Basis (Oxide Wt%)
Al_2O_3	6.94	7.57
CaO	7.01	7.65
CdO	0.12	0.13
Cu_2O	0.80	0.87
CuO	0.89	0.97
Fe_2O_3	18.92	20.63
FeO	0.99	1.08
Li_2O	0.03	0.03
MgO	5.08	5.54
MnO	12.35	13.47
Na_2O	0.25	0.27
Sb_2O_3	0.04	0.04
SiO_2	8.54	9.32
ZnO	25.64	27.97
$\text{SO}_4^{=}$	3.02	3.29
F^-	0.74	0.81
Cl^-	0.33	0.36
SUMS	91.69	100.00

using the steps outlined in 6.2 through 6.10. In order to calculate the Loss-on-Heating (wt% LOH) at a given thermal treatment temperature, the wt% LOH at 105°C from Table 3 is used as a starting point, for example, 86.7 wt%, and the measured wt% TOC. The wt% OH^- and CO_2 content are calculated from the wt% LOH data at 300°C and 1000°C (see 6.8 and 6.9) as follows:

$$\text{OH}^-(\text{wt\%}) \approx (\text{wt\% LOH})_{300^\circ\text{C}} - (\text{wt\% LOH})_{105^\circ\text{C}} - \text{wt\% TOC} \quad (8)$$

$$= 86.7 - 0 \text{ wt\%} = 1.5 \text{ wt\%}$$

$$\text{CO}_2(\text{wt\%}) \approx \{(\text{wt\% LOH})_{1000^\circ\text{C}} - (\text{wt\% LOH})_{300^\circ\text{C}} - (\text{wt\% NO}_2^-)\}$$

$$- (\text{wt}\% \text{NO}_3^-) \cdot (44/60) \{89.5 - 88.2 - 0 - 0.5\} \cdot (44/60) \\ = 0.59 \text{wt}\%$$

6.13.2 The total wt% LOH between 105°C and ~1000°C is:

$$\text{wt}\% \text{LOH}_{1000-105^\circ\text{C}} = \text{OH}^- + \text{CO}_2 + \text{NO}_2^- + \text{NO}_3^- + \text{TOC} = 1.5 + 0.59 \\ + 0 + 0.5 + 0 = 2.59 \text{wt}\% \quad (9)$$

6.13.3 While the wt% LOH released from the wet sludge at room temperature to the off-gas (up to a temperature of ~1000°C) is:

$$\text{wt}\% \text{LOH}_{1000-25^\circ\text{C}} = \quad (10) \\ \text{H}_2\text{O}(\text{steam}) + \text{OH}^- + \text{CO}_2 + \text{NO}_2^- + \text{NO}_3^- + \text{TOC} = \\ 86.7 + 1.5 + 0.59 + 0 + 0.5 + 0 = 89.3 \text{wt}\%$$

6.13.4 The total wt% LOH to the off-gas system must include these species that volatilize completely (100 %) plus any contributions from Cl^- , F^- , and SO_4^{2-} which partially volatilize. The volatility of Cl^- , F^- , and SO_4^{2-} is a function of thermal treatment temperature, waste form composition, presence of water vapor, and the reduction/oxidation equilibria in the thermal treatment unit (see 6.11.3). At an 1150°C thermal treatment temperature the total wt% LOH to the off-gas per 100 lb of waste processed can be calculated as:

$$\text{wt}\% \text{LOH}_{1150^\circ\text{C}} (\text{wt}\%) = \quad (11) \\ \text{H}_2\text{O vapor} + \text{OH}^- + \text{CO}_2 + \text{NO}_2^- + \text{NO}_3^- + \text{TOC} + \\ (\text{SO}_4^{2-} \text{ in waste times } 37 \% \text{ volatilization from Fig. 3} \\ \text{times } 21 \% \text{ waste loading dilution factor}) + \text{F}^- + \text{Cl}^- = \\ 86.7 + 1.5 + 0.59 + 0 + 0.5 + 0 + 0.37(0.21)(4.79) + 0 + 0 = \\ 89.7 \text{ wt}\%$$

6.13.5 At higher thermal treatment temperatures, for example, 1500°C such as those necessitated by basalt glass or basalt glass-ceramics, the Cl^- and F^- would be volatile and add another 1.07 wt% LOH to the off-gas. The SO_4^{2-} is ~95 % volatile. This leaves only 0.24 wt% SO_4^{2-} in the waste form, well below the 0.7 limit for molten salt layer formation even at 100 % waste loading. The total wt% LOH at ~1500°C can be calculated as:

$$\text{wt}\% \text{LOH}_{>1500^\circ\text{C}} = \quad (12) \\ \text{H}_2\text{O vapor} + \text{OH}^- + \text{CO}_2 + \text{NO}_2^- + \text{NO}_3^- + \text{TOC} + \\ 95 \% \text{SO}_4^{2-} + \text{F}^- + \text{Cl}^- = \\ 86.7 + 1.5 + 0.59 + 0 + 0.5 + 0 + 0.95(4.79) + 0.33 + 0.74 = \\ 94.9 \text{wt}\%$$

7. Test Method B

7.1 Waste analysis Method B uses wastes dried at 105°C to determine the weight percent solids and wastes dried at $\geq 1000^\circ\text{C}$ for cation analysis. The waste analyses strategy for Method B is given in Fig. 4.

7.2 *Weight Percent Solids*—Wastes should be dried at 105°C until a constant weight is achieved to determine the wt% solids at this temperature.

7.2.1 Calculate the wt% solids at 105°C by the following:

$$\text{wt}\% \text{solids} = \{(W_3 - W_1)105^\circ\text{C} / (W_2 - W_1)_{\text{rt}}\} \cdot 100 \quad (13)$$

where:

W_1 = weight of the crucible,

W_2 = weight of crucible and waste at room temperature (rt), and

W_3 = weight of crucible and waste after drying at 105°C.

7.3 *Loss-On-Heating and Off-Gas System Loading*—Wastes should be dried at $\geq 1000^\circ\text{C}$ until a constant weight is achieved to determine the Loss-On-Heating (wt% LOH) at this temperature. Calculate the wt% LOH at $\geq 1000^\circ\text{C}$ by the following:

$$(\text{wt}\% \text{LOH})_{\geq 1000^\circ\text{C}} = \quad (14)$$

$$\{(W_2 - W_1)_{\text{rt}} - (W_3 - W_1)_{\geq 1000^\circ\text{C}} / (W_2 - W_1)_{\text{rt}}\} \cdot 100$$

where:

W_1 = weight of the crucible,

W_2 = weight of crucible and waste at room temperature (rt), and

W_3 = weight of crucible and waste after drying at $\geq 1000^\circ\text{C}$.

7.3.1 The $(\text{wt}\% \text{LOH})_{\geq 1000^\circ\text{C}}$ gives the total amount of volatiles to be expected in the off-gas in weight percent.

7.4 *Cation Analyses*—Calcine a few grams of waste at $\geq 1000^\circ\text{C}$ and follow the dissolution methods outlined in 6.3.

7.5 *Anion Analyses*—Calcine a few grams of waste at $\geq 1000^\circ\text{C}$ and follow the dissolution methods outlined in 6.4. Speciation of volatile anions such as CO_3^{2-} , NO_3^- , and NO_2^- will not be possible as this method gives the total volatiles (wt%). Depending on the calcining temperature, F^- , Cl^- and SO_4^{2-} may or may not be present.

7.6 *Accuracy Assessment by Mass Balance* ($100 \pm 5 \text{ wt}\%$)—Follow methods outlined in 6.11.1. If an oxide mass balance of $100 \pm 5 \text{ wt}\%$ cannot be achieved, repeat analysis, try Waste Analysis Method C or Method A.

8. Test Method C

8.1 Waste analysis Method C uses wastes dried at 105°C to determine the weight percent solids and wastes dried at $\geq 1000^\circ\text{C}$ for cation analysis. The waste analyses strategy for Method C is given in Fig. 5.

8.2 *Weight Percent Solids*—Same as section 7.2.

8.3 *Loss-On-Heating and Off-Gas System Loading*—Same as section 7.3.

8.4 *Cation Analyses*—Weigh out 10 g of waste. Add a known amount of B_2O_3 to the waste and fuse into glass at $\geq 1000^\circ\text{C}$ until a constant weight is achieved. Up to 5 g of B_2O_3 can be added per 10 g of waste. Follow dissolution and analytic methods outlined in 6.3.

8.5 *Anion Analyses*—Weigh out 10 g of waste. Add a known amount of B_2O_3 to the waste and fuse into glass at $\geq 1000^\circ\text{C}$ until a constant weight is achieved. Up to 5 g of B_2O_3 can be added per 10 g of waste. Follow the dissolution methods

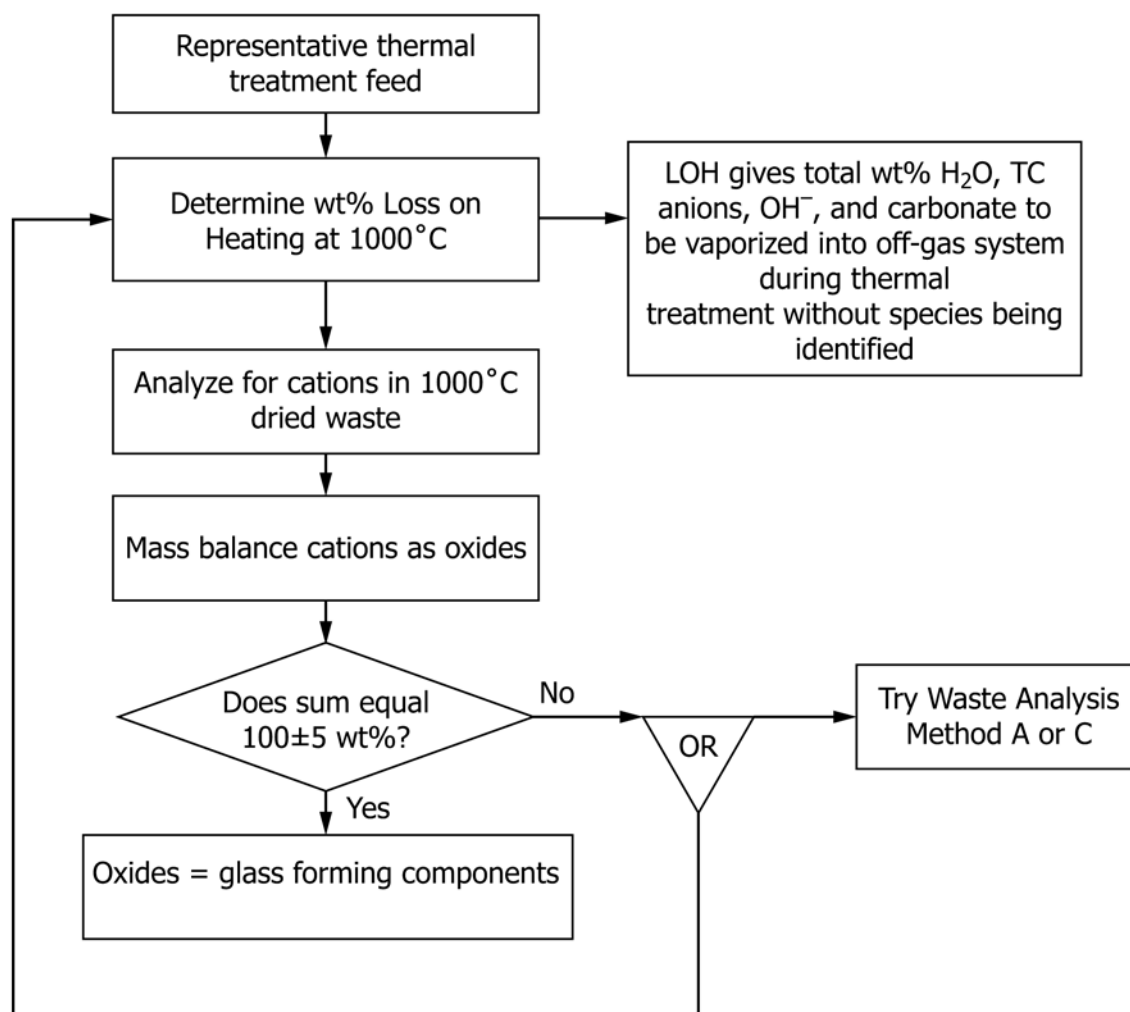


FIG. 4 Waste Analysis Method B

outlined in 6.4. Speciation of volatile anions such as CO_3^- , NO_3^- , and NO_2^- will not be possible as this method gives the total volatiles. Depending on the calcining temperature, F^- , Cl^- and SO_4^- may or may not be present.

8.6 Accuracy Assessment by Mass Balance (100 ± 5 wt%)—Subtract the amount of B_2O_3 added in step 8.4 from the amount of B_2O_3 measured in the waste glass. Follow the methods outlined in 6.11.1. If an oxide mass balance of 100 ± 5 wt% cannot be achieved, repeat analysis, try Waste Analysis Method B or Method A.

9. Precision and Bias

9.1 No statement is made about the precision and bias of the individual test methods used to determine the cation, anion,

and volatile constituents of a waste. The precision and accuracy of these methods are given in the test methods referenced in this guide. Since multiple test methods must be used to achieve a complete waste analysis, a method to determine the accuracy of the combined analyses to within 100 ± 5 wt% are given in 6.11 for Test Method A, in 7.6 for Test Method B, and in 8.6 for Test Method C.

10. Keywords

10.1 accuracy assessment; mass balance; thermal treatment; waste analyses

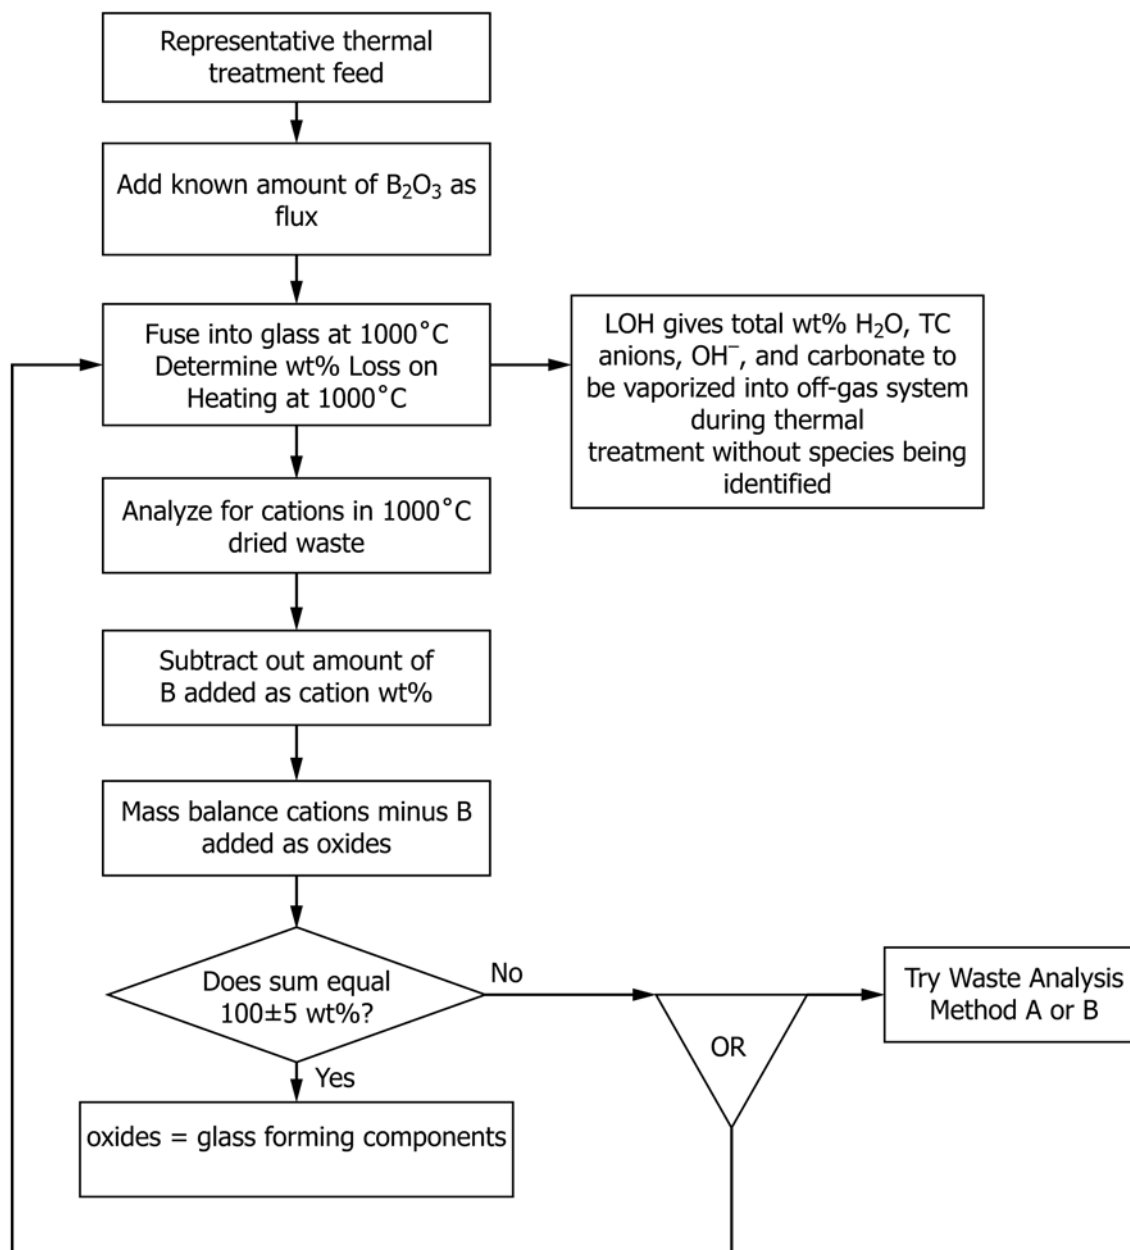


FIG. 5 Waste Analysis Method C

APPENDIX

(Nonmandatory Information)

X1. CHOICE OF OXIDE SYSTEMS FOR FORMATION OF GLASS WASTE FORMS

X1.1 When waste analyses from Methods A, B, and C are converted to an oxide basis, the use of phase diagrams such as those shown in Figs. X1.1-X1.3 can be used to determine the best glass forming system for the waste of concern. These examples are not considered inclusive of all potential oxide systems that can be used for thermal treatment of waste since

additional factors such as cost and compatibility of the molten waste plus glass forming oxides with the thermal treatment unit materials of construction must be considered. However, the diagrams illustrate how simple waste form compositions can be achieved by adjusting the waste plus glass former composition to take advantage of the common glass forming constituents,

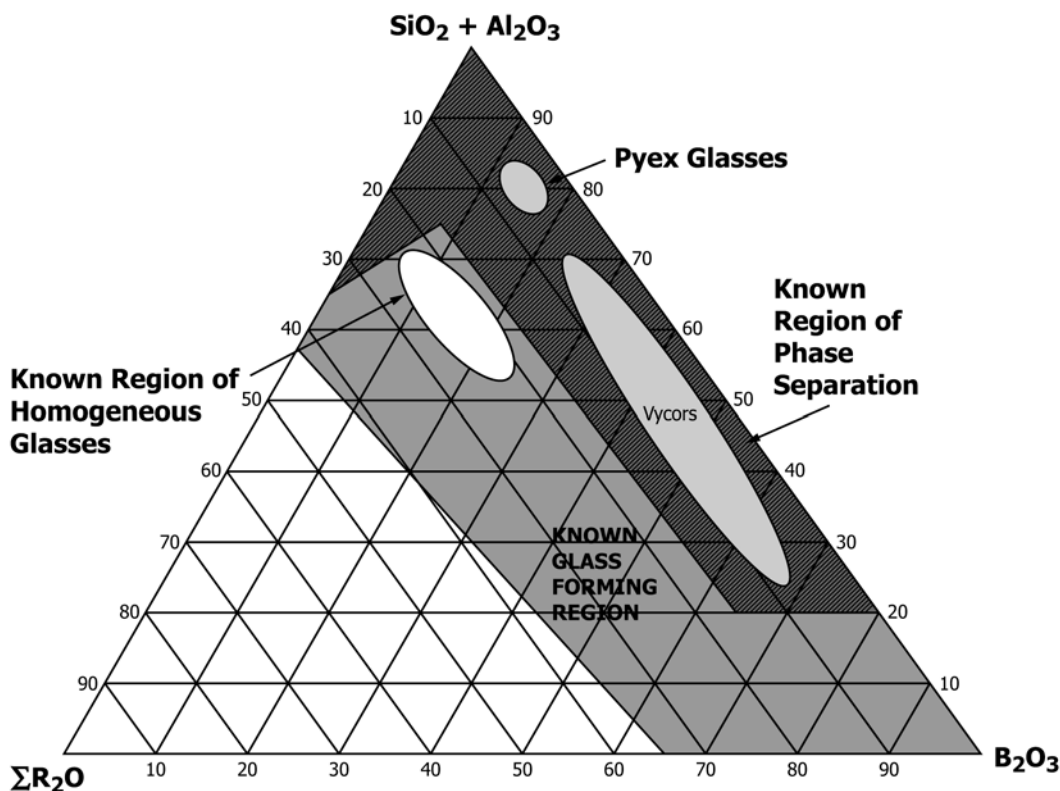


FIG. X1.1 Ternary Diagram of the Alkali-borosilicate Oxide System Demonstrating the Compositional Regions of Common Glass Formation and Usage are Located

for example, Si, Al, Na, and Ca, already in the waste material.

X1.2 The tolerance of glass based waste forms for many different kinds of waste, plus the common glass constituents contained in many wastes enables glass waste forms to be very accommodating to process chemistry variation. During the vitrification process the waste species become bonded in the glass or crystalline phases as oxide components. Hence all diagrams are given in oxide weight percent (wt%) in order to illustrate the composition range(s) in which glass waste forms will most likely form. The glass forming regions are shaded in Figs. X1.1-X1.3. Formulation of waste glasses outside the shaded areas will result in glass ceramics and/or glass slag waste form formation.

X1.3 Borosilicate glasses are alkali-aluminosilicate type glasses which are fluxed with boron (Fig. X1.1) and can accommodate up to ~12 wt% Fe_2O_3 and other transition metals. The generally low alumina content of these waste forms and the presence of boron lowers the melt viscosity and hence the processing temperature to ~1150°C relative to that of the aluminosilicate glasses which melt in excess of 1400°C. The lower melt temperature of borosilicate glass waste forms allows for greater retention of volatile hazardous and radioactive species than higher temperature glass waste forms. Borosilicate glasses are currently being used in the US, UK, Germany, France, and Japan, to stabilize high level radioactive wastes. Other countries such as Switzerland have accepted this form of stabilization for waste arising from the reprocessing of their fuel abroad. Belgium had been using borosilicate glass for

radioactive waste disposal until recently.


X1.4 The Soda-lime-silica oxide system is shown in Fig. X1.2. Soda-lime-silica (SLS) glass is known to be extremely tolerant of heavy metals waste constituents.^{22,24} SLS glass formulations have been used for In-Situ Vitrification (ISV) to solidify contaminated soils²⁵ and a barium (Ba) analog (Soda-Baria-Silica) glass has been used at Fernald to vitrify residues from uranium ore processing that contain large contents of uranium, radium, and lead.^{26,27} For Fernald waste solidification the barium rich glass was chosen due to the high barium

²⁴ Jantzen, C. M., Pickett, J. B., and Ramsey, W. G., "Reactive Additive Stabilization Process (RASP) for Hazardous and Mixed Waste Vitrification," *Proceed. Second Inter. Symp. on Mixed Waste*, A. A. Moghissi, R. K. Blauvelt, G. A. Benda, and N. E. Rothermich (Eds.), Am. Soc. Mech. Eng., 1993, pp. 4.2.1-4.2.13.

²⁵ Callow, R. A., Thompson, L. E., Weidner, J. R., Loehr, C. A., McGrail, B. P., and Bates, S. O., "In-situ Vitrification Application to Buried Waste: Final Report of Intermediate Field Tests at Idaho National Engineering Laboratory," *U.S. DOE Report EGG-WTD-9807*, Idaho National Engineering Laboratory, Idaho Falls, ID, August, 1991.

²⁶ Janke, D. S., Chapman, C. C., and Vogel, R. A., "Results of Vitrifying Fernald K-65 Residue," *Nuclear Waste Management IV*, G. G. Wicks, D. F. Bickford, and L. R. Bunnell (Eds.), Ceramic Transactions, Vol 23, American Ceramic Society, Westerville, OH, 1991, pp. 53-61.

²⁷ Jantzen, C. M., and Pickett, J. B., "Vitrification of Simulated Fernald K-65 Silo Waste at Low Temperature," *Environmental Issues and Waste Management Technologies in the Ceramic and Nuclear Industries*, Vol IV Ceramic Transactions, v. 93, J. Marra and G. T. Chandler (Eds.), American Ceramic Society, Westerville, OH, 1999, pp. 203-212; Jantzen, C. M., and Pickett, J. B., "Vitrification of Simulated Fernald K-65 Silo Waste at Low Temperature," *U.S. DOE Report WSRC-TR-97-0061*, Rev. 1, January 14, 1999.

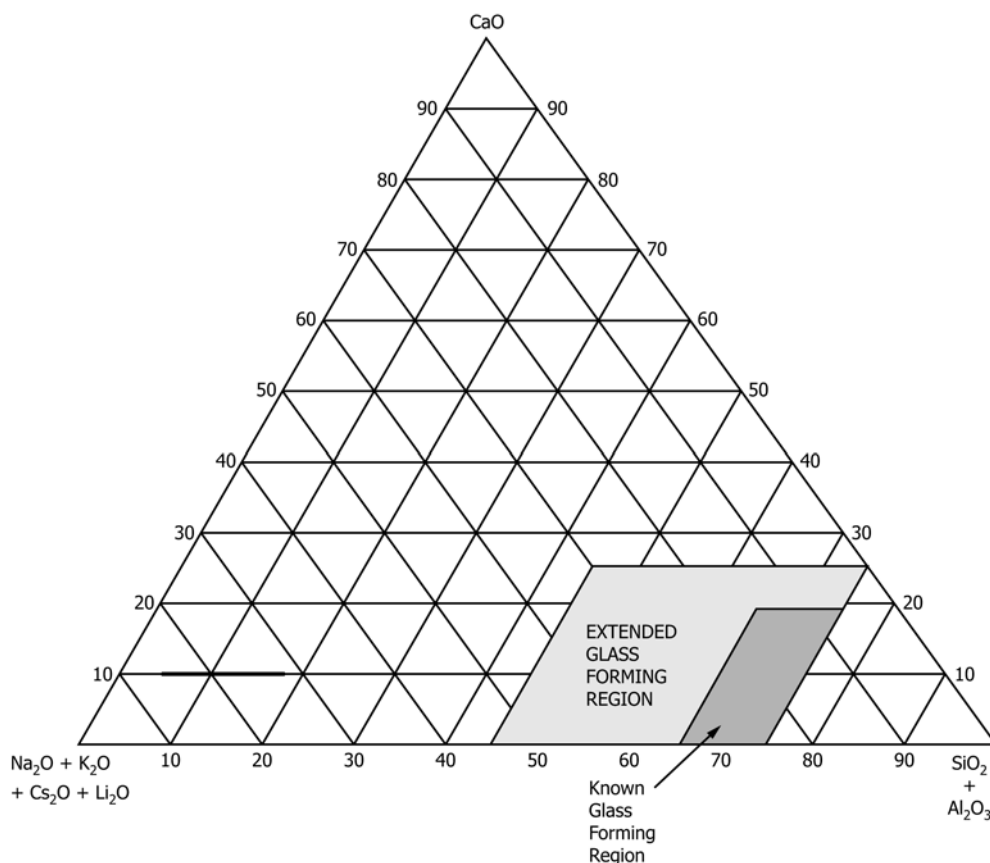

NOTE 1—The lighter shaded area indicates the extended glass forming region demonstrated by Jantzen (Jantzen, C. M., Pickett, J. B., and Ramsey, W. G., “Reactive Additive Stabilization Process (RASP) for Hazardous and Mixed Waste Vitrification,” *Proceed. Second Inter. Symp. on Mixed Waste*, A. A. Moghissi, R. K. Blauvelt, G. A. Benda, and N. E. Rothermich (Eds.), Am. Soc. Mech. Eng., 1993, pp. 4.2.1-4.2.13.) to form in the presence of high Fe_2O_3 and ZnO containing wastes and using the RASPTM vitrification technology.

FIG. X1.2 Ternary Diagram Showing the Region of Glass Formation (Darker Shaded Area) in the Soda-Lime-Silica (SLS) Oxide System

content of the waste. SLS glasses were also successfully fabricated from reactive sodium (Na) metal formed and contaminated during efforts to develop sodium-cooled fast breeder nuclear reactors.²⁸

X1.5 The basalt glass forming system shown in Fig. X1.3 has been used to stabilize high Fe_2O_3 wastes from incinerators. Incinerator slag²⁹ and nuclear waste incinerator ash³⁰ containing little or no alkali has been mixed with a common rock, basalt, and basalt glass or glass ceramics have been fabricated


at temperatures in excess of 1300 to 1400°C (Fig. X1.3). The basalt glass ceramic system was also used for cleanup of UO_2 fuel rods from Three Mile Island.³¹ While the high temperature of basalt glass ceramics was appropriate for the remediation of UO_2 waste, the high temperatures can cause excessive volatility of some hazardous waste species and, therefore, basalt glass has not become widely used for stabilization of wastes containing hazardous volatile constituents.

²⁸ Kumar, R., and Helt, J. E., “Improved Treatment/Disposal of Reactive Metals. Phase II: Technical Research and Development,” *U.S. DOE Report ANL-91/21*, Argonne National Laboratory, Argonne, IL, May, 1991.

²⁹ Queneau, P. B., May, L. D., and Cregar, D. E., “Application of Slag Technology to Recycling of Solid Wastes,” *1991 Incineration Conference*, Knoxville, TN, May, 1991.

³⁰ Lebeau, M. J., and Girod, M., “Incorporation of Simulated Nuclear Ashes in Basalt: An Experimental Investigation,” *Am. Ceram. Soc. Bull.*, 66 [11], 1987, pp. 1640-1646.

³¹ Welch, J. M., Miller, R. L., and Flinn, J. E., “Immobilization of Three-Mile Island Core Debris,” *Nuclear Waste Management*, G. G. Wicks and W. A. Ross (Eds.), *Advances in Ceramics*, V. 8, American Ceramic Society, Columbus, OH, 1984, pp. 611-618.

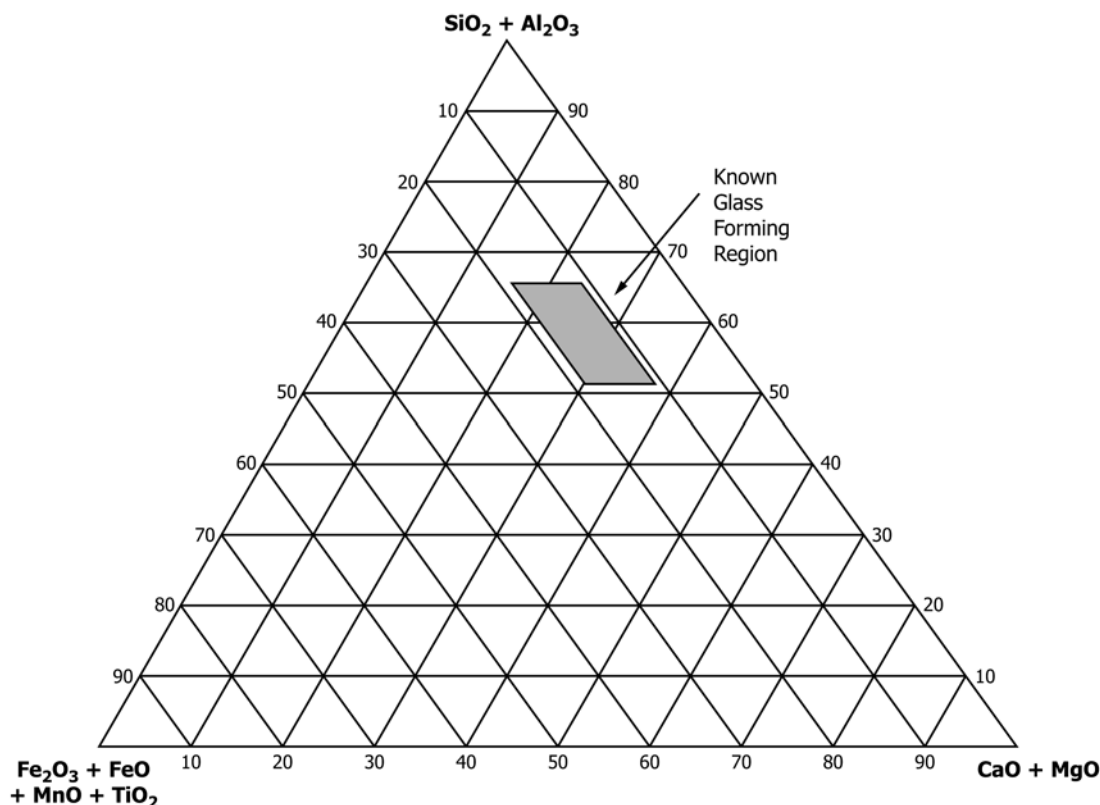

NOTE 1—Glass forming composition limits determined from Volf, Table 114 containing the composition limits of basaltic fiber glasses (Volf, M. B., “Technical Glasses,” Sir Issac Pitman & Sons, Ltd, London 1961, p. 465.)

FIG. X1.3 Ternary Diagram Showing the Region of Glass Formation (Shaded Area) in the Basalt Glass Ceramic System

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/