



Standard Practice for Design of Journal Bearing Supports to be Used in Fiber Reinforced Concrete Beam Tests¹

This standard is issued under the fixed designation C1812/C1812M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

^{ε1} NOTE—The designation was corrected editorially in June 2016 to conform with the units statement (1.2).

1. Scope

1.1 This practice prescribes the design of journal-bearing type rollers to support each end of fiber-reinforced concrete beams tested using Test Method C1399/C1399M or Test Method C1609/C1609M. The roller design is intended to provide a consistent and relatively low value of effective coefficient of friction at the beam supports. The bearing design incorporates metal-on-metal sliding surfaces lubricated with grease.

NOTE 1—During the progress of a test, a crack or cracks open on the underside of the beam between the loaded third points causing the underside of each portion of the beam to move away from the center. The design is intended to provide for unlimited rotation of the roller at the point of contact with the test beam in response to this motion.

NOTE 2—The design of the supporting rollers is a significant factor in determining the magnitude of the arching forces that cause error in flexural test results.² Improperly designed supporting rollers can influence the apparent flexural behavior of fiber-reinforced concrete beams.³ The effective coefficient of friction can be determined using a method similar to that described by Bernard.⁴

1.2 *Units*—The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the*

responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

2. Referenced Documents

2.1 ASTM Standards:⁵

C125 Terminology Relating to Concrete and Concrete Aggregates

C1399/C1399M Test Method for Obtaining Average Residual-Strength of Fiber-Reinforced Concrete

C1609/C1609M Test Method for Flexural Performance of Fiber-Reinforced Concrete (Using Beam With Third-Point Loading)

D4950 Classification and Specification for Automotive Service Greases

2.2 SAE International Standard:⁶

J 404 Chemical Composition of SAE Alloy Steels

3. Terminology

3.1 Definitions:

3.1.1 For definitions of terms used in this practice, refer to Terminology C125.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 *effective coefficient of friction, n* —a dimensionless ratio of the horizontal force required to initiate rotation of the roller support applied at the contact point between the roller and test beam divided by the normal force applied at the same point (see Fig. 1).

3.2.2 *roller, n* —a journal bearing capable of continuous rotation without exhibiting a significant variation in resistance to rotation.

4. Significance and Use

4.1 The presence of friction in the supporting rollers used when testing a fiber-reinforced concrete beam will increase the

¹ This practice is under the jurisdiction of ASTM Committee C09 on Concrete and Concrete Aggregates and is the direct responsibility of Subcommittee C09.42 on Fiber-Reinforced Concrete.

Current edition approved July 1, 2015. Published September 2015. DOI: 10.1520/C1812_C1812M-15E01.


² Zollo, R. F., 2013. "Analysis of Support Apparatus for Flexural Load-deflection Testing: Minimizing Bias," *Journal of Testing and Evaluation*, ASTM International, Vol. 41, No. 1, pp. 1-6.

³ Wille, K. and Parra-Montesinos, G.J., 2012. "Effect of Beam Size, Casting Method, and Support Conditions on Flexural Behavior of Ultra-High-Performance Fiber-Reinforced Concrete," *ACI Journal of Materials*, Vol. 109, No. 3, pp. 379-388.

⁴ Bernard, E.S., 2014. "Influence of friction in supporting rollers on the apparent flexural performance of third-point loaded fibre reinforced concrete beams," *Advanced Civil Engineering Materials*, ASTM International Vol. 2, No. 1, pp. 158-176.

⁵ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

⁶ Available from SAE International (SAE), 400 Commonwealth Dr., Warrendale, PA 15096, <http://aerospace.sae.org>.

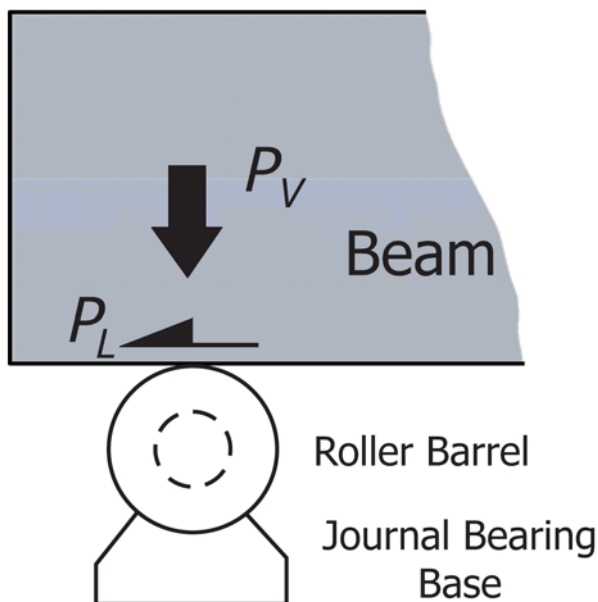

P_L = frictional force applied to the roller by the beam.
 P_V = vertical force applied to the roller by the beam.

FIG. 1 Forces Acting on a Supporting Roller During a Test

apparent load resistance of the beam. Roller supports designed in accordance with this practice will provide a relatively low and consistent value of friction at the supports.

4.2 Two types of rollers are used to support a beam. One includes a cylindrical bearing that allows the roller assembly to rotate along an axis parallel to the longitudinal axis of the beam and thereby accommodate any warping introduced during specimen fabrication. The other roller does not include the cylindrical bearing.

4.3 The rollers are designed for use with 150 mm [6 in.] or 100 mm [4 in.] deep beams of square cross-section.

4.4 A method is provided for correcting the apparent load resistance measured using the roller with a known value of the effective coefficient of friction of the roller supports to obtain an estimate of the load resistance in the absence of friction.

5. Apparatus

5.1 *Geometry*—A pair of rollers is required to support a beam during a test. The barrel of each roller, which is that portion of the roller in contact with the beam, shall be free to rotate about an axis perpendicular to the longitudinal axis of the beam to accommodate movement of the initial support point on the beam away from the center during a test. Friction between sliding surfaces within each roller will generate a small resistance to rotation of the barrel relative to the mounting (see Fig. 1). A roller fabricated in accordance with this practice will exhibit an effective coefficient of friction of about 0.10.⁴ Journal bearing supports manufactured in conformance with this practice do not need to be tested to confirm that the effective coefficient of friction meets requirements.

5.1.1 One of the two rollers supporting the underside of the beam shall be able to rotate about an axis parallel to the longitudinal axis of the beam to accommodate a warped test beam surface that could induce torsion in the beam during testing (see Note 3 and Fig. 2). The other roller shall be fixed against rotation about a longitudinal axis to prevent the beam from overturning during installation and testing (see Fig. 3). Rotation about a longitudinal axis shall be accommodated by inclusion of a cylindrical bearing surface under the roller mount with a center of rotation that coincides with the plane of the contacting surface between roller and bottom of the beam. The base of the cylindrical bearing surface shall include bolt

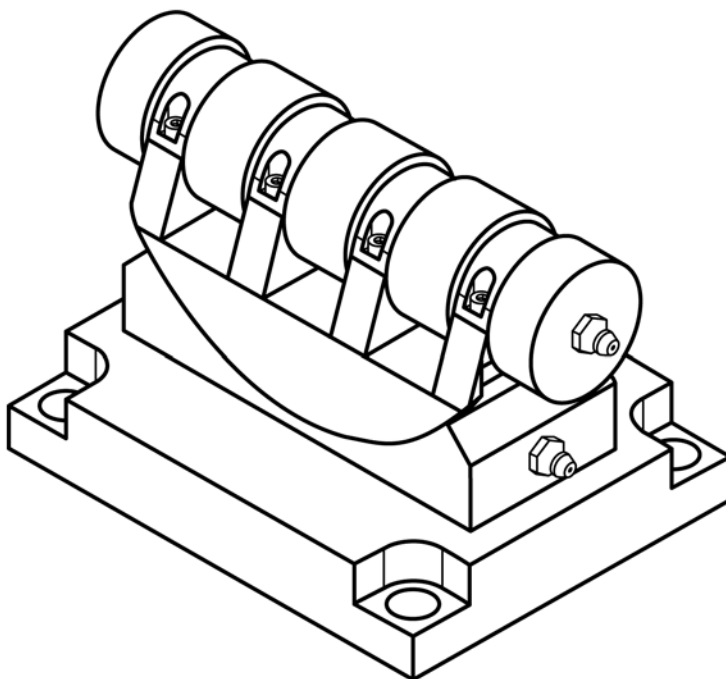


FIG. 2 General Arrangement Drawing of Supporting Roller with a Cylindrical Bearing Base

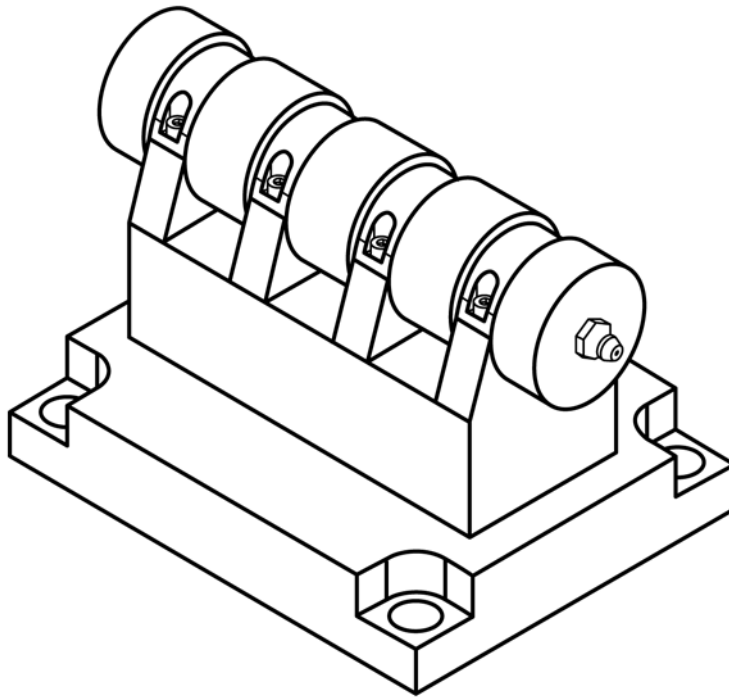


FIG. 3 General Arrangement Drawing of Supporting Roller with a Fixed Bearing Base

holes to facilitate fixing the roller to the testing machine. The roller that is fixed against rotation about a longitudinal axis (Fig. 3 and Fig. 6) shall incorporate a similar mounting so that the total height is the same as the roller assembly shown in Fig. 2 and Fig. 5 and the beam is maintained level during a test. The barrel of each roller is fabricated from one piece of steel. Caps secure the roller barrel in place so that it may rotate but not displace during a test. The cylindrical seat of the roller that is free to rotate about a longitudinal axis shall include a flange and a recess as shown in Fig. 4 to prevent longitudinal translation during testing.

NOTE 3—The upper half of the cylindrical bearing surface is not fixed to the lower half, but is restrained by guides intended to prevent the upper part of the bearing from sliding in the longitudinal direction in response to the forces imposed by the beam as it deflects at the bottom surface and each half of the beam moves away from the center as the crack(s) widen.

NOTE 4—To check that a properly manufactured and lubricated journal bearing assembly is functional, the rotating roller within the assembly must turn at least 360° without undue resistance when turned by hand. Such a check should be performed before each test is undertaken.

5.2 Steel Grade—The rollers and their corresponding mountings shall be fabricated using SAE 4140 alloy steel or equivalent.

5.3 Surface Treatment—The sliding and rotating surfaces of the roller, bushings, and cylindrical bearing within the support mounting shall be machined to a high-grade machine finish with a roughness average of 0.8 μm [32 $\mu\text{in.}$] or better. The difference in radius between the contacting surface of the roller barrel and the corresponding contacting surface of the bushing is limited to 0.10 mm [0.004 in.].

5.4 Lubrication—The design includes grease ports for lubricating the sliding surfaces. Grease shall be applied to the surfaces via the grease ports to limit friction and expel debris that may collect at the junctions between the shaft of the roller and the bushing caps. The user shall establish a schedule for grease application to ensure proper operation of the roller assemblies. The grease shall be National Lubricating Grease Institute (NLGI) Grade 2 lithium complex molybdenum disulfide high-pressure grease as described in Specification D4950 or equivalent.

5.5 Mounting of Rollers within Testing Machine—The mounting shall include a 25 mm [1 in.] thick steel plate with bolts located so as to secure the roller supports to the test machine during testing. The designs shown in Figs. 2-6 incorporate four bolt holes in the base of the bearing mount with an overall height of roller and mount equal to 100 mm [4.0 in.]. These dimensions have been found to perform satisfactorily in service, but the exact dimensions of the bases are permitted to be altered to suit the dimensions of the test machine to which they are fixed.

5.6 Dimensions—The dimensions of the rollers shown in Figs. 5 and 6 are based on SI units. Equivalent dimensions in inches are listed in Table 1. Tolerances on dimensions are ± 0.1 mm [0.004 inches].

6. Keywords

6.1 fiber-reinforced concrete; flexural performance; friction; post-crack; residual strength; roller supports

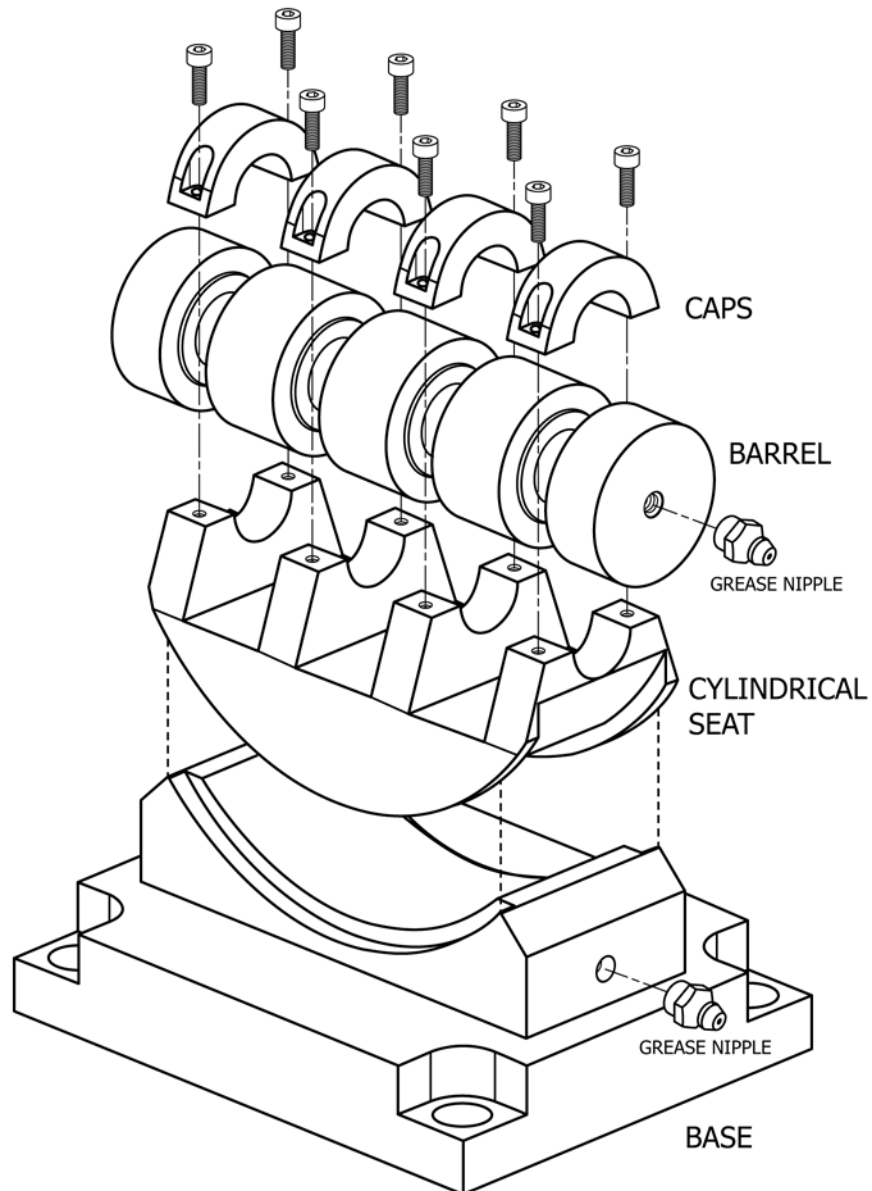


FIG. 4 Exploded View of Roller Assembly Showing Bushing Caps to Secure Roller Barrel and Flanges to Prevent Sliding in the Longitudinal Direction

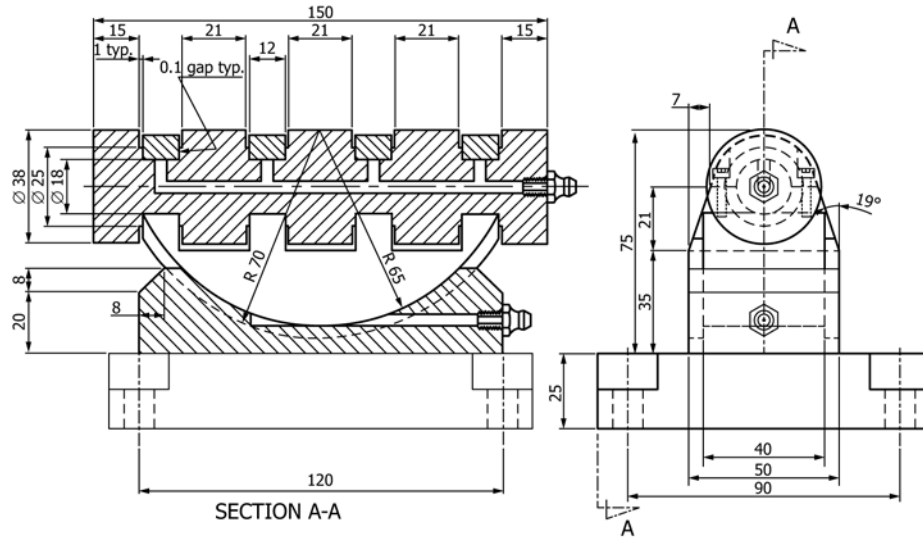


FIG. 5 Sectional View of Roller on Cylindrical Bearing Base with Dimensions in mm

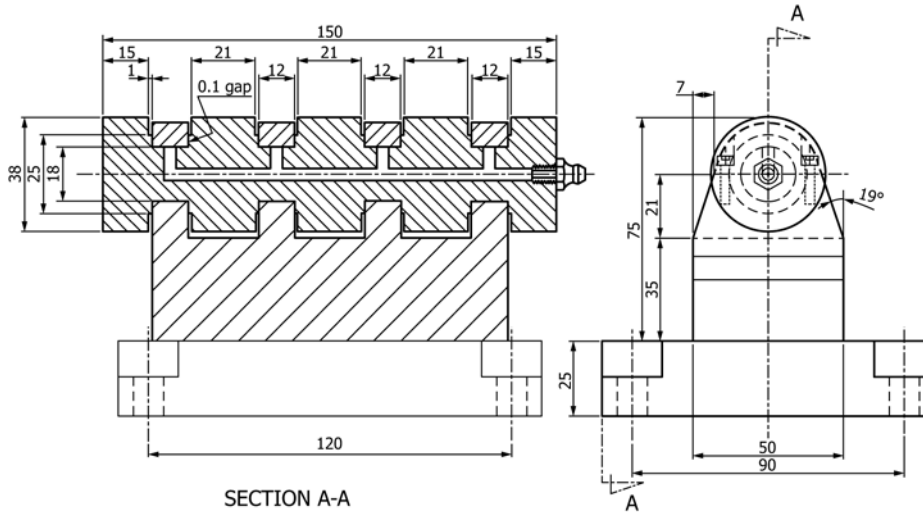


FIG. 6 Sectional View of Roller on Fixed Bearing Base with Dimensions in mm

TABLE 1 List of Dimensions in SI Units and Equivalents in Inches

Dimension in millimetres	Dimension in inches
1	0.04
7	0.28
8	0.32
12	0.50
15	0.59
18	0.71
20	0.79
21	0.83
25	1.00
34	1.34
38	1.50
40	1.58
50	2.00
65	2.56
70	2.76
75	3.00
90	3.50
120	4.72
150	6.00

APPENDIX

(Nonmandatory Information)

X1. CORRECTION OF TEST RESULTS FOR FRICTION IN SUPPORTS

X1.1 Scope

X1.1.1 This appendix provides recommendations for correction of flexural strength results obtained in beam tests when an effective coefficient of friction of known magnitude is present in the supporting rollers under a beam subject to third-point loading.

X1.1.2 The correction method may be applied to all values of load resistance obtained prior to and after cracking of the concrete matrix in the beam test.

X1.2 Calculation

X1.2.1 *Apparent Load Resistance of Beam*—Fig. X1.1 is a

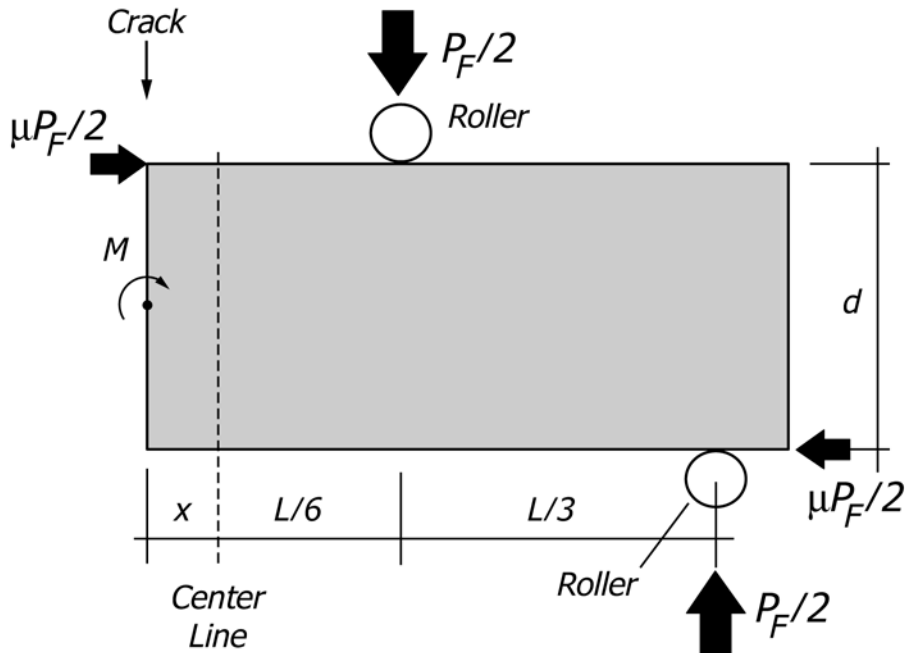


FIG. X1.1 Free-Body Diagram for a Third-Point Loaded Beam with Off-Center Crack and an Effective Coefficient of Friction Equal to μ at Each Supporting Roller

free-body diagram of the cracked portion of a beam for which the effect of friction on the apparent load resistance can be evaluated. The ratio, α , of the apparent load resistance, P_F , of a third-point loaded beam in the presence of friction within the supporting rollers to the load resistance of the same beam in the absence of friction, P_0 , is found as:

$$\alpha = \frac{P_F}{P_0} = \frac{L}{(L - 3 \mu d)} \quad (\text{X1.1})$$

where:

L = beam span, mm [in.],

μ = effective coefficient of friction of the roller support, dimensionless, and

d = beam depth, mm [in.].

For Test Methods **C1399/C1399M** and **C1609/C1609M**, $d = L/3$, thus the ratio α for a third-point loaded beam is expressed as:

$$\alpha = \frac{1}{(1 - \mu)} \quad (\text{X1.2})$$

X1.2.2 Correction of Apparent Load Resistance—The value of α is equal to 1.11 for an effective coefficient of friction, μ , in a roller support under a third-point loaded beam equal to 0.10. To remove the error introduced by the presence of friction in the rollers, the corrected load resistance of the beam is found as:

$$P_0 = P_F / \alpha \quad (\text{X1.3})$$

X1.2.3 Application of Correction Factor—If a roller conforming to the design prescribed in this practice is used to support each end of a third-point loaded beam, the effective coefficient of friction can be taken to equal 0.10 assuming the rollers are regularly cleaned and maintained. The correction to the load resistance of the beam indicated by **Eq X1.3** is then applied to all points of the recorded load-deflection record.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>