



# Standard Specification for Chemical-Resistant Ceramic Tower Packings<sup>1</sup>

This standard is issued under the fixed designation C515; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This specification covers fired ceramic shapes formed from naturally occurring clays and from compounded bodies that are used as packing in tower installations. These ceramic units are designed primarily for use in process equipment for the chemical or allied industries.

1.2 The physical and chemical properties that affect quality of packing materials are covered in this specification. Properties that affect actual operational efficiency or characteristics of processing towers are not covered.

1.3 The values stated in inch-pound units are to be regarded as the standard. The values given in parentheses are for information only.

1.4 The following precautionary statement pertains to the test method portion only, Section 7, of this standard. *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>2</sup>

C279 Specification for Chemical-Resistant Masonry Units  
C373 Test Method for Water Absorption, Bulk Density, Apparent Porosity, and Apparent Specific Gravity of Fired Whiteware Products, Ceramic Tiles, and Glass Tiles  
E4 Practices for Force Verification of Testing Machines

## 3. Terminology

### 3.1 Definitions:

3.1.1 *tower packing*—a term covering variously shaped ceramic pieces such as spheres, cylindrical rings with either

normal or angular ends, rings with included obstructions, perforated cylinders, and curved saddles. These shapes are used within columns or towers to provide inert surfaces for promotion of energy transfer or chemical reaction between liquids and liquids, gases and liquids, and gases and gases.

3.1.1.1 *Discussion—Clay*: An earthy or stony mineral aggregate consisting, essentially of hydrous silicates of alumina, plastic when sufficiently pulverized and wetted, rigid when dry, and vitreous when fired at a sufficiently high temperature.

3.1.2 *chemical stoneware tower packing*—pieces manufactured from specially compounded bodies consisting of clays and other minerals, of natural origin.

3.1.3 *chemical porcelain tower packing*—pieces manufactured from specially compounded bodies, consisting of refined clays and other naturally occurring minerals. These pieces are characteristically smooth-textured, vitreous, and white or light gray in color.

## 4. Shapes, Sizes, and Quantities

4.1 The number of dumped pieces of cylindrical-type packing per cubic foot shall conform to the requirements for each size of rings, packings, and saddles as specified in Table 1, Table 2, and Table 3 or as negotiated between customer and supplier.

## 5. Tolerances for Rings

5.1 *Dimensional Accuracy*—The average outside diameter and average length shall be within  $\pm 5\%$  of specified size for 80 % of a lot, and within  $\pm 10\%$  of specified size for 100 % of a lot.

5.2 Measurement of the ring shall be made with calipers, avoiding flashes, protrusions, and obviously defective areas. The average outside diameter shall be determined as one half the sum of the maximum and minimum outside diameters. The average length shall be determined as one half the sum of the maximum and minimum lengths.

5.3 *Ovalness*—The difference between maximum and minimum outside diameters of any ring in a lot shall not exceed 10 % of the specified size.

5.4 *Inspection*—The sample plan and procedure shall be as agreed upon by the supplier and purchaser at time of purchase.

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee D32 on Catalysts and is the direct responsibility of Subcommittee D32.02 on Physical-Mechanical Properties.

Current edition approved Dec. 1, 2013. Published December 2013. Originally approved in 1963. Last previous edition approved in 2007 as C515 – 95 (2007). DOI: 10.1520/C0515-13.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

**TABLE 1 Requirements for Shapes, Sizes, and Quantities of Rings**

Raschig Rings		
Size, <sup>A</sup> in. (mm)	Nominal Wall Thickness, in. (mm)	Approximate Number per Cubic Foot <sup>B</sup> (0.03 m <sup>3</sup> )
1/4 (6.4)	1/32 to 1/16 (0.8 to 1.6)	79 200
5/16 (7.9)	1/16 (1.6)	36 000
3/8 (9.5)	3/32 to 1/16 <sup>C</sup> (2.4 to 1.6)	22 500
1/2 (12.7)	3/32 (2.4)	9 960
5/8 (15.9)	3/32 to 1/8 <sup>C</sup> (2.4 to 3.2)	5 360
3/4 (19.1)	3/32 to 1/8 <sup>C</sup> (2.4 to 3.2)	2 890
1 (25.4)	1/8 (3.2)	1 260
1 1/4 (31.8)	3/16 (4.8)	640
1 1/2 (38.1)	1/4 (6.4)	360
2 (50.8)	3/16 to 1/4 <sup>C</sup> (4.8 to 6.4)	155
3 (76.2)	3/8 (9.5)	64 to 74
4 (101.6)	1/2 (12.7)	27 to 31
6 (152.4)	5/8 (15.9)	8 to 9

Lessing Rings		
Size, <sup>A</sup> in. (mm)	Nominal Wall Thickness, in. (mm)	Approximate Number per Cubic Foot <sup>B</sup> (0.03 m <sup>3</sup> )
1 (25.4)	1/8 (3.2)	1220
1 1/4 (31.8)	3/16 (4.8)	620
1 1/2 (38.1)	1/4 (6.4)	330
2 (50.8)	1/4 (6.4) to (9.5) <sup>C</sup>	142
3	5/16 (7.9) to 3/8 (9.5) <sup>C</sup>	44
4	3/8 (9.5) to 1/2 (12.7) <sup>C</sup>	22

Cross Partition Rings			
Size, <sup>A</sup> in. (mm)	Nominal Wall Thickness, in. (mm)	Number per Cubic Foot (0.03 m <sup>3</sup> )	
		Square Set	Stagger Set
3 (76.2)	5/16 (7.9) to 3/8 (9.5)	64	74
4 (101.6)	3/8 (9.5) to 1/2 (12.7)	27	31
6 (152.4)	1/2 (12.7)	8	9

<sup>A</sup> This dimension describes both the specified length and the specified outside diameter, and is intended as a guide rather than as an acceptance criterion.

<sup>B</sup> Dumped, except for values assigned to 3 in. (76.2 mm) of larger rings, which are usually stacked in square or stagger set. These numbers are to be considered as guides rather than as acceptance criteria.

<sup>C</sup> Representative of different manufacturers' practices.

**TABLE 2 Requirements for Sizes and Quantities of Saddles**

Saddles	
Saddle Designation	Approximate Number per Cubic Foot <sup>A</sup> (0.03 m <sup>3</sup> ) <sup>B</sup>
1/4	115 000
3/8	50 000
1/2	17 000
3/4	6 200
1	2 100
1 1/2	650
2	240
3	50

<sup>A</sup> As randomly dumped.

<sup>B</sup> 1 in. = 25.4 mm.

NOTE 1—See Table 2 for piece size counts of saddles which define size tolerances.

**TABLE 3 Requirements for Shapes, Sizes, and Quantities of Saddles<sup>A</sup>**

Berl Saddles <sup>B</sup>		Square Cut Saddles <sup>C</sup>	
Size, in. (mm) <sup>D</sup>	Minimum Number per Cubic Foot <sup>E</sup> (0.03 m <sup>3</sup> )	Size, in. (mm) <sup>D</sup>	Minimum Number per Cubic Foot <sup>E</sup> (0.03 m <sup>3</sup> )
1-4	96 050	1/4	99 450
1/2	15 840	1/2	18 630
3/4	4 700	3/4	6 110
1	2 070	1	2 240
1 1/2	630	1 1/2	675
2	238	2	257

<sup>A</sup> Saddle shapes and piece count shall conform to samples previously approved by the consumer.

<sup>B</sup> See United States Patent 1,796,501. This saddle is disclosed in an expired patent. Interested parties are invited to submit information regarding the identification of an alternative(s) to this item to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,<sup>1</sup> which you may attend.

<sup>C</sup> See United States Patent 2,639,909. This saddle is disclosed in an expired patent. Interested parties are invited to submit information regarding the identification of an alternative(s) to this item to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,<sup>1</sup> which you may attend.

<sup>D</sup> 1 in. = 25.4 mm.

<sup>E</sup> See Footnote B to Table 1.

## 6. Chemical Composition

6.1 The appearance of iron or other leachable impurities on the surfaces may be cause for rejection if this is a matter of concern to the purchaser.

6.2 The presence of undesirable trace elements such as boron is to be considered as a special case and will be treated as such by the purchaser and the manufacturer.

## 7. Test Methods

7.1 *Crushing Tests*—Make crushing tests on any standard machine conforming to the requirements of Practice E4. Break ten or more specimens between 1/8-in. (3.2-mm) thick squares of a metal that is oil-hardened to HR C60, with cushions of 0.022-in. (0.56-mm) blotting paper between the hardened plate and the specimen as shown in Fig. 1. The loading rate shall be between 0.2 to 1.0 in. (5 to 25 mm)/min, or between 100 to 500 lbf/min (445 to 2224 N/min). The report shall include the average load causing failure, calculated in pounds-force per linear inch (or newtons per metre) and the loading rate used.

## 8. Physical Requirements

8.1 *Crushing Strength*—Ceramic tower packing in the form of rings must withstand a load of at least 25 lbf/linear in. (4.4 kN) when the load is applied (distributed) along a full element of the cylinder which lies in a longitudinal plane containing the cylinder axis. In the case of cross-partition rings, the load must be distributed along an element in a longitudinal plane containing the cylinder axis and midway between the partitions.

### 8.2 Water Absorption:

8.2.1 Porcelain packing shall absorb no more than 0.5 weight percent water as determined in accordance with Test Method C373.

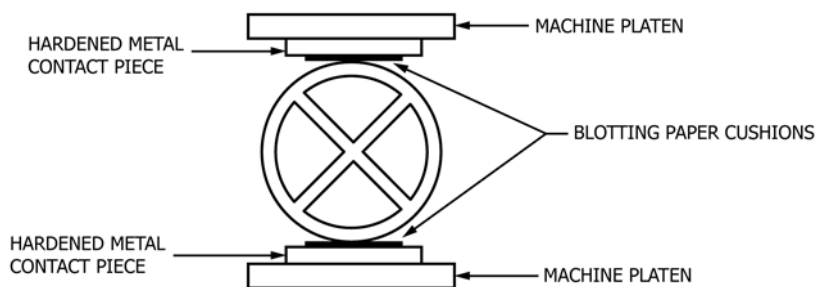


FIG. 1 Arrangement of Apparatus for Crushing Test

8.2.2 Stoneware packing shall absorb no more than 3 weight percent water as determined in accordance with Test Method C373.

### 8.3 Acid-Resisting Properties.

NOTE 2—Ceramic tower packings are used in acidic or chemically neutral solutions and as heat transfer media.

8.3.1 Porcelain packing shall lose no more than 4 % of its original weight when determined in accordance with Section 7 of Specification C279.

8.3.2 Stoneware packing shall lose no more than 10 % of its original weight as determined in accordance with Specification C279.

NOTE 3—In preparing samples no attempt shall be made to remove the skin surface of the units and a significant random sample should be taken for use in Specification C279.

## 9. Precision and Bias

9.1 The determination of water absorption by Test Method C373 is accurate to  $\pm 0.2$  % water absorption in interlaboratory

testing when the average value recorded by all laboratories is assumed to be the true water absorption. The precision is approximately  $\pm 0.1$  % water absorption on measurements made by a single experienced operator.

9.2 The original data on acid weight loss on eight (8) different types of cross partition rings run by four different labs in accordance with Specification C279 gave the following standard deviations:

Type of Ring	Standard Deviation
1-in. porcelain	0.36
3-in. porcelain	0.42
1-in. Stoneware	0.48
3-in. Stoneware	0.92
3-in. Clay	3.22

## 10. Keywords

10.1 acid resistance; ceramic; chemical-resistant; crushing strength; low absorption; porcelain; rings; saddles; stoneware; tower packing

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/*