



# Standard Test Methods for Tension Testing of Carbon and Graphite Mechanical Materials<sup>1</sup>

This standard is issued under the fixed designation C565; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reappraisal.

## 1. Scope\*

1.1 These test methods cover the apparatus, specimen, and procedures for the tension testing of carbon and graphite mechanical materials with a grain size smaller than 0.79 mm.

1.2 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.2.1 *Exception*—All of the figures are dimensioned in inches in accordance with the original standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

**C749** Test Method for Tensile Stress-Strain of Carbon and Graphite

**E4** Practices for Force Verification of Testing Machines

**E6** Terminology Relating to Methods of Mechanical Testing

## 3. Terminology

3.1 *Definitions:*

3.1.1 The definitions of terms relating to tension testing in Terminology **E6** shall be considered as applying to the terms used in these test methods.

3.1.2 *tensile strength,  $n$* —property of solid material that indicates its ability to withstand a uniaxial tensile load, converted to unit stress based on the original cross-section area of the tensile test specimen.

3.1.3 *ultimate tensile strength,  $n$* —the maximum tensile stress applied in stretching a specimen to rupture.

## 4. Significance and Use

4.1 These test methods may be used for quality control testing of established grades of carbon and graphite materials, in the development of new grades, and for other purposes where relative strength levels are the primary quantities of interest. This test method may be applicable only if the ratio of specimen diameter to grain size, or flaw size, is greater than 5.

4.2 These test methods do not substitute for that described in Test Method **C749**, but are useful where less sophisticated data and less expensive techniques are sufficient.

4.3 Carbon and graphite materials exhibit significant physical property differences within parent materials. Exact sampling patterns and grain orientations must be specified in order to make meaningful tensile strength comparisons.

## 5. Apparatus

5.1 *Testing Machine*—The machine used for tension testing shall conform to the requirements of Practices **E4**. The testing machine shall have a capacity that the breaking load of the test specimen falls between 10 % and 90 % of the scale capacity.

5.2 *Gripping Devices*—Gripping devices that conform to the principles of those illustrated in **Fig. 1** shall be used (dimensions that reflect the use of SI units are permissible). These gripping devices shall be attached to the heads of the testing machine through chain connectors. **Fig. 2** shows the gripping device connected to the heads. Extreme care shall be taken that the axis of the test specimen is located on the center line of the head of the testing machine.

## 6. Test Specimens

6.1 Test specimens shall be produced to the configuration shown in **Fig. 3**.


6.2 Improperly prepared test specimens often cause unsatisfactory test results. It is important, therefore, that care be exercised in the preparation of specimens, particularly in the machining and polishing.

6.3 The specimen shall be hand polished with No. 000 dry paper until no circular grooves are visible to the naked eye.

<sup>1</sup> These test methods are under the jurisdiction of ASTM Committee **D02** on Petroleum Products, Liquid Fuels, and Lubricants and are the direct responsibility of Subcommittee **D02.F0** on Manufactured Carbon and Graphite Products.

Current edition approved Dec. 1, 2015. Published January 2016. Originally approved in 1965. Last previous edition approved in 2010 as C565 – 93(2010) <sup>$\epsilon$ 1</sup>. DOI: 10.1520/C0565-15.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

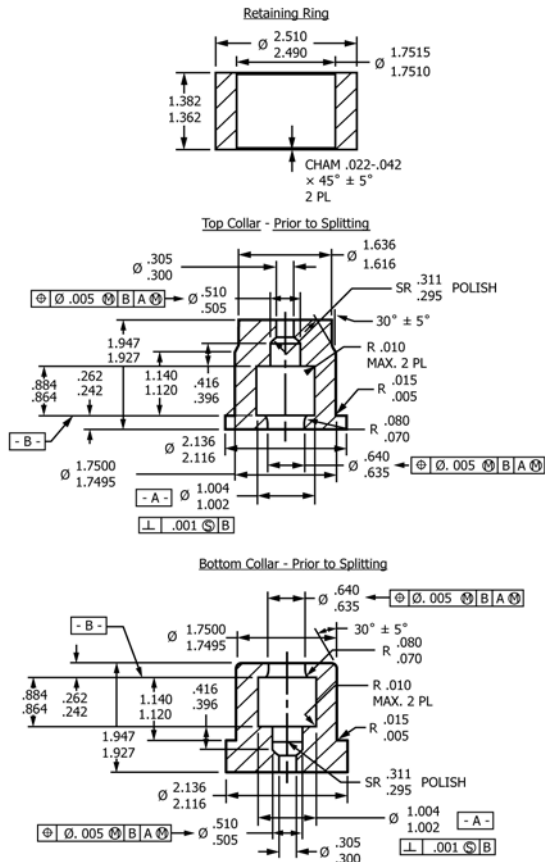

NOTE 1—All dimensions are in inches.

NOTE 2—Material is stainless steel.

NOTE 3—Surface finish of working surfaces, 11 microinches AA or better.

NOTE 4—Break all sharp corners.

NOTE 5—Top and bottom collars to be split into two 180° sections. Max cutwidth not to exceed 1/16 in.

FIG. 1 Gripping Devices

6.4 The acceptable fracture zone of the specimen shall be 19 mm long with the center of the zone at the point of minimum diameter. Marks indicating fracture zone limits may be applied with ink or layout dope, but no scratching, punching, or notching of the specimen is permissible.

6.5 To determine the cross-sectional area, the diameter of the specimen at the narrowest point shall be used. The dimension shall be recorded to the nearest 0.02 mm.

## 7. Speed of Testing

7.1 Speed of testing may be defined in terms of free-running of the crosshead speed or in terms of rate of stressing the specimen. Both methods are permissible.

7.2 When free-running crosshead speed is used, the speed shall be 0.50 % ± 10 % mm/min.

7.3 When rate of stressing the specimen is used, an applied force of 890 N/min ± 220 N/min shall be used.

## 8. Tensile Strength

8.1 Calculate the tensile strength by dividing the maximum load carried by the specimen during a tension test by the


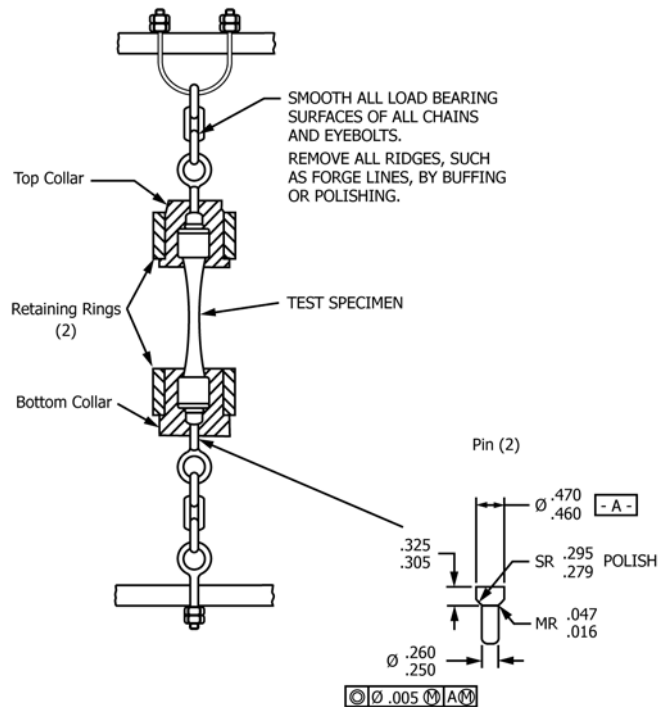


FIG. 2 Test Setup

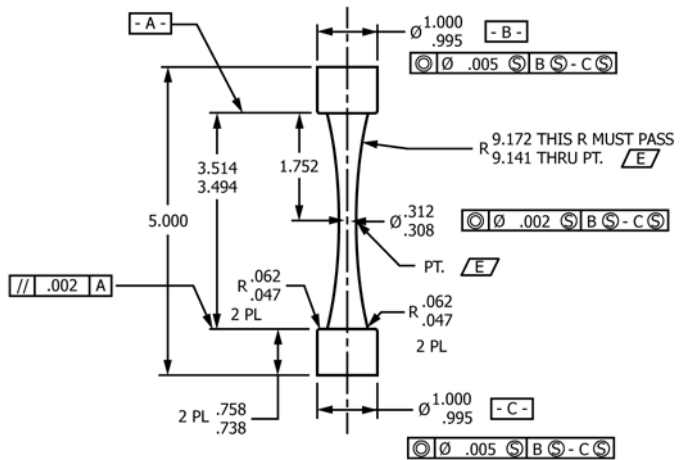

NOTE 1—All dimensions are in inches.

NOTE 2—Specimen shall be hand-polished on 9.141 to 9.172 radius with No. 000 dry paper until no circular grooves are visible to the naked eye.

FIG. 3 Test Specimen

cross-sectional area of the specimen as defined in 6.5. The weight of the bottom grip assembly must be accounted for in the tensile strength calculation.

8.2 If any part of the fracture takes place outside the acceptable fracture zone as defined in 6.4, the test shall be discarded but reported.

## 9. Report

9.1 Report the following:

9.1.1 Identification; manufacturer, grade number, lot number, and original material size;

- 9.1.2 Average ultimate tensile strength (MPa);
- 9.1.3 Method of loading (see Section 7);
- 9.1.4 Number of samples tested;
- 9.1.5 Number of samples reported;
- 9.1.6 Standard deviation (MPa); and
- 9.1.7 Specimen orientation.

## 10. Precision and Bias

10.1 These test methods are intended to be less sophisticated than the method described in Test Method C749. For this reason an interlaboratory test program was not performed, but rather a direct comparison of the two tensile-test techniques was made. Two graphite grades of low variability were tested by two different laboratories, one with extensive experience with Test Method C749, the other in the technique of this standard.

10.2 The details of the experiments, the data base, and the statistical analyses may be obtained from ASTM.<sup>3</sup>

10.3 *Precision*—Approximately 20 specimens of the two materials were supplied for testing under these test methods

and ten specimens for testing under Test Method C749. The resulting data were examined for outliers by the Dixon Test, Grubb's *T*-Test, and skewness. The data sets were examined for normality by the Kolmogorov-Smirnov Test and for skewness and kurtosis. No outliers were found and only kurtosis for the two ten-specimen sets was found to be significant. This does not invalidate a test on means.

10.3.1 By the approximate *T*-test, the means for the two techniques were found to be the same for any significance level  $\alpha$  equal to or less than 0.60 (two sided) corresponding to an observed difference in means of 0.9 %. An *F*-test on variance ratios between the two tests showed a significant difference at  $\alpha$  equal to or greater than 0.025 (one sided) for the observed variance ratio of about five.

10.3.2 It is concluded that these test methods will quite satisfactorily produce mean values of tensile strengths, but are not satisfactory for producing good estimates for variance (standard deviation) unless proven by other measurement techniques for the material in question.

10.4 *Bias*—Bias has not been determined.

## 11. Keywords

11.1 carbon; graphite; tensile strength

## SUMMARY OF CHANGES

Subcommittee D02.F0 has identified the location of selected changes to this standard since the last issue (C565 – 93 (2010)<sup>ε1</sup>) that may impact the use of this standard. (Approved Dec. 1, 2015.)

(1) Revised Section 3.

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>*