



## Standard Test Method for Hydrogen Gas Generation of Aluminum Emulsified Asphalt Used as a Protective Coating for Roofing<sup>1</sup>

This standard is issued under the fixed designation D6356/D6356M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

<sup>ε1</sup> NOTE—Units information was editorially revised in June 2011.

### 1. Scope

1.1 This test method covers a hydrogen gas and stability test for aluminum emulsified asphalt coatings.

1.2 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

D1079 [Terminology Relating to Roofing and Waterproofing](#)

D2939 [Test Methods for Emulsified Bitumens Used as Protective Coatings](#) (Withdrawn 2012)<sup>3</sup>

E1 [Specification for ASTM Liquid-in-Glass Thermometers](#)

### 3. Summary of Test Method

3.1 A 200 g sample of water based aluminized coating is heated to  $51.7 \pm 1^\circ\text{C}$  [ $125 \pm 2^\circ\text{F}$ ] in an Erlenmeyer flask and the volume in millilitres of hydrogen gas evolved is measured. The test is conducted for one week (168 h) with a reading taken

every 24 h. The test room is to be maintained at  $73.4 \pm 3.6^\circ\text{F}$  in order to standardize gas collection temperature in the burette receptacle.

### 4. Significance and Use

4.1 This procedure measures the amount of hydrogen gas generation potential of aluminized emulsion roof coating. There is the possibility of water reacting with aluminum pigment to generate hydrogen gas. This situation is to be avoided, so this test was designed to evaluate coating formulations and assess the propensity to gassing.

### 5. Apparatus and Materials

5.1 The assembly of the hydrogen gas generation test apparatus is illustrated in [Fig. 1](#). Details of the component part are as follows:

5.1.1 *Wide Mouth Glass Erlenmeyer Flask*, 250-mL capacity.

5.1.2 *Beaker*, glass, 250-mL.

5.1.3 *Burette*, standard glass 100-mL graduated with glass stopcock and 0.2 mL divisions.

5.1.4 *Condenser*, glass jacketed, having the dimensions shown in [Fig. 2](#).

5.1.5 *Glass Tubing*, standard glass 6.35 mm [ $\frac{1}{4}$  in.] inside diameter 7.94 mm [ $\frac{5}{16}$  in.] outside diameter and 127 mm [5 in.] length for forming the J tube.

5.1.6 *Tubing*, pure latex amber rubber tubing, 6.35 mm [ $\frac{1}{4}$  in.].

5.1.7 *Neoprene Rubber Stopper*, No. 8 with one hole (preferred connection for glass condenser to 250-mL Erlenmeyer flask).

5.1.8 *Oil or Water Bath*—Constant temperature immersion circulating bath capable of temperature control.

5.1.9 *Oil*—Commercially available mineral oil or suitable heat transfer fluid.

5.1.10 *Thermometer*—ASTM thermometer having a range from  $-2$  to  $+80^\circ\text{C}$  [ $30$  to  $180^\circ\text{F}$ ] and conforming to the requirements for thermometer 15C or 15F as prescribed in Specification [E1](#).

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D08 on Roofing and Waterproofing and is the direct responsibility of Subcommittee D08.09 on Bituminous Emulsions.

Current edition approved May 1, 2011. Published June 2011. Originally approved in 1998. Last previous edition approved in 2004 as D6356 – 98 (2004). DOI: 10.1520/D6356\_D6356M-98R11E01.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> The last approved version of this historical standard is referenced on [www.astm.org](http://www.astm.org).

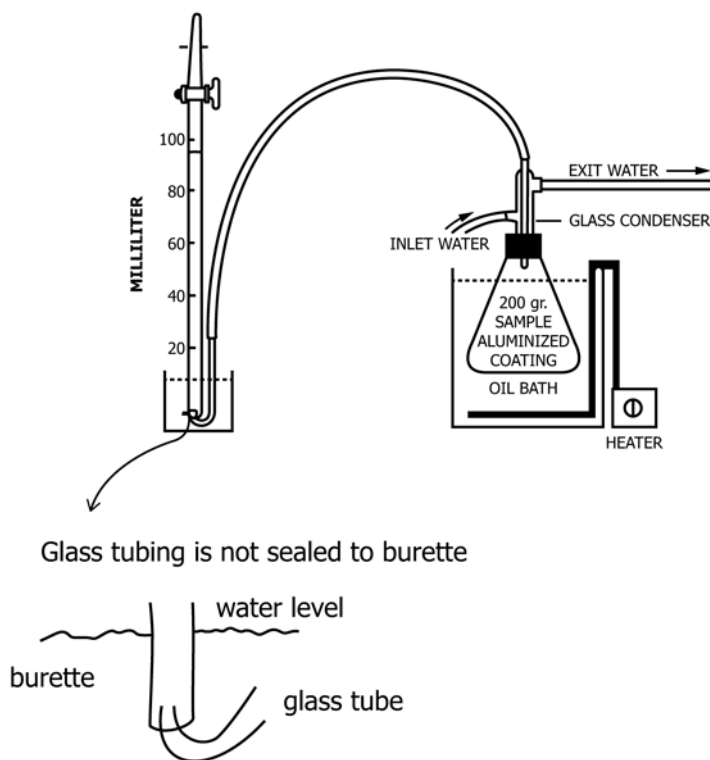


FIG. 1 Hydrogen Gas Generation Test Apparatus

## 6. Sampling

6.1 Sample the material in accordance with Test Methods [D2939](#).

## 7. Procedure

7.1 Weigh 200 g of the sample directly in the 250-mL Erlenmeyer flask ensuring that none coats the neck where the stopper is placed.

7.2 Insert the filled flask into the oil or water bath (temperature controlled to  $51.7 \pm 1^\circ\text{C}$  [ $125 \pm 2^\circ\text{F}$ ]) and connect the glass condenser-stopper into the neck of the flask. Flask should be supported internally via flask holder or externally with a suitable clamping device.

7.3 Fill the 250-mL beaker with water and insert the 100-mL burette and J-tube into the water. Avoid the introduction of water into the J-tube.

7.4 Draw the water level to the 100-mL mark on the burette and close the stopcock.

7.5 Record the time as the start of the induction period.

7.6 After a 1 h induction period, record the time and the water level point on the burette. The latter figure is the zero point. Do not include the one hour induction period level point in the calculation and report.

7.7 Unless otherwise specified, conduct the test at a room temperature of  $23.0 \pm 2^\circ\text{C}$  [ $73.4 \pm 3.6^\circ\text{F}$ ] for one week, (168 h), with a reading taken every 24 h at the corresponding time

that the zero point was taken. It is recognized that test duration is seven days per week and readings may not be practical on weekends or holidays.

7.8 If the gas quantity approaches the confines of the burette, the test should be terminated.

## 8. Calculation and Report

8.1 *Hydrogen Gas Evolution*—Calculate the total millilitres of hydrogen gas evolved to the nearest 0.1-mL as follows:

$$H = V - Z \quad (1)$$

where:

$H$  = hydrogen gas evolved in mL,  
 $V$  = volume of water in burette at 168 h, and  
 $Z$  = zero point volume of water in burette.

8.2 Report the results as the hydrogen gas content to the nearest 0.1 mL.

## 9. Precision and Bias

9.1 See [Table 1](#).

## 10. Keywords

10.1 emulsified asphalt; hydrogen gas; roofing; stability; water based aluminum



**TABLE 1 Statistical Analysis for Gas Evolution of Emulsion Aluminum Coatings Round Robin Results**

Material	$n$	Variance Component Estimate for Laboratory	Variance Component Estimate Between Laboratories	Repeatability	Reproducibility
				$2.83\sqrt{\text{Var}_{\text{Mat}}}$	$2.83\sqrt{\text{Var}_{\text{Mat}} + \text{Var}_{\text{Lab}}}$
E interlaboratory	10	0.92	1.88	2.71	4.74
F interlaboratory	11	1.42	6.19	3.37	7.81
G interlaboratory	11	3.09	13.72	5.0	11.6
H interlaboratory	11	7.25	9.85	7.62	11.7
All materials All laboratories	11	20.00	5.92	12.6	14.4

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or [service@astm.org](mailto:service@astm.org) (e-mail); or through the ASTM website ([www.astm.org](http://www.astm.org)). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>*