



# Standard Test Method for Determining Poisson's Ratio of Honeycomb Cores<sup>1</sup>

This standard is issued under the fixed designation D6790/D6790M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This test method covers the determination of the sandwich honeycomb core Poisson's ratio from the anticlastic curvature radii, see Fig. 1.

1.2 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.2.1 Within the text, the inch-pound units are shown in brackets.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

D2711/C2711M Test Method for Density of Sandwich Core Materials

D883 Terminology Relating to Plastics

D3878 Terminology for Composite Materials

D5229/D5229M Test Method for Moisture Absorption Properties and Equilibrium Conditioning of Polymer Matrix Composite Materials

E122 Practice for Calculating Sample Size to Estimate, With Specified Precision, the Average for a Characteristic of a Lot or Process

E177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods

E456 Terminology Relating to Quality and Statistics

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D30 on Composite Materials and is the direct responsibility of Subcommittee D30.09 on Sandwich Construction.

Current edition approved April 1, 2016. Published April 2016. Originally approved in 2002. Last previous edition approved in 2014 as D6790 - 14. DOI: 10.1520/D6790\_D6790M-16.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

## 3. Terminology

3.1 *Definitions*—Terminology D3878 defines terms relating to high-modulus fibers and their composites, as well as terms relating to sandwich constructions. Terminology D883 defines terms relating to plastics. Terminology E456 and Practice E177 define terms relating to statistics. In the event of a conflict between terms, Terminology D3878 shall have precedence over the other terminologies.

3.2 *Symbols:*  $c$  = chord measurement

$CV$  = coefficient of variation statistic of a sample population for a given property (in percent)

$d$  = depth measurement

$R_a$  = anticlastic curvature radius

$R_c$  = cylinder radius

$S_{n-1}$  = standard deviation statistic of a sample population for a given property

$x_i$  = test result for an individual specimen from the sample population for a given property

$\bar{x}$  = mean or average (estimate of mean) of a sample population for a given property

$\nu$  = Poisson's ratio

## 4. Summary of Test Method

4.1 This test method determines the Poisson's ratio of sandwich honeycomb core by bending the core around a cylinder and taking measurements of the anticlastic curvature that occurs.

## 5. Significance and Use

5.1 Certain sandwich panel analyses require the Poisson's ratio of the honeycomb core. It is not possible to measure the honeycomb's Poisson's ratio by conventional methods.

5.2 This test method provides a standard method of determining the Poisson's ratio of honeycomb core materials for design properties, material specifications, research and development applications, and quality assurance.

5.3 Factors that influence the Poisson's ratio of honeycomb core materials and shall therefore be reported include the following: core material, methods of material fabrication, core geometry, core thickness, core thickness uniformity, cell wall thickness, specimen geometry, specimen preparation, and specimen conditioning.

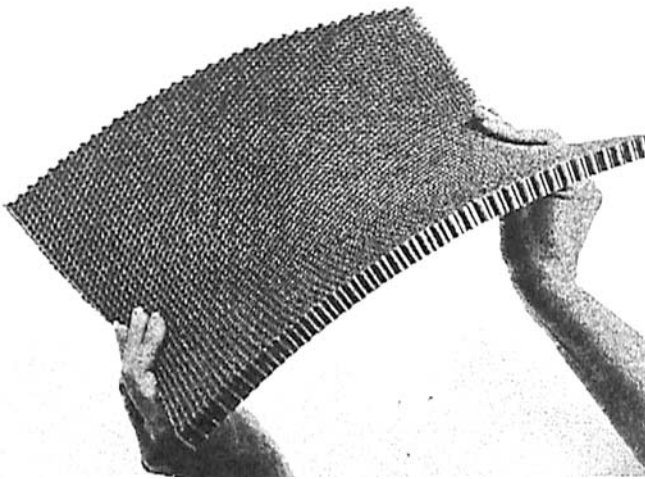


FIG. 1 Anticlastic Curvature

## 6. Interferences

6.1 The test method described here is one means of obtaining the Poisson's ratio of honeycomb core. However, this test method has not been widely used, and it is in its conceptual stage.

6.2 *Material and Specimen Preparation*—Poor material fabrication practices and damage induced by improper specimen machining are known causes of high data scatter for sandwich cores. Important aspects of sandwich core specimen preparation that contribute to data scatter include the existence of joints, voids or other core discontinuities, out-of-plane curvature, and surface roughness. Non-uniform edge geometry can influence the measurement of the chord distance described in 11.6.

6.3 *Core Geometry*—Core-specific geometric factors that affect Poisson's ratio include core cell size, uniformity of core cell geometry, core cell wall thickness, core cell wall thickness uniformity, core thickness, and core thickness uniformity.

6.4 *Environment*—Results are affected by the environmental conditions under which specimens are conditioned, as well as the conditions under which the core is tested. Specimens tested in various environments can exhibit differences in Poisson's ratio.

6.5 *Specimen-Cylinder Contact*—Results may vary if the specimen is too rigid in bending to permit intimate contact of its surface with the cylinder along the specimen center line without fracturing the core. Use of a larger cylinder radius is recommended if the midpoints of two parallel ends of the core specimen cannot be made to contact the standard cylinder using light hand pressure.

6.6 *Measurement Devices*—Measurements for anticlastic curvature depth described in 11.6 may be affected by the width of the scale described in 7.3 where it contacts the specimen.

## 7. Apparatus

7.1 *Micrometers and Calipers*—A micrometer having a flat anvil interface, or a caliper of suitable size, shall be used. The accuracy of the instrument(s) shall be suitable for reading to

within 0.5 % of the sample length, width and thickness. For typical specimen geometries, an instrument with an accuracy of  $\pm 0.025$  mm [ $\pm 0.001$  in.] is desirable for thickness measurement, whereas an instrument with an accuracy of  $\pm 0.25$  mm [ $\pm 0.01$  in.] is desirable for length and width measurement.

7.2 *Cylinders*—A cylinder shall be utilized to bend the core to a defined radius of curvature. Standard tests shall utilize a cylinder of 305 mm [12 in.] radius. This radius is generally acceptable for testing of cores up to 25 mm [1.0 in.] in thickness. A larger cylinder radius shall be used if the midpoints of two parallel ends of the core specimen cannot be made to contact the standard cylinder using light hand pressure without fracturing the core. Tests conducted using non-standard cylinder radii must be designated as such, with the cylinder radius reported with any test results.

7.3 *Scale*—A scale is required that is capable of measuring length with an accuracy of  $\pm 1$  mm [ $\pm 0.05$  in.].

7.4 *Straight Edge*—A straight edge is required that is capable of measuring length with an accuracy of  $\pm 1$  mm [ $\pm 0.05$  in.].

## 8. Sampling and Test Specimens

8.1 *Sampling*—Test at least five specimens per test condition unless valid results can be gained through the use of fewer specimens, such as in the case of a designed experiment. For statistically significant data, consult the procedures outlined in Practice E122. Report the method of sampling.

### 8.2 Test Specimens:

8.2.1 *Core Geometry*—Core test specimens shall be square. The length and width should be great enough to obtain an anticlastic curvature when the specimen is bent over the cylinder. A specimen size of 300 by 300 mm [12 by 12 in.] in planar dimensions is recommended. For honeycomb cores, the planar dimension cross-section is defined to be in the facing plane (in regard to the orientation that the core would be placed in a structural sandwich construction) and is perpendicular to the orientation of the cell walls. Larger specimen sizes may be required if the cylinder radius is larger than 305 mm [12 in.].

8.2.2 *Core Thickness*—Various core thicknesses should be tested. A core thickness of 13 mm (0.50 in.) is recommended as a starting thickness.

8.2.3 *Core Preparation and Machining*—Prepare the core material samples so that the facing plane surfaces are parallel to each other and perpendicular to the sides of the core. Take precautions when cutting specimens from large sheets of core material to avoid notches, undercuts, rough or uneven surfaces due to inappropriate machining methods. Record and report the core material specimen cutting preparation method.

8.3 *Labeling*—Label the test specimens so that they will be distinct from each other and traceable back to the sheet of origin, and will neither influence the test nor be affected by it.

## 9. Calibration

9.1 The accuracy of all measuring equipment shall have certified calibrations that are current at the time of use of the equipment.

## 10. Conditioning

10.1 The recommended pre-test condition is effective moisture equilibrium at a specific relative humidity as established by Test Method [D5229/D5229M](#); however, if the test requestor does not explicitly specify a pre-test conditioning environment, no conditioning is required and the test specimens may be tested as prepared.

10.2 The pre-test specimen conditioning process, to include specified environmental exposure levels and resulting moisture content, shall be reported with the test data.

NOTE 1—The term “moisture,” as used in Test Method [D5229/D5229M](#), includes not only the vapor of a liquid and its condensate, but the liquid itself in large quantities, as for immersion.

10.3 If no explicit conditioning process is performed, the specimen conditioning process shall be reported as “unconditioned” and the moisture content as “unknown.”

## 11. Procedure

### 11.1 Parameters to be Specified Before Test:

11.1.1 The specimen sampling method, specimen geometry, and conditioning travelers (if required).

11.1.2 The properties and data reporting format desired.

NOTE 2—Determine specific material property, accuracy, and data reporting requirements prior to test for proper selection of apparatus.

11.1.3 The environmental conditioning parameters.

### 11.2 General Instructions:

11.2.1 Report any deviations from this test method, whether intentional or inadvertent.

11.2.2 If core material density is to be reported, then obtain these samples from the same sheet of core material being tested. Density may be evaluated in accordance with Test Method [C271/C271M](#).

11.2.3 Following final core material specimen machining, but before conditioning and testing, measure the specimen length and width in the planar dimensions at three places. The thickness of the specimen shall be measured at four locations and recorded as the average of the four measurements. The accuracy of these measurements shall be within 0.5 % of the dimension. Measure the specimen length and width with an

accuracy of  $\pm 0.25$  mm [ $\pm 0.010$  in.]. Measure the specimen thickness with an accuracy of  $\pm 0.025$  mm [ $\pm 0.001$  in.]. Record the dimensions to three significant figures in units of millimetres [inches].

11.3 Condition the specimens as required. Store the specimens in the conditioned environment until test time, if the test environment is different from the conditioning environment.

11.4 Following final specimen conditioning, but before testing, re-measure the specimen length, width, and thickness as in [11.2.3](#). Mark the midpoint along each of the specimen edges with an accuracy of  $\pm 1$  mm [ $\pm 0.05$  in.] (ensuring the marking medium will neither influence the test nor be affected by it).

11.5 Bend the honeycomb core specimen around the cylinder of known radius, making sure the midpoints of two parallel ends of the specimen contact the cylinder. If the ends of the specimen cannot be made to contact the standard cylinder using light hand pressure without fracturing the core, a larger cylinder radius shall be used to determine the Poisson’s ratio.

11.6 With the specimen bent around the cylinder, place the straight edge (specified in [7.4](#)) across the midpoints of the two edges of the specimen not in contact with the cylinder (as shown in [Fig. 2](#)) and measure the chord distance,  $c$ . Using the measured chord distance, locate and mark the midpoint of the straight edge (as shown in [Fig. 2](#)) with an accuracy of  $\pm 1$  mm [ $\pm 0.05$  in.]. Position the scale (specified in [7.3](#)) at the midpoint of the straight edge (as shown in [Fig. 2](#)) and measure the depth,  $d$ . Take care to avoid imparting transverse forces to the specimen when positioning the straight edge and scale, as such loading can affect the chord distance and depth measurements.

## 12. Validation

12.1 Property values shall not be calculated for any specimen that contains some obvious flaw described in [6.2](#), unless such flaw constitutes a variable being studied. Resets shall be performed for any specimen on which values are not calculated.

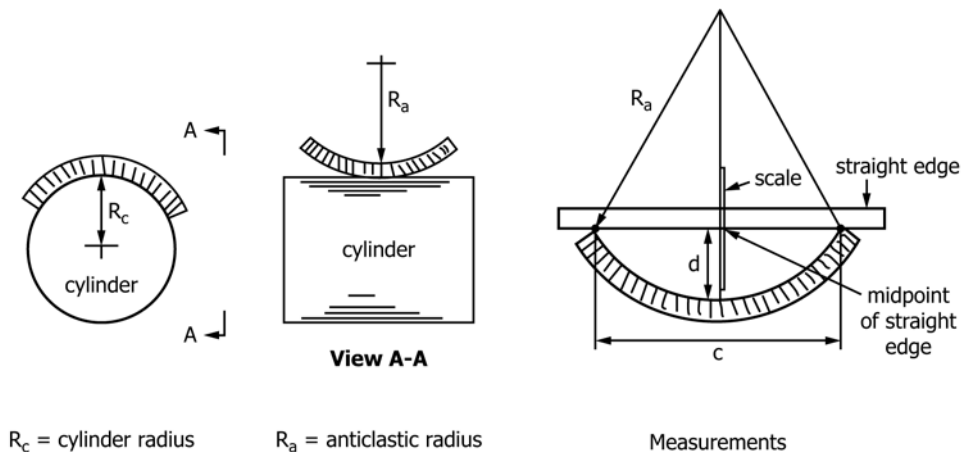


FIG. 2 Measurements



### 13. Calculations

13.1 *Poisson's Ratio*—Calculate the anticlastic curvature radius,  $R_a$ , and Poisson's ratio,  $\nu$ , of the specimens as follows:

$$R_a = \frac{4d^2 + c^2}{8d} \quad \nu = \frac{R_c}{R_a} \quad (1)$$

(see Fig. 2)

where:

$\nu$  = Poisson's ratio,  
 $R_a$  = anticlastic curvature radius,  
 $R_c$  = cylinder radius,  
 $c$  = chord measurement, and  
 $d$  = depth measurement.

13.2 *Statistics*—For each series of test samples, calculate average value, standard deviation, and coefficient of variation (in percent) for Poisson's ratio:

$$\bar{x} = \frac{\left( \sum_{i=1}^n X_i \right)}{n} \quad (2)$$

$$S_{n-1} = \sqrt{\frac{\left( \sum_{i=1}^n x_i^2 - n \bar{x}^2 \right)}{(n-1)}} \quad (3)$$

$$CV = 100 \times \frac{S_{n-1}}{\bar{x}} \quad (4)$$

where:

$\bar{x}$  = sample mean (average),  
 $S_{n-1}$  = sample standard deviation,  
 $CV$  = sample coefficient of variation, %,  
 $n$  = number of specimens, and  
 $x_i$  = measured or derived property.

### 14. Report

14.1 Report the following information, or references pointing to other documentation containing this information, to the maximum extent applicable (reporting of items beyond the control of a given testing laboratory, such as might occur with material details or specimen fabrication parameters, shall be the responsibility of the requestor):

14.1.1 The revision level or date of issue of this test method.

14.1.2 The name(s) of the test operator(s).

14.1.3 Any variations to this test method, anomalies noticed during testing, or equipment problems occurring during testing.

14.1.4 Identification of all the materials constituent to the sandwich core specimen tested, including for each: material specification, material type, manufacturer's material designation, manufacturer's batch or lot number, source (if not from manufacturer), date of certification, and expiration of certification.

14.1.5 Description of the fabrication steps used to prepare the sandwich core specimen including: fabrication start date, fabrication end date, process specification(s), and a description of the equipment used.

14.1.6 Method of preparing the test specimen, including specimen labeling scheme and method, specimen geometry, sampling method, and specimen cutting method(s).

14.1.7 Results of any nondestructive evaluation tests.

14.1.8 Calibration dates and methods for all measurements and test equipment.

14.1.9 Individual values of length, width, and thickness for each specimen (prior to and after conditioning, if appropriate).

14.1.10 Measured core density.

14.1.11 Conditioning parameters and results.

14.1.12 Relative humidity and temperature of the testing laboratory.

14.1.13 Number of specimens tested.

14.1.14 Cylinder radius.

14.1.15 Dimensions of which core direction was bent over the cylinder,  $L$  or  $W$ .

14.1.16 Individual chord distance measurements, depth measurements, and anticlastic curvature radius values.

14.1.17 The Poisson's ratios; individual values, averages, standard deviations, and coefficients of variation.

### 15. Precision and Bias

15.1 *Precision*—The data required for the development of a precision statement are not available for this test method.

15.2 *Bias*—Bias cannot be determined for this test method as no acceptable reference material exists.

### 16. Keywords

16.1 core; honeycomb; Poisson's ratio

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/*