



Designation: E749/E749M – 17

Standard Practice for Acoustic Emission Monitoring During Continuous Welding¹

This standard is issued under the fixed designation E749/E749M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope*

1.1 This practice provides recommendations for acoustic emission (AE) monitoring of weldments during and immediately following their fabrication by continuous welding processes.

1.2 The procedure described in this practice is applicable to the detection and location of AE sources in weldments and in their heat-affected zone during fabrication, particularly in those cases where the time duration of welding is such that fusion and solidification take place while welding is still in progress.

1.3 The effectiveness of acoustic emission to detect discontinuities in the weldment and the heat-affected zone is dependent on the design of the AE system, the AE system verification procedure, the weld process, and the material type. Materials that have been monitored include low-carbon steels, low-alloy steels, stainless steels, and some aluminum alloys. The system performance must be verified for each application by demonstrating that the defects of concern can be detected with the desired reliability.

1.4 *Units*—The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

1.6 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

¹ This practice is under the jurisdiction of ASTM Committee E07 on Nondestructive Testing and is the direct responsibility of Subcommittee E07.04 on Acoustic Emission Method.

Current edition approved June 1, 2017. Published June 2017. Originally approved in 1980. Last previous edition approved in 2012 as E749-12. DOI: 10.1520/E0749-17.

2. Referenced Documents

2.1 ASTM Standards:²

E543 Specification for Agencies Performing Nondestructive Testing

E569 Practice for Acoustic Emission Monitoring of Structures During Controlled Stimulation

E650 Guide for Mounting Piezoelectric Acoustic Emission Sensors

E1316 Terminology for Nondestructive Examinations

2.2 ASNT Standards:³

SNT-TC-1A Recommended Practice for Nondestructive Testing Personnel Qualification and Certification

ANSI/ASNT CP-189 Standard for Qualification and Certification of Nondestructive Testing Personnel

2.3 AIA Standard:⁴

NAS-410 Certification and Qualification of Nondestructive Personnel (Quality Assurance Committee)

2.4 ISO Standard:⁵

ISO 9712 Non-Destructive Testing: Qualification and Certification of NDT Personnel

3. Terminology

3.1 *Definitions*—For definitions of terms relating to acoustic emission testing, see Section B of Terminology E1316.

4. Significance and Use

4.1 Detection and location of AE sources in weldments during fabrication may provide information related to the integrity of the weld. Such information may be used to direct repair procedures on the weld or as a guide for application of other nondestructive evaluation (NDE) methods. A major attribute of applying AE for in-process monitoring of welds is

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from American Society for Nondestructive Testing (ASNT), P.O. Box 28518, 1711 Arlingate Ln., Columbus, OH 43228-0518, <http://www.asnt.org>.

⁴ Available from Aerospace Industries Association of America, Inc. (AIA), 1000 Wilson Blvd., Suite 1700, Arlington, VA 22209-3928, <http://www.aia-aerospace.org>.

⁵ Available from International Organization for Standardization (ISO), ISO Central Secretariat, BIBC II, Chemin de Blandonnet 8, CP 401, 1214 Vernier, Geneva, Switzerland, <http://www.iso.org>.

*A Summary of Changes section appears at the end of this standard

the ability of the method to provide immediate real-time information on weld integrity. This feature makes the method useful to lower weld costs by repairing defects at the most convenient point in the production process. The AE activity from discontinuities in the weldment is stimulated by the thermal stresses from the welding process. The AE activity resulting from this stimulation is detected by AE sensors in the vicinity of the weldment, which convert the acoustic waves into electronic signals. The AE instrumentation processes signals and provides means for immediate display or indication of AE activity and for permanent recordings of the data.

4.2 Items to be considered in preparation and planning for monitoring should include but not be limited to the following:

- 4.2.1 Description of the system or object to be monitored or examined,
- 4.2.2 Extent of monitoring, that is, entire weld, cover passes only, and so forth,
- 4.2.3 Limitations or restrictions on the sensor mounting procedures, if applicable,
- 4.2.4 Performance parameters to be established and maintained during the AE system verification procedure (sensitivity, location accuracy, and so forth),
- 4.2.5 Maximum time interval between AE system verification checks,
- 4.2.6 Performance criteria for purchased equipment,
- 4.2.7 Requirements for permanent records of the AE response, if applicable,
- 4.2.8 Content and format of test report, if required, and
- 4.2.9 Operator qualification and certification, if required.

5. Basis of Application

5.1 The following items are subject to contractual agreement between the parties using or referencing this practice.

5.2 Personnel Qualification:

5.2.1 If specified in the contractual agreement, personnel performing examinations to this standard shall be qualified in accordance with a nationally or internationally recognized NDT personnel qualification practice or standard such as ANSI/ASNT CP-189, SNT-TC-1A, NAS-410, ISO 9712, or a similar document and certified by the employer or certifying agency, as applicable. The practice or standard used and its applicable revision shall be identified in the contractual agreement between the using parties.

5.3 *Qualification of Nondestructive Agencies*—If specified in the contractual agreement, NDT agencies shall be qualified and evaluated as described in Practice E543. The applicable edition of Practice E543 shall be specified in the contractual agreement.

5.4 *Procedures and Techniques*—The procedures and techniques to be utilized shall be as specified in the contractual agreement.

6. Examination Preparation

6.1 The following preparatory procedures should be completed before initiating AE monitoring:

6.1.1 Select the location(s) where the sensor(s) will be acoustically coupled. The sensor(s) should be centrally located

near the weldment to provide for optimal AE response from all portions of the weld. If the sensor(s) are piezoelectric, this location should be such that the maximum temperature stays below manufacturers' specifications of the sensor(s). Take care in selecting the sensor mounting locations to avoid contact or disturbance, or both, of the sensor by any of the welding or structural positioning equipment. Typical distances from 150 to 300 mm [6 to 12 in.] from the heat-affected zone of the weld are usually satisfactory. Typical fixed sensor placement patterns that have been successfully used are shown in Figs. 1-3.

6.1.1.1 If a fixed contact sensor(s) is used, clean the area(s) where attachment will be made to eliminate loose scale, welding flux, or other debris, and attach the sensor in accordance with Guide E650.

6.1.1.2 If moving sensors are used, clean the coupling path so that uniform sensitivity is maintained as the sensor moves. Fig. 4 shows side and top views of a typical configuration for moving sensors.

6.1.2 Position and route the signal cables connecting the sensor(s) to the AE instrumentation to avoid contacting the hot weld bead or entangling the welding and positioning equipment.

6.1.3 Adjustment of Apparatus:

6.1.3.1 After all sensors are mounted, connected, and operational (without objectionable background noise), the AE monitoring system can then be adjusted using an AE simulator.

6.1.3.2 *Gain Adjustment*—To set or select the overall gain for a channel (if necessary), locate the acoustic emission simulator at a selected distance adjacent to the sensor. Monitor the response to the simulated emission, and adjust the overall channel gain to a specified amplitude level. Repeat this procedure two times, placing the simulator at the same distance from the sensor but at different azimuthal positions relative to the original simulator positions (see Fig. 5). Record the average gain for the three simulator positions. Repeat the entire procedure for each AE sensor on the structure, and adjust the gains. The average gains for all channels should give responses to the simulator that have peak voltages identical to within ± 3 dB.

6.1.4 *Determination of Source-Location Accuracy*—Check the operation of the AE source-location function by analyzing simulated AE signals from several random locations in the weld and on the structure, as well as from any specific critical locations. For each placement of the simulator, determine and record the precision and accuracy of the AE location function. It should be noted that the accuracy of locating the simulator source will not necessarily be the same as for locating a real AE source. During trial welding in multi-pass configurations, it should be verified that location accuracy is maintained during

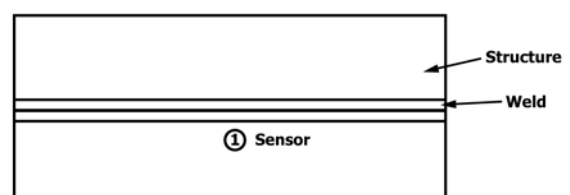


FIG. 1 Typical Sensor Placement for Single Channel AE Monitoring of a Linear Weld

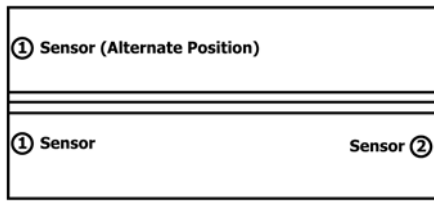


FIG. 2 Typical Sensor Placement for Two-Channel AE Monitoring of a Linear Weld

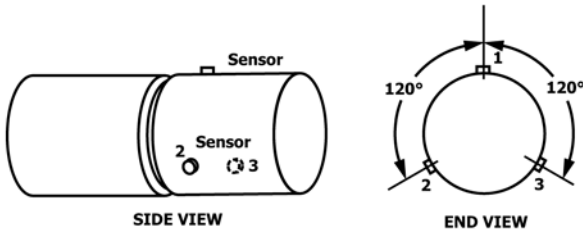


FIG. 3 Typical Sensor Placement for Three-Channel AE Monitoring of a Circular Weld

weld buildup. Experiments indicate that location accuracy depends on the percentage completion of multi-pass welds.

6.2 Check the integrity of the welding ground return system to eliminate the possibility of diverting the weld currents to the AE instrumentation ground.

7. Apparatus

7.1 The AE apparatus normally consists of sensors, preamplifiers, and electronic instrumentation with display and recording capabilities. Acoustic emission monitoring during welding places many specialized requirements on AE apparatus due to severe environmental factors and interfering noise sources. The following criteria provide guidelines to aid in minimizing these interfering factors, and maximizing the effectiveness of the monitoring process:

7.1.1 *Sensors* should be used that are capable of operating in the temperature range to be encountered. Use of “high-temperature” sensors or waveguides to isolate conventional sensors may be necessary for multi-pass, high heat input welds, or welds maintained at elevated preheat temperatures. The sensors should be electrically insulated from the structure under test to ensure that the weld current or welder ground is not coupled into the AE instrumentation. If the weld current is pulsed or has a significant transient component, differential sensors may aid in suppressing interference.

7.1.2 *Frequency Bandpass Filters* are recommended to minimize background noise interference during AE monitoring of welding. A low-frequency limit to the passband in the vicinity of 100 kHz will aid in minimizing background noise due to mechanical noise sources such as grinding, chipping, and manipulation of the structure under test. Radio frequency interference due to contactors and heavy electrical machinery, as well as the welding arc, may be minimized by use of a high-frequency limit to the passband ranging from 100 kHz to 1 MHz. The sensor operating frequency range should be compatible with the above considerations.

7.2 The *Welding Arc* is a low-level continuous source of AE. To minimize interference from the welding arc, the sensitivity of the AE monitoring apparatus should be adjusted so that arc noise is below the trigger threshold. This sensitivity is the maximum usable AE sensitivity for weld monitoring and varies with different welding methods. Table 1 indicates overall gain for a particular system monitoring welding methods and using typical commercial piezoelectric transducers. This table is for general guideline purposes and not for direct reference.

7.3 *Single-Channel AE Instrumentation* employing a single sensor may provide information on the presence of discontinuities in a weld. For low-heat input welds, where the delay time between fusion and AE activity is short, discontinuities may also be located in the weld by noting the presence of unusual AE activity and recording the position of the welding head when such activity occurs. As the weld heat input increases, the delay time between fusion and AE activity usually increases, thus making use of multichannel arrival time interval measurements necessary for AE source location.

7.4 The AE apparatus should be capable of providing output signals that are proportional to overall acoustic activity (such as RMS or Average Signal Level, ASL) and acoustic emission energy or count rate. In addition, AE counts, energy or peak amplitude for each AE event plotted versus time is useful for AE monitoring of welds. The latter are particularly useful for acoustically active weld processes such as submerged-arc welding where the presence of solid flux cracking contributes greatly to the AE activity. Experience has shown that for these types of welds, the AE activity from flaws and from normal slag bead cracking may have similar peak amplitudes and energies. To prevent false alarms from acceptable slag bead activity, gated rate monitors can sometimes be used to identify flaw activity which generally consists of groups of AE events occurring at much higher rates than the rate of slag bead events.

8. Examination Procedures

8.1 Acoustic emission data may be accumulated during the welding process. Due to the delay between weld fusion (solidification) and AE activity, monitoring must continue for a time period following welding to acquire all significant AE data. The AE monitoring time after welding increases with increasing weld heat input, ranging from 10 seconds for manual gas tungsten (approximately 100 A) to more than 2 minutes for submerged arc welding (600 to 800 A). The desirable time should be established during developmental monitoring of trial welds.

8.2 For AE systems with gain controls, the gain-setting procedure should be reapplied at the completion of a weld. For heavy section welds that may take many days to complete, the gain-setting procedure should be reapplied at least once during every work shift (for example, 8 hours). All changes in system gain or source location accuracy should be recorded and the system readjusted as necessary.

8.3 Observable conditions that occur in conjunction with unusual AE activity should be recorded to aid in later interpretation of the data. This would include cleanup or chipping and grinding by the welder, for example.

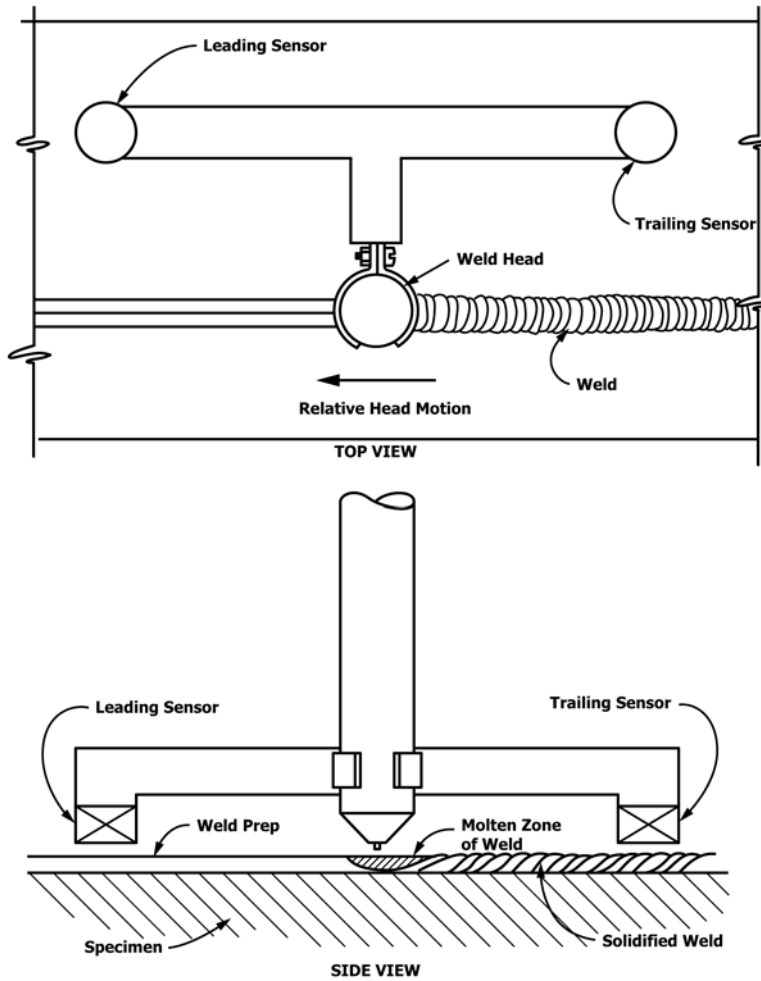


FIG. 4 Moving Sensor Configuration with Sensor Position Fixed Relative to Weld Head

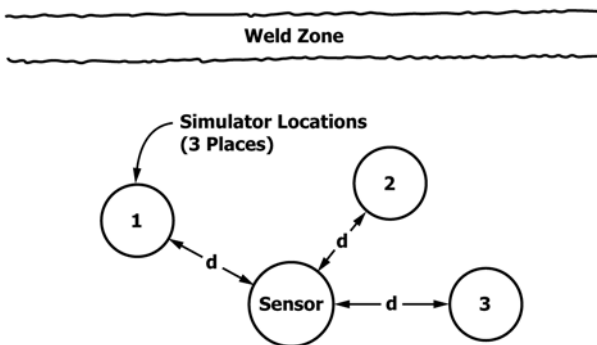


FIG. 5 AE Simulator Positions During Sensor Calibration

TABLE 1 Gain For AE System Utilizing Typical Commercially Available Piezoelectric Sensors Monitoring Typical Weld Methods

Weld Method	AE System Gain Range, dB
Submerged arc (single or tandem wire 800 to 1000 A)	35 to 45
Submerged arc (single wire 400 to 500 A)	45 to 55
Submerged arc (single wire 200 to 400 A)	55 to 65
Gas shielded metal arc (MIG or short arc 150 to 400 A)	50 to 70
Gas shielded tungsten arc (TIG 75 to 250 A)	60 to 80

9.1.4 Sensor specifications, including size, sensitivity, frequency response, method of attachment, type of couplant, and type and length of connecting cables,

9.1.5 Sensor location(s),

9.1.6 Schedule, procedure, and results of all AE system verifications, and

9.1.7 Permanent record of AE indications as defined in Section 9 .

10. Interpretation of Results

10.1 When repairs are made during welding, records of locations are not required. If repairs are made after welding, summarize all results on an appropriate layout map of the weld, or in tabular form, for ready reference and interpretation.

9. Examination Records

9.1 The examination records should contain the following information:

9.1.1 AE system verification data and instrument adjustments (including equipment description and performance data),

9.1.2 Monitoring procedure developed on trial welds,

9.1.3 Material and physical characteristics of the structure,



10.2 In general, acoustic emission weld data must be evaluated against a baseline obtained from known acceptable welds of a given type using the specific AE system and from the AE signals from known defects in the same weld type. Significant weld discontinuities may be characterized by increased AE event count, increased rate of AE events, increased AE intensity, or peak amplitude.

10.3 Based on the AE monitoring results, additional NDT examinations (for example, visual, ultrasonic examination, radiography, or other) should be performed, if necessary or warranted.

11. Report

11.1 If a report is required, it should contain the examination records and interpretation of results.

12. Keywords

12.1 continuous welding; fusion solidification; heat-affected zone; high-temperature sensors; in-process defect location; thermal stress; wave guides

SUMMARY OF CHANGES

Committee E07 has identified the location of selected changes to this standard since the last issue (E749 - 12) that may impact the use of this standard. (June 1, 2017)

(1) Added ISO 9712 to section 2.

(2) Added ISO 9712 to subsection 5.2.1.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>