



Standard Specification for Glass Fiber Reinforced Polyethylene (PE-GF) Spiral Wound Large Diameter Pipe¹

This standard is issued under the fixed designation F2720/F2720M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope*

1.1 This specification covers requirements and test methods for materials, dimensions, workmanship, joining systems, and marking for large diameter, 12 in. [300 mm] and larger, inside diameter controlled glass fiber reinforced polyethylene (PE-GF) spiral wound pipe with electrofusion joints. The piping is intended for new construction and renewal of existing piping systems used for the transport of water, slurries, municipal sewage, domestic sewage, effluents, etc., in pressure systems.

NOTE 1—Pipe produced to this specification should be installed in accordance with Practice D2774 or F1668, where applicable, and with the manufacturer's recommendations.

1.2 The values stated in either inch-pound units or SI units are to be regarded separately as standard. Within the text the SI units are shown in brackets. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.3 All pipes produced under this specification are pressure-rated.

1.4 This specification includes criteria for choice of raw material and test methods for evaluation of raw material, together with performance requirements and test methods for determining conformance with the requirements.

1.5 In referee decisions, the SI units shall be used for metric-sized pipe and inch-pound units for pipe sized per ANSI (ANSI B 36.10).

1.6 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:²

- D618 Practice for Conditioning Plastics for Testing
- D638 Test Method for Tensile Properties of Plastics
- D790 Test Methods for Flexural Properties of Unreinforced and Reinforced Plastics and Electrical Insulating Materials
- D792 Test Methods for Density and Specific Gravity (Relative Density) of Plastics by Displacement
- D1505 Test Method for Density of Plastics by the Density-Gradient Technique
- D1598 Test Method for Time-to-Failure of Plastic Pipe Under Constant Internal Pressure
- D1600 Terminology for Abbreviated Terms Relating to Plastics
- D2122 Test Method for Determining Dimensions of Thermoplastic Pipe and Fittings
- D2657 Practice for Heat Fusion Joining of Polyolefin Pipe and Fittings
- D2774 Practice for Underground Installation of Thermoplastic Pressure Piping
- D2837 Test Method for Obtaining Hydrostatic Design Basis for Thermoplastic Pipe Materials or Pressure Design Basis for Thermoplastic Pipe Products
- D3350 Specification for Polyethylene Plastics Pipe and Fittings Materials
- D3895 Test Method for Oxidative-Induction Time of Polyolefins by Differential Scanning Calorimetry
- F412 Terminology Relating to Plastic Piping Systems
- F1290 Practice for Electrofusion Joining Polyolefin Pipe and Fittings
- F1668 Guide for Construction Procedures for Buried Plastic Pipe

2.2 ANSI Standard:

- B36.10 Standard Dimensions of Steel Pipe (IPS)³

¹ This specification is under the jurisdiction of ASTM Committee F17 on Plastic Piping Systems and is the direct responsibility of Subcommittee F17.11 on Composite.

Current edition approved Dec. 1, 2009. Published March 2010. Originally approved in 2008. Last previous edition approved in 2008 as F2720/F2720M-08. DOI:10.1520/F2720_F2720M-09.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, <http://www.ansi.org>.

TABLE 1 Physical Properties of PE-GF Material Tested as Pipe

Property	Test Method[s]	Units	Minimum Value
Density	ASTM D792 or D1505	g/cm ³	1.04
Oxidation Induction Time @ 412°F [200°C]	ASTM D3895	minutes	20
Tensile strength @ yield (longitudinal direction)	ASTM D638	kpsi [MPa]	5.075 [35.0]
Tensile Elastic Modulus	ASTM D638	kpsi [N/mm ²]	333.5 [2300]
Flexural Elastic Modulus	ASTM D790	kpsi [MPa]	372 [2566]
Resistance to Notch Test	ISO 13479	hours	2500
Hydrostatic Design Basis for water at 73°F [23°C]	ASTM D2837	psi [MPa]	2500 [17.22]

TABLE 2 Standard Pressure Ratings

SIDR	11	13.5	15	17	19	21	24	27	31	35	39	44	49	55	63	70
Design Factor	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5
HDB, psi	3200	3200	3200	3200	3200	3200	3200	3200	3200	3200	3200	3200	3200	3200	3200	3200
P, psi	267	221	201	180	160	143	127	113	101	90	80	71	64	57	51	45
P, kPa	1838	1521	1389	1238	1103	983	876	781	696	621	553	493	439	391	349	311
SIDR	11	13.5	15	17	19	21	24	27	31	35	39	44	49	55	63	70
Design Factor	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5	0.5
HDB, psi	2500	2500	2500	2500	2500	2500	2500	2500	2500	2500	2500	2500	2500	2500	2500	2500
P, psi	208	172	157	140	125	111	99	88	79	70	63	56	50	44	40	35
P, kPa	1436	1188	1085	967	862	768	685	610	544	485	432	385	343	306	272	243

2.3 ISO Standard:

ISO 13479 Polyolefin Pipes for the Conveyance of Fluids—Determination of Resistance to Crack Propagation—Test Method for Slow Crack Growth on Notched Pipes (Notch Test)⁴

2.4 NSF/ANSI Standards:

Standard No. 4 for Plastic Piping Components and Related Materials⁵

Standard No. 61 for Drinking Water Systems Components—Health Effects⁵

3. Terminology

3.1 Definitions—Definitions are in accordance with Terminology **F412** and abbreviations are in accordance with Terminology **D1600**, unless otherwise specified. The abbreviation for polyethylene is PE.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 glass fiber reinforced polyethylene (PE-GF)—short glass fiber reinforced polyethylene compound.

3.2.2 relation between standard dimension ratio, hydrostatic design stress, and pressure rating:—

$$P = \frac{2S}{(Di/t) + 1} \quad (1)$$

where:

S = hydrostatic design stress (HDS), psi [or kPa or MPa],
 P = pressure rating, psi [or kPa or MPa],
 Di = average inside diameter, in. [or mm],
 t = minimum wall thickness, in. [or mm], and
 Di/t = standard dimension ratio or standard inside diameter dimension ratio (SIDR).

⁴ Available from International Organization for Standardization (ISO), 1, ch. de la Voie-Creuse, Case postale 56, CH-1211, Geneva 20, Switzerland, <http://www.iso.ch>.

⁵ Available from NSF International, P.O. Box 130140, 789 N. Dixboro Rd., Ann Arbor, MI 48113-0140, <http://www.nsf.org>.

3.2.3 relationship between hydrostatic design basis [HDB] and hydrostatic design stress (HDS)—the hydrostatic design stress, S , is determined by multiplying the hydrostatic design basis (HDB) by the design factor, n . The design factor, n , has a value less than 1.0.

3.2.3.1 Discussion—The hydrostatic pressure rating of pipes described in this specification is based on the use of a (service) design factor of 0.5.

4. Materials

4.1 General—The polyethylene, reinforcements, colorants, and other additives, when combined as a composite structure, shall produce a pipe that shall meet the performance requirements of this specification.

4.2 Glass Fiber Reinforced Polyethylene (PE-GF) Material—Pipe shall be made of PE-GF plastic compound meeting the requirements shown in **Table 1**. The PE-GF pipe, as manufactured, shall have a minimum hydrostatic design basis (HDB) of 2500 psi [17.2 MPa] for water at 73.4°F [23°C] determined using Test Method **D2837**. Pressure ratings are shown in **Table 2**. Ambient and elevated temperature sustained pressure testing requirements are shown in **Table 5**.

4.3 Polyethylene (PE)—The polyethylene base compound prior to the incorporation of the glass fibers shall meet the minimum property requirements of either cell class 333444 or 444454 as described in Specification **D3350**. The inner and external un-reinforced polyethylene layers shall be either black or colored and shall be made of the same polyethylene compound that is used to make the PE-GF compound.

4.4 Glass Fibers—Short glass fibers.

4.5 Color and Ultraviolet (UV) Stabilization—The pipe shall be black or blue or black with blue stripes. The external and internal colored polyethylene layers shall be made of un-reinforced polyethylene compounds meeting the requirements of Specification **D3350** Code C or Code E. Code C polyethylene compounds shall have between 2.0 and 3.0

TABLE 3
Table 3A: Inch Based PE-GF Pipe Dimensions and Out-of-Roundness Allowance

Nominal Pipe Size in. [mm]	Inside Diameter, minimum in. [mm]	Inside diameter, maximum in. [mm]	Maximum Out-of-Roundness in. [mm]
18 [457]	17.82 [453]	18.0 [457]	0.18 [5]
24 [610]	23.76 [604]	24.0 [610]	0.24 [6]
30 [762]	29.70 [754]	30.0 [762]	0.30 [8]
36 [914]	35.64 [905]	36.0 [914]	0.36 [9]
42 [1067]	41.58 [1056]	42.0 [1067]	0.42 [11]
48 [1219]	47.52 [1207]	48.0 [1219]	0.48 [12]
54 [1372]	53.46 [1358]	54.0 [1372]	0.54 [14]
60 [1524]	59.40 [1509]	60.0 [1524]	0.60 [15]
72 [1829]	71.28 [1811]	72.0 [1829]	0.72 [18]
84 [2134]	83.16 [2112]	84.0 [2134]	0.84 [21]
96 [2438]	95.04 [2414]	96.0 [2438]	0.96 [24]
108 [2743]	106.92 [2716]	108.0 [2743]	1.08 [27]
120 [3048]	118.80 [3018]	120.0 [3048]	1.20 [30]
145 [3683]	143.55 [3646]	145.0 [3683]	1.45 [37]

Table 3B: Metric Based PE-GF Pipe Dimensions and Out-of-Roundness Allowance

Nominal Pipe Size, in. [mm]	Inside Diameter, minimum in. [mm]	Inside Diameter, maximum in. [mm]	Maximum Out-of-Roundness in. [mm]
12 [300]	11.81 [300]	12.13 [308]	0.39 [10]
16 [400]	15.75 [400]	16.06 [408]	0.55 [14]
20 [500]	19.69 [500]	20.00 [508]	0.67 [17]
24 [600]	23.62 [600]	23.98 [609]	0.83 [21]
28 [700]	27.56 [700]	27.95 [710]	0.94 [24]
32 [800]	31.50 [800]	31.97 [812]	1.10 [28]
36 [900]	35.43 [900]	35.94 [913]	1.22 [31]
40 [1000]	39.37 [1000]	39.96 [1015]	1.38 [35]
44 [1100]	43.31 [1100]	43.90 [1115]	1.50 [38]
48 [1200]	47.24 [1200]	47.95 [1218]	1.65 [42]
52 [1300]	51.18 [1300]	51.89 [1318]	1.77 [45]
56 [1400]	55.12 [1400]	55.94 [1421]	1.93 [49]
64 [1600]	62.99 [1600]	63.94 [1624]	2.20 [56]
72 [1800]	70.87 [1800]	71.93 [1827]	2.48 [63]
80 [2000]	78.74 [2000]	79.92 [2030]	2.76 [70]
88 [2200]	86.61 [2200]	87.91 [2233]	3.03 [77]
96 [2400]	94.49 [2400]	95.91 [2436]	3.31 [84]
104 [2600]	102.36 [2600]	103.90 [2639]	3.58 [91]
112 [2800]	110.24 [2800]	111.89 [2842]	3.86 [98]
120 [3000]	118.11 [3000]	119.49 [3035]	4.13 [105]
128 [3200]	125.98 [3200]	127.87 [3248]	4.41 [112]
136 [3400]	133.86 [3400]	135.87 [3451]	4.69 [119]
144 [3600]	141.73 [3600]	143.86 [3654]	4.96 [126]
152 [3800]	149.61 [3800]	151.85 [3857]	5.24 [133]
160 [4000]	157.48 [4000]	159.84 [4060]	5.51 [140]

percent carbon black. Code E polyethylene compounds shall be colored and protected from Ultraviolet (UV) degradation with UV stabilizers.

4.6 Rework Material—Clean rework material generated from the manufacturer’s own pipe production shall be allowed up to a maximum of 10 % by weight in the PE-GF compound. The PE-GF pipe produced shall meet all the requirements of this specification.

5. Classification and Uses

5.1 Uses—The requirements of this specification are intended to provide pipe suitable for underground or above ground pressure applications as well as gravity and low pressure drainage of sewer and surface water.

5.2 Classifications—This specification covers PE-GF pressure pipe products made in standard inside diameter ratios (SIDR) from 11 to 70. Standard pressure ratings for the various SIDR pipes are shown in [Table 2](#).

6. Joining Systems

6.1 Electrofusion Joint:

6.1.1 The joint shall consist of an integral electrofusion device built into the inside of the bell and a plain spigot, which come together to form an electrofusion joint with the proper application of electrical current for an appropriate time period. The seal is made by electrofusion joining through an integral electrofusion device built into the belled end of the pipe. The spigot is inserted into the socket (or bell) and current applied to the contacts.

6.2 Electrofusion Coupling—The seal is made by electrofusion joining through a separate electrofusion coupling or fitting. The electrofusion fitting may be an enlarged OD coupler, a reduced ID coupler, or an equal OD/ID internal coupler.

6.2.1 The assembly of the electrofusion joint shall follow the general requirements of Practice [F1290](#) and with the manufacturer’s recommendations.



TABLE 4

Table 4A: Inch Based PE-GF Minimum and Maximum Wall Thickness by SDR

Nominal Pipe Size, in. [mm]	SIDR 11		SIDR 13.5		SIDR 15		SIDR 17	
	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]
18 [457]	1.62 [41]	1.88 [48]	1.32 [34]	1.53 [39]	1.19 [30]	1.38 [35]	1.05 [27]	1.22 [31]
24 [610]	2.16 [55]	2.51 [64]	1.76 [45]	2.04 [52]	1.58 [40]	1.84 [47]	1.40 [36]	1.62 [36]
30 [762]	2.70 [69]	3.14 [80]	2.20 [56]	2.56 [65]	1.98 [50]	2.30 [58]	1.75 [44]	2.03 [52]
36 [914]	3.24 [82]	3.76 [96]	2.64 [67]	3.07 [78]	2.38 [60]	2.76 [70]	2.10 [53]	2.44 [62]
42 [1067]	3.78 [96]	4.39 [112]	3.08 [78]	3.58 [92]	2.77 [70]	3.22 [82]	2.45 [62]	2.84 [72]
48 [1219]	4.32 [110]	5.02 [127]	3.52 [89]	4.09 [104]	3.17 [80]	3.68 [93]	2.80 [71]	3.25 [82]
54 [1372]	4.86 [123]	5.65 [143]	3.96 [101]	4.60 [117]	3.56 [91]	4.14 [105]	3.14 [80]	3.65 [93]
60 [1524]	5.40 [137]	6.27 [159]	4.40 [112]	5.11 [130]	3.96 [101]	4.60 [117]	3.49 [89]	4.06 [103]
72 [1829]	6.48 [165]	7.53 [191]	5.28 [134]	6.13 [156]	4.75 [121]	5.52 [140]	4.19 [107]	4.87 [124]
84 [2134]	7.56 [192]	8.78 [223]	6.16 [156]	7.16 [182]	5.54 [141]	6.44 [164]	4.89 [124]	5.68 [144]
96 [2438]	8.64 [219]	10.04 [255]	7.04 [179]	8.18 [208]	6.34 [161]	7.36 [187]	5.59 [142]	6.49 [165]
108 [2743]	9.72 [247]	11.29 [287]	7.92 [201]	9.20 [234]	7.13 [181]	8.28 [210]	6.29 [160]	7.31 [186]
120 [3048]	10.80 [274]	12.55 [319]	8.80 [224]	10.22 [260]	7.92 [201]	9.20 [234]	6.99 [178]	8.12 [206]
145 [3683]	13.05 [331]	15.16 [385]	10.63 [270]	12.35 [314]	9.57 [243]	11.12 [282]	8.44 [214]	9.81 [249]

Table 4B: Inch Based PE-GF Minimum and Maximum Wall Thickness by SDR

Nominal Pipe Size, in. [mm]	SIDR 19		SIDR 21		SIDR 24		SIDR 27	
	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]
18 [457]	0.94 [24]	1.09 [28]	0.85 [22]	0.99 [25]	0.74 [19]	0.86 [22]	0.66 [17]	0.77 [19]
24 [610]	1.25 [32]	1.45 [37]	1.13 [29]	1.31 [33]	0.99 [25]	1.15 [29]	0.88 [22]	1.02 [26]
30 [762]	1.56 [40]	1.82 [46]	1.41 [36]	1.64 [42]	1.24 [31]	1.44 [37]	1.10 [28]	1.28 [32]
36 [914]	1.88 [48]	2.18 [55]	1.70 [43]	1.97 [50]	1.49 [38]	1.73 [44]	1.32 [34]	1.53 [39]
42 [1067]	2.19 [56]	2.54 [65]	1.98 [50]	2.30 [58]	1.73 [44]	2.01 [51]	1.54 [39]	1.79 [45]
48 [1219]	2.50 [64]	2.91 [74]	2.26 [57]	2.63 [67]	1.98 [50]	2.30 [58]	1.76 [45]	2.04 [52]
54 [1372]	2.81 [71]	3.27 [83]	2.55 [65]	2.96 [75]	2.23 [57]	2.59 [66]	1.98 [50]	2.30 [58]
60 [1524]	3.13 [79]	3.63 [92]	2.83 [72]	3.29 [83]	2.48 [63]	2.88 [73]	2.20 [56]	2.56 [65]
72 [1829]	3.75 [95]	4.36 [111]	3.39 [86]	3.94 [100]	2.97 [75]	3.45 [88]	2.64 [67]	3.07 [78]
84 [2134]	4.38 [111]	5.08 [129]	3.96 [101]	4.60 [117]	3.47 [88]	4.03 [102]	3.08 [78]	3.58 [91]
96 [2438]	5.00 [127]	5.81 [148]	4.53 [115]	5.26 [134]	3.96 [101]	4.60 [117]	3.52 [89]	4.09 [104]
108 [2743]	5.63 [143]	6.54 [166]	5.09 [129]	5.91 [150]	4.46 [113]	5.18 [131]	3.96 [101]	4.60 [117]
120 [3048]	6.25 [159]	7.26 [184]	5.66 [144]	6.57 [167]	4.95 [126]	5.75 [146]	4.40 [112]	5.11 [130]
145 [3683]	7.56 [192]	8.78 [223]	6.84 [174]	7.94 [202]	5.98 [152]	6.95 [176]	5.32 [135]	6.18 [157]

Table 4C: Inch Based PE-GF Minimum and Maximum Wall Thickness by SDR

Nominal Pipe Size, in. [mm]	SIDR 31		SIDR 35		SIDR 39		SIDR 44	
	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]
18 [457]	0.57 [15]	0.67 [17]	0.51 [13]	0.59 [15]	0.46 [12]	0.53 [13]	0.41 [10]	0.47 [12]
24 [610]	0.77 [19]	0.89 [23]	0.68 [17]	0.79 [20]	0.61 [15]	0.71 [18]	0.54 [14]	0.63 [16]
30 [762]	0.96 [24]	1.11 [28]	0.85 [22]	0.99 [25]	0.76 [19]	0.88 [22]	0.68 [17]	0.78 [20]
36 [914]	1.15 [29]	1.34 [34]	1.02 [26]	1.18 [30]	0.91 [23]	1.06 [27]	0.81 [21]	0.94 [24]
42 [1067]	1.34 [34]	1.56 [40]	1.19 [30]	1.38 [35]	1.07 [27]	1.24 [31]	0.95 [24]	1.10 [28]
48 [1219]	1.53 [39]	1.78 [45]	1.36 [34]	1.58 [40]	1.22 [31]	1.42 [36]	1.08 [27]	1.25 [32]
54 [1372]	1.72 [44]	2.00 [51]	1.53 [39]	1.77 [45]	1.37 [35]	1.59 [40]	1.22 [31]	1.41 [36]
60 [1524]	1.92 [49]	2.23 [57]	1.70 [43]	1.97 [50]	1.52 [39]	1.77 [45]	1.35 [34]	1.57 [40]
72 [1829]	2.30 [58]	2.67 [68]	2.37 [60]	2.04 [52]	1.83 [46]	2.12 [54]	1.62 [41]	1.88 [48]
84 [2134]	2.68 [68]	3.12 [79]	2.38 [60]	2.76 [70]	2.13 [54]	2.48 [63]	1.89 [48]	2.20 [56]
96 [2438]	3.07 [78]	3.56 [90]	2.72 [69]	3.15 [80]	2.44 [62]	2.83 [72]	2.16 [55]	2.51 [64]
108 [2743]	3.45 [88]	4.01 [102]	3.05 [78]	3.55 [90]	2.74 [70]	3.18 [81]	2.43 [62]	2.82 [72]
120 [3048]	3.83 [97]	4.45 [113]	3.39 [86]	3.94 [100]	3.05 [77]	3.54 [90]	2.70 [69]	3.14 [80]
145 [3683]	4.63 [118]	5.38 [137]	4.10 [104]	4.76 [121]	3.68 [93]	4.28 [109]	3.26 [83]	3.79 [96]

Table 4D: Inch Based PE-GF Minimum and Maximum Wall Thickness by SDR

Nominal Pipe Size, in. [mm]	SIDR 49		SIDR 55		SIDR 63		SIDR 70	
	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]	Min. Wall in. [mm]	Max. Wall in. [mm]
18 [457]	0.36 [9]	0.42 [11]	0.32 [8]	0.38 [10]	0.28 [7]	0.33 [8]	0.25 [6]	0.30 [8]
24 [610]	0.48 [12]	0.56 [14]	0.43 [11]	0.50 [13]	0.38 [10]	0.44 [11]	0.34 [9]	0.39 [10]
30 [762]	0.61 [15]	0.70 [18]	0.54 [14]	0.63 [16]	0.47 [12]	0.55 [14]	0.42 [11]	0.49 [13]
36 [914]	0.73 [18]	0.84 [21]	0.65 [16]	0.75 [19]	0.57 [14]	0.66 [17]	0.51 [13]	0.59 [15]
42 [1067]	0.85 [22]	0.99 [25]	0.76 [19]	0.88 [22]	0.66 [17]	0.77 [19]	0.59 [15]	0.69 [18]
48 [1219]	0.97 [25]	1.13 [29]	0.86 [22]	1.00 [25]	0.75 [19]	0.88 [22]	0.68 [17]	0.79 [20]
54 [1372]	1.09 [28]	1.27 [32]	0.97 [25]	1.13 [29]	0.85 [22]	0.99 [25]	0.76 [19]	0.89 [23]
60 [1524]	1.21 [31]	1.41 [36]	1.08 [27]	1.25 [32]	0.94 [24]	1.10 [28]	0.85 [22]	0.99 [25]
72 [1829]	1.45 [37]	1.69 [43]	1.30 [33]	1.51 [38]	1.13 [29]	1.31 [33]	1.02 [26]	1.18 [30]
84 [2134]	1.70 [43]	1.97 [50]	1.51 [38]	1.76 [45]	1.32 [34]	1.53 [39]	1.19 [30]	1.38 [35]
96 [2438]	1.94 [49]	2.25 [57]	1.73 [44]	2.01 [51]	1.51 [31]	1.75 [45]	1.36 [34]	1.58 [40]
108 [2743]	2.18 [55]	2.53 [64]	1.94 [49]	2.26 [57]	1.70 [43]	1.97 [50]	1.53 [39]	1.77 [45]
120 [3048]	2.42 [62]	2.82 [72]	2.16 [55]	2.51 [64]	1.89 [48]	2.19 [56]	1.70 [43]	1.97 [50]
145 [3683]	2.93 [74]	3.40 [86]	2.61 [66]	3.03 [77]	2.28 [58]	2.65 [67]	2.05 [52]	2.38 [61]

Table 4E: Metric Based PE-GF Minimum and Maximum Wall Thickness by SDR

Nominal Pipe Size, in. [mm]	SIDR 11		SIDR 13.5		SIDR 15		SIDR 17	
	Min wall in. [mm]	Max wall in., [mm]	Min wall in., [mm]	Max wall in., [mm]	Min wall in., [mm]	Max wall in., [mm]	Min wall in., [mm]	Max wall in., [mm]



TABLE 4 Continued

12 [300]	1.07 [27.2]	1.26 [32]	0.88 [22.4]	0.98 [25]	0.80 [20.2]	0.88 [22.4]	0.70 [17.8]	0.78 [19.7]
16 [400]	1.43 [36.4]	1.65 [42]	1.17 [29.7]	1.30 [33]	1.06 [26.9]	1.17 [29.7]	0.94 [23.8]	1.04 [26.3]
20 [500]	1.79 [45.4]	2.09 [53]	1.46 [37.1]	1.63 [41.5]	1.32 [33.6]	1.46 [37.1]	1.17 [29.7]	1.29 [32.8]
24 [600]	2.14 [54.4]	2.48 [63]	1.75 [44.5]	1.97 [50]	1.59 [40.3]	1.75 [44.5]	1.41 [35.7]	1.55 [39.4]
28 [700]	2.50 [63.5]	2.91 [74]	2.04 [51.8]	2.28 [58]	1.85 [47.0]	2.04 [51.8]	1.64 [41.6]	1.81 [45.9]
32 [800]	2.87 [73]	3.31 [84]	2.33 [59.2]	2.60 [66]	2.11 [53.7]	2.33 [59.2]	1.87 [47.5]	2.06 [52.4]
36 [900]	3.23 [82]	3.74 [95]	2.63 [66.7]	2.95 [75]	2.38 [60.5]	2.63 [66.7]	2.11 [53.5]	2.32 [59.0]
40 [1000]	3.58 [91]	4.13 [105]	2.92 [74.1]	3.27 [83]	2.65 [67.2]	2.92 [74.1]	2.34 [59.4]	2.58 [65.5]
44 [1100]	3.94 [100]	4.57 [116]	3.22 [81.7]	3.58 [91]	2.91 [74.0]	3.22 [81.7]	2.57 [65.3]	2.84 [72.1]
48 [1200]	4.29 [109]	4.96 [126]	3.50 [88.8]	3.90 [99]	3.17 [80.6]	3.50 [88.8]	2.81 [71.3]	3.09 [78.6]
52 [1300]	4.65 [118]	5.39 [137]	3.78 [96.0]	4.25 [108]	3.42 [87.0]	3.78 [96.0]	3.04 [77.2]	3.35 [85.2]
56 [1400]	5.00 [127]	5.83 [148]	4.09 [104]	4.61 [117]	3.70 [94.0]	4.08 [103.6]	3.28 [83.2]	3.61 [91.7]
64 [1600]	5.71 [145]	6.65 [169]	4.66 [118.4]	5.24 [133]	4.23 [107.5]	4.66 [118.4]	3.74 [95.1]	4.13 [104.8]
72 [1800]	6.42 [163]	7.48 [190]	5.24 [133.1]	5.91 [150]	4.76 [120.9]	5.24 [133.1]	4.21 [107.0]	4.64 [117.9]
80 [2000]	7.17 [182]	8.31 [211]	5.82 [147.9]	6.54 [166]	5.29 [134.3]	5.82 [147.9]	4.68 [118.9]	5.15 [130.9]
88 [2200]	7.87 [200]	9.13 [232]	6.41 [162.7]	7.20 [183]	5.82 [147.8]	6.41 [162.7]	5.15 [130.8]	5.67 [144.0]
96 [2400]	8.58 [218]	9.96 [253]	6.99 [177.5]	7.87 [200]	6.35 [161.2]	6.99 [177.5]	5.61 [142.6]	6.18 [157.0]
104 [2600]	9.29 [236]	10.79 [274]	7.57 [192.3]	8.50 [216]	6.88 [174.7]	7.57 [192.3]	6.08 [154.5]	6.70 [170.1]
112 [2800]	10.04 [255]	11.61 [295]	8.15 [207.1]	9.17 [233]	7.41 [188.1]	8.15 [207.1]	6.55 [166.4]	7.21 [183.2]
120 [3000]	10.75 [273]	12.44 [316]	8.73 [221.8]	9.84 [250]	7.93 [201.5]	8.73 [221.8]	7.02 [178.3]	7.73 [196.3]
128 [3200]	11.46 [291]	13.31 [338]	9.31 [236.6]	10.51 [267]	8.46 [215.0]	9.31 [236.8]	7.49 [190.2]	8.24 [209.4]
136 [3400]	12.20 [310]	14.09 [358]	9.90 [251.4]	11.18 [284]	8.99 [228.4]	9.90 [251.4]	7.96 [202.1]	8.76 [222.5]
144 [3600]	12.91 [328]	14.88 [378]	10.48 [266]	11.85 [301]	9.52 [241.8]	10.48 [266.1]	8.43 [214.0]	9.27 [235.5]
152 [3800]	13.54 [344]	15.67 [398]	11.06 [281]	12.48 [317]	10.05 [255.3]	11.06 [281.0]	8.89 [225.8]	9.78 [248.5]
160 [4000]	14.25 [362]	16.54 [420]	11.64 [295.7]	13.15 [334]	10.58 [268.7]	11.64 [295.7]	9.36 [237.7]	10.30 [261.6]

Table 4F: Metric Based PE-GF Minimum and Maximum Wall Thickness by SDR

Nominal Pipe Size, in. [mm]	SIDR 19		SIDR 21		SIDR 24		SIDR 27	
	Min wall in. [mm]	Max wall in. [mm]	Min wall in. [mm]	Max wall in. [mm]	Min wall in. [mm]	Max wall in. [mm]	Min wall in. [mm]	Max wall in. [mm]
12 [300]	0.62 [15.8]	0.69 [17.5]	0.55 [14.0]	0.61 [15.5]	0.49 [12.4]	0.54 [13.8]	0.43 [11.0]	0.48 [12.2]
16 [400]	0.83 [21.1]	0.92 [23.4]	0.74 [18.7]	0.81 [20.7]	0.65 [16.5]	0.72 [18.3]	0.58 [14.7]	0.64 [16.3]
20 [500]	1.04 [26.3]	1.15 [29.1]	0.92 [23.3]	1.02 [25.8]	0.81 [20.7]	0.90 [22.9]	0.72 [18.3]	0.80 [20.3]
24 [600]	1.24 [31.6]	1.37 [34.9]	1.10 [28.0]	1.22 [30.9]	0.98 [24.8]	1.08 [27.4]	0.87 [22.0]	0.96 [24.3]
28 [700]	1.45 [36.8]	1.60 [40.6]	1.28 [32.6]	1.42 [36.0]	1.14 [29.0]	1.26 [32.0]	1.01 [25.7]	1.12 [28.4]
32 [800]	1.66 [42.1]	1.83 [46.5]	1.47 [37.3]	1.62 [41.2]	1.30 [33.1]	1.44 [36.6]	1.16 [29.4]	1.28 [32.5]
36 [900]	1.87 [47.4]	2.06 [52.3]	1.65 [42.0]	1.82 [46.3]	1.46 [37.2]	1.62 [41.1]	1.30 [33.0]	1.43 [36.4]
40 [1000]	2.07 [52.6]	2.28 [58.0]	1.83 [46.6]	2.02 [51.4]	1.63 [41.4]	1.80 [45.7]	1.44 [36.7]	1.59 [40.5]
44 [1100]	2.28 [58.0]	2.52 [64.0]	2.02 [51.2]	2.22 [56.4]	1.79 [45.4]	1.98 [50.2]	1.59 [40.4]	1.76 [44.6]
48 [1200]	2.49 [63.2]	2.74 [69.7]	2.20 [56.0]	2.43 [61.7]	1.95 [49.6]	2.15 [54.7]	1.73 [44.0]	1.91 [48.5]
52 [1300]	2.70 [68.6]	2.97 [75.4]	2.39 [60.8]	2.64 [67.0]	2.12 [57.9]	2.34 [59.4]	1.88 [47.8]	2.07 [52.6]
56 [1400]	2.90 [73.7]	3.20 [81.2]	2.57 [65.3]	2.83 [72.0]	2.28 [66.2]	2.51 [63.8]	2.02 [51.4]	2.23 [56.7]
64 [1600]	3.31 [84.2]	3.65 [92.8]	2.94 [74.6]	3.24 [82.2]	2.61 [74.4]	2.87 [73.0]	2.31 [58.7]	2.55 [64.7]
72 [1800]	3.73 [94.7]	4.11 [104.3]	3.31 [84.0]	3.64 [92.5]	2.93 [74.4]	3.23 [82.0]	2.60 [66.1]	2.87 [72.9]
80 [2000]	4.15 [105.3]	4.57 [116.0]	3.67 [93.3]	4.05 [102.8]	3.26 [82.7]	3.59 [91.1]	2.89 [73.4]	3.19 [80.9]
88 [2200]	4.56 [115.8]	5.02 [127.5]	4.04 [102.6]	4.45 [113.0]	3.58 [91.0]	3.94 [100.2]	3.18 [80.7]	3.50 [88.9]
96 [2400]	4.97 [126.3]	5.48 [139.1]	4.41 [111.9]	4.85 [123.2]	3.91 [99.3]	4.31 [109.4]	3.47 [88.1]	3.82 [97.1]
104 [2600]	5.39 [136.8]	5.93 [150.6]	4.78 [121.3]	5.26 [133.6]	4.23 [107.5]	4.66 [118.4]	3.76 [95.4]	4.14 [105.1]
112 [2800]	5.80 [147.4]	6.39 [162.3]	5.14 [130.6]	5.66 [143.8]	4.56 [115.8]	5.02 [127.5]	4.04 [102.7]	4.45 [113.1]
120 [3000]	6.22 [157.9]	6.84 [173.8]	5.51 [139.9]	6.06 [154.0]	4.89 [124.1]	5.38 [136.7]	4.33 [110.1]	4.78 [121.3]
128 [3200]	6.63 [168.4]	7.30 [185.4]	5.88 [149.3]	6.47 [164.4]	5.21 [132.3]	5.74 [145.7]	4.62 [117.4]	5.09 [129.3]
136 [3400]	7.04 [178.9]	7.75 [196.9]	6.24 [158.6]	6.87 [174.6]	5.54 [140.6]	6.09 [154.8]	4.91 [124.8]	5.41 [137.4]
144 [3600]	7.46 [189.5]	8.21 [208.6]	6.61 [167.9]	7.28 [184.8]	5.86 [148.9]	6.45 [163.9]	5.20 [132.1]	5.73 [145.5]
153 [3800]	7.87 [200.0]	8.67 [220.1]	6.98 [177.2]	7.68 [195.1]	6.19 [157.2]	6.81 [173.1]	5.49 [139.4]	6.04 [153.5]
160 [4000]	8.29 [210.5]	9.12 [231.7]	7.35 [186.6]	8.09 [205.4]	6.51 [165.4]	7.17 [182.1]	5.78 [146.8]	6.36 [161.6]

Table 4G: Metric Based PE-GF Minimum and Maximum Wall Thickness by SDR

Nominal Pipe Size, in. [mm]	SIDR 31		SIDR 35		SIDR 39		SIDR 44	
	Min wall in. [mm]	Max wall in. [mm]	Min wall in. [mm]	Max wall in. [mm]	Min wall in. [mm]	Max wall in. [mm]	Min wall in. [mm]	Max wall in. [mm]
12 [300]	0.39 [9.8]	0.43 [10.9]	0.34 [8.7]	0.38 [9.7]	0.30 [7.7]	0.34 [8.6]	0.27 [6.9]	0.30 [7.7]
16 [400]	0.51 [13.0]	0.57 [14.4]	0.46 [11.8]	0.51 [12.9]	0.41 [10.3]	0.45 [11.5]	0.36 [9.1]	0.40 [10.2]
20 [500]	0.64 [16.3]	0.71 [18.1]	0.57 [14.5]	0.63 [16.1]	0.51 [12.9]	0.56 [14.3]	0.45 [11.4]	0.50 [12.7]
24 [600]	0.77 [19.5]	0.85 [21.6]	0.69 [17.4]	0.76 [19.3]	0.61 [15.4]	0.67 [17.1]	0.54 [13.7]	0.60 [15.2]
28 [700]	0.90 [22.8]	0.99 [25.2]	0.80 [20.3]	0.89 [22.5]	0.71 [18.0]	0.78 [19.9]	0.63 [16.0]	0.70 [17.7]
32 [800]	1.03 [26.1]	1.14 [28.9]	0.91 [23.1]	1.01 [25.6]	0.81 [20.6]	0.90 [22.8]	0.72 [18.3]	0.80 [20.3]
36 [900]	1.15 [29.3]	1.28 [32.4]	1.02 [26.0]	1.13 [28.7]	0.91 [23.1]	1.01 [25.6]	0.81 [20.6]	0.90 [22.8]
40 [1000]	1.28 [32.6]	1.42 [36.0]	1.14 [28.9]	1.26 [31.9]	1.01 [25.7]	1.12 [28.4]	0.90 [22.8]	0.99 [25.2]
44 [1100]	1.41 [35.8]	1.56 [39.6]	1.25 [31.8]	1.39 [35.4]	1.11 [28.3]	1.23 [31.3]	0.99 [25.1]	1.09 [27.8]
48 [1200]	1.54 [39.1]	1.70 [43.2]	1.37 [34.7]	1.51 [38.3]	1.21 [30.8]	1.34 [34.0]	1.08 [27.4]	1.19 [30.3]
52 [1300]	1.67 [42.3]	1.84 [46.8]	1.48 [37.6]	1.64 [41.6]	1.31 [33.4]	1.45 [36.9]	1.17 [29.7]	1.29 [32.8]
56 [1400]	1.80 [45.6]	1.98 [50.3]	1.59 [40.5]	1.76 [44.7]	1.42 [36.0]	1.56 [39.7]	1.26 [32.0]	1.39 [35.3]
64 [1600]	2.05 [52.1]	2.26 [57.5]	1.82 [46.3]	2.01 [51.1]	1.62 [41.1]	1.79 [45.4]	1.44 [36.6]	1.59 [40.4]
72 [1800]	2.31 [58.6]	2.54 [64.6]	2.05 [52.1]	2.26 [57.5]	1.82 [46.3]	2.01 [51.1]	1.62 [41.1]	1.79 [45.4]
80 [2000]	2.57 [65.2]	2.83 [71.9]	2.28 [57.9]	2.51 [63.8]	2.02 [51.4]	2.23 [56.7]	1.80 [45.7]	1.98 [50.4]
88 [2200]	2.82 [71.7]	3.11 [79.0]	2.50 [63.6]	2.76 [70.1]	2.22 [56.5]	2.45 [62.3]	1.98 [50.3]	2.19 [55.5]
96 [2400]	3.08 [78.2]	3.39 [86.2]	2.73 [69.4]	3.01 [76.5]	2.43 [61.7]	2.68 [68.0]	2.16 [54.8]	2.38 [60.4]
104 [2600]	3.33 [84.7]	3.67 [93.3]	2.96 [75.2]	3.26 [82.9]	2.63 [66.8]	2.90 [73.6]	2.34 [59.4]	2.58 [65.5]

TABLE 4 *Continued*

112 [2800]	3.59 [91.2]	3.96 [100.5]	3.19 [81.0]	3.51 [89.2]	2.83 [72.0]	3.12 [79.3]	2.52 [64.0]	2.78 [70.5]
120 [3000]	3.85 [97.7]	4.24 [107.6]	3.42 [86.8]	3.76 [95.6]	3.04 [77.1]	3.35 [85.0]	2.70 [68.5]	2.97 [75.5]
126 [3200]	4.10 [104.2]	4.52 [114.8]	3.65 [92.6]	4.02 [102.0]
134 [3400]	4.36 [110.8]	4.80 [122.0]	3.87 [98.4]	4.27 [108.4]	3.54 [90.0]	3.90 [99.1]	3.15 [80.0]	3.47 [88.1]
142 [3600]	4.62 [117.3]	5.09 [129.2]	4.10 [104.1]	4.52 [114.7]
150 [3800]	4.87 [123.8]	5.37 [136.3]	4.33 [109.9]	4.76 [121.0]
158 [4000]	5.13 [130.3]	5.65 [143.5]	4.56 [115.7]	5.02 [127.4]	4.05 [102.8]	4.46 [113.2]	3.60 [91.4]	3.96 [100.7]

Table 4H: Metric Based PE-GF Minimum and Maximum Wall Thickness by SIDR

Nominal Pipe Size, in. [mm]	SIDR 49		SIDR 55		SIDR 63		SIDR 70	
	Min wall in. [mm]	Max wall in. [mm]	Min wall in. [mm]	Max wall in. [mm]	Min wall in. [mm]	Max wall in. [mm]	Min wall in. [mm]	Max wall in. [mm]
12 [300]	0.24 [6.1]	0.27 [6.9]	0.21 [5.4]	0.24 [6.1]	0.19 [4.8]	0.21 [5.4]	0.17 [4.3]	0.19 [4.9]
16 [400]	0.32 [8.1]	0.36 [9.1]	0.28 [7.2]	0.32 [8.1]	0.25 [6.4]	0.28 [7.2]	0.22 [5.7]	0.25 [6.4]
20 [500]	0.40 [10.2]	0.45 [11.4]	0.35 [9.0]	0.39 [10.0]	0.31 [8.0]	0.35 [8.9]	0.28 [7.1]	0.31 [8.0]
24 [600]	0.48 [12.2]	0.54 [13.6]	0.43 [10.8]	0.47 [12.0]	0.38 [9.6]	0.42 [10.7]	0.34 [8.6]	0.38 [9.6]
28 [700]	0.56 [14.2]	0.62 [15.8]	0.50 [12.6]	0.55 [14.0]	0.44 [11.2]	0.49 [12.5]	0.39 [10.0]	0.44 [11.1]
32 [800]	0.64 [16.2]	0.71 [18.0]	0.57 [14.4]	0.63 [16.0]	0.51 [12.9]	0.56 [14.3]	0.45 [11.4]	0.50 [12.7]
36 [900]	0.72 [18.3]	0.80 [20.3]	0.64 [16.3]	0.71 [18.1]	0.57 [14.5]	0.63 [16.1]	0.51 [12.9]	0.56 [14.3]
40 [1000]	0.80 [20.3]	0.89 [22.5]	0.71 [18.1]	0.79 [20.1]	0.63 [16.1]	0.70 [17.9]	0.56 [14.3]	0.63 [15.9]
44 [1100]	0.88 [22.3]	0.97 [24.7]	0.78 [19.9]	0.87 [22.0]	0.70 [17.7]	0.77 [19.6]	0.62 [15.7]	0.69 [17.4]
48 [1200]	0.96 [24.4]	1.06 [27.0]	0.85 [21.7]	0.94 [24.0]	0.76 [19.3]	0.84 [21.4]	0.68 [17.2]	0.75 [19.1]
52 [1300]	1.04 [26.4]	1.15 [29.2]	0.93 [23.5]	1.02 [26.0]	0.82 [20.9]	0.91 [23.1]	0.73 [18.6]	0.81 [20.6]
56 [1400]	1.12 [28.4]	1.24 [31.4]	1.00 [25.3]	1.10 [28.0]	0.89 [22.5]	0.98 [24.9]	0.79 [20.0]	0.87 [22.1]
64 [1600]	1.28 [32.5]	1.41 [35.9]	1.14 [28.9]	1.26 [31.9]	1.01 [25.7]	1.12 [28.4]	0.90 [22.9]	1.00 [25.3]
72 [1800]	1.44 [36.6]	1.59 [40.4]	1.28 [32.5]	1.41 [35.9]	1.14 [28.9]	1.26 [31.9]	1.01 [25.7]	1.12 [28.4]
80 [2000]	1.60 [40.6]	1.76 [44.8]	1.42 [36.1]	1.57 [39.9]	1.26 [32.1]	1.40 [35.5]	1.13 [28.6]	1.24 [31.6]
88 [2200]	1.76 [44.7]	1.94 [49.3]	1.56 [39.7]	1.72 [43.8]	1.39 [35.3]	1.54 [39.0]	1.24 [31.4]	1.37 [34.7]
96 [2400]	1.92 [48.7]	2.11 [53.7]	1.70 [43.3]	1.88 [47.8]	1.52 [38.6]	1.68 [42.6]	1.35 [34.3]	1.49 [37.9]
104 [2600]	2.08 [52.8]	2.29 [58.2]	1.85 [47.0]	2.04 [51.8]	1.65 [41.8]	1.81 [46.1]	1.46 [37.2]	1.62 [41.1]
112 [2800]	2.24 [56.9]	2.47 [62.7]	1.99 [50.6]	2.20 [55.8]	1.77 [45.0]	1.95 [49.6]	1.57 [40.0]	1.74 [44.2]
120 [3000]	2.40 [60.9]	2.64 [67.1]	2.13 [54.2]	2.35 [59.8]	1.90 [48.2]	2.09 [53.2]	1.69 [42.9]	1.86 [47.3]
134 [3400]	2.80 [71.1]	3.09 [78.4]	2.49 [63.2]	2.74 [69.7]	2.21 [56.2]	2.44 [62.0]	1.97 [50.0]	2.17 [55.1]
158 [4000]	3.20 [81.2]	3.52 [89.5]	2.84 [72.2]	3.13 [79.6]	2.53 [64.3]	2.79 [70.9]	2.25 [57.2]	2.48 [63.1]

TABLE 5 Ambient and Elevated Temperature Sustained Pressure Requirements

PE-GF HDB Classification, psi [MPa]	Test Temperature, °F [°C]	Test Hoop Stress, psi [MPa]	Minimum Time without Failure, h
2500 [17.1]	73 ± 3.6 [23 ± 2]	4200 [29.0]	100
3200 [22.1]	73 ± 3.6 [23 ± 2]	5075 [35.0]	100
2500 [17.1]	176 ± 3.6 [80 ± 2]	1660 [11.5]	165
3200 [22.1]	176 ± 3.6 [80 ± 2]	2175 [15.0]	165
2500 [17.1]	176 ± 3.6 [80 ± 2]	1380 [9.50]	1000
3200 [22.1]	176 ± 3.6 [80 ± 2]	1885 [13.0]	1000

7. Requirements

7.1 Workmanship—The inside and outside surfaces shall be semi-matte or semi-glossy in appearance and be free of chalking, sticky, or tacky material. The pipe walls shall be free of cracks, blisters, foreign inclusions, or other defects that are visible to the naked eye and that may affect the wall integrity.

7.2 Pipe Dimensions:

7.2.1 Diameter—The average inside diameter of the pipe, including the diameter in integral socket or bell sections where present, shall meet the requirements given in [Table 3](#), when measured in accordance with [8.4.1](#).

7.2.2 Pipe Wall Thickness—The minimum wall thickness of the pipe (see [Fig. 1](#)) shall meet the requirements given in [Table 5](#), when measured in accordance with [8.4.2](#).

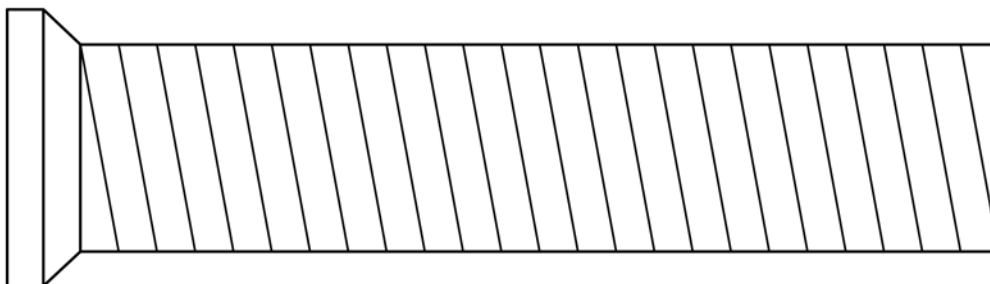


FIG. 1 Typical Construction of Glass Fiber Reinforced PE Spiral Wound Pipe

7.2.3 Laying Length—Standard pipe laying length, measured from the bottom of the bell to the tip of the spigot (see Fig. 1), shall be 19.7 ft [6.0 m] when measured in accordance with Test Method D2122. For pipe with an integral bell, the pipe laying length is measured from the bottom of the bell to the tip of the spigot.

7.3 Ambient and Elevated Temperature Sustained Pressure Test—Test representative PE-GF pipe in accordance with 8.5 at one ambient temperature and stress condition and one elevated temperature and stress condition for the specified minimum time to failure as shown in Table 5.

8. Test Methods

8.1 Conditioning—When conditioning is required for referee tests, condition the specimens in accordance with Procedure A of Practice D618 at $73.4 \pm 3.6^\circ\text{F}$ [$23 \pm 2^\circ\text{C}$] and $50 \pm 5\%$ relative humidity for not less than 40 h prior to test. Conduct tests under the same conditions of temperature and humidity, unless otherwise specified.

8.1.1 Quality Control Testing—Unless otherwise specified, condition specimens for a minimum of 4 h prior to test in air or in water at $73.4 \pm 3.6^\circ\text{F}$ [$23 \pm 2^\circ\text{C}$]. Test the specimens at $73.4 \pm 3.6^\circ\text{F}$ without regard to relative humidity.

8.2 Test Conditions—Conduct tests other than those for routine quality control purposes in the Standard Laboratory Atmosphere of $73.4 \pm 3.6^\circ\text{F}$ [$23 \pm 2^\circ\text{C}$] and $50 \pm 5\%$ relative humidity, unless otherwise specified in the referenced test method or in this specification. In cases of disagreement, retesting shall be conducted with the temperature and relative humidity tolerances limited to 61.8°F [1°C] and 62% respectively.

8.3 Sampling—The selection of samples of the pipe shall be as agreed upon between the purchaser and the seller. In case of no prior agreement, any sample selected by the testing laboratory shall be deemed adequate.

8.4 Dimensions:

8.4.1 Average Inside Diameter—Determine the average inside diameter using a circumferential wrap tape. Make sure to use only a wide-band steel tape. Place it inside and around the pipe making sure that it is at right angles to the pipe axis and is flat against the pipe surface. Observe the diameter, estimating to the nearest 0.005 in. [0.1 mm] or 0.001 in. [0.02 mm], as required. As an alternative method, use an internal micrometer or telescoping gage, accurate to 60.01 in. [60.2 mm]. Take sufficient readings, a minimum of 4, at the same position with respect to the end of the pipe to ensure that the maximum and minimum values have been determined. Calculate the average diameter as the arithmetic mean of diameters measured.

8.4.2 Wall Thickness—Measure the wall thickness in accordance with the requirements of Test Method D2122. Make sufficient readings, a minimum of 8, around the circumference to ensure that the minimum thickness has been determined. Use of a properly calibrated ultrasonic thickness tester is also permitted under this specification. For nondestructive testing, this is the preferred method. Make sufficient readings to ensure that the minimum thickness has been determined.

8.4.3 Out of Roundness—Measure the out of roundness in accordance with the requirements of Test Method D2122.

8.5 Ambient and Elevated Temperature Sustained Pressure Testing—Prepare three specimens and test in accordance with Test Method D1598 at the hoop stress and temperature specified in Table 5 for the particular PE-GF HDB classification. All three specimens shall exceed the minimum time before failure without failing. Use water as the internal test medium.

9. Sampling, Inspection, and Retest

9.1 Sampling—The selection of the sample, or samples, and the inspection of the product, shall be as agreed upon by the purchaser and the seller.

9.2 Notification—If inspection is specified by the purchaser, the manufacturer shall notify the purchaser in advance of the date, time, and place of testing of the pipe in order that the purchaser may be represented at the test by his inspector.

9.3 Access—The purchaser's inspector shall have free access to those parts of the manufacturer's plant that are involved in testing work performed under this specification. The manufacturer shall afford the inspector, without charge, all reasonable facilities for determining whether the pipe meets the requirements of this specification.

9.4 Retest and Rejection—If the results of any test(s) do not meet the requirements of this specification, the test(s) may be conducted again in accordance with an agreement between the purchaser and the seller. There shall be no agreement to lower the minimum requirement of the specification by such means as omitting tests that are a part of the specification, substituting or modifying a test method, or by changing the specification limits. In retesting, the product requirements of this specification shall be met and the test methods designated in this specification shall be followed. If upon retest failure occurs, the quantity of product represented by the test(s) does not meet the requirements of this specification.

NOTE 2—Sampling, and any retesting, are normally done at the time of manufacture.

10. Certification

10.1 When specified in the purchase order or contract, a producer's or supplier's certification shall be furnished to the purchaser that the material was manufactured, sampled, tested, and inspected in accordance with this specification and has been found to meet the requirements. When specified in the purchase order or contract, a report of the test results shall be furnished.

11. Marking

11.1 Quality of Marking—The marking shall be applied to the pipe in such a manner that it remains legible (easily read) after installation and inspection. It shall be placed, at least, at each end of each length of pipe or spaced at intervals of not more than 10 ft [3.0 m].

11.2 Markings—Each standard and random length of pipe in compliance with this specification shall be clearly marked by the producer with the following information: this designation, ASTM D2720/D2720M; the nominal pipe size, in inches; the

legend PE-GF pipe; the HDS nominal value; the pressure class, the manufacturer's name, trade name, or trademark and the manufacturer's production code, identifying plant location, machine and date of manufacture.

12. Packaging

12.1 All pipes, unless otherwise specified, shall be packed or loaded onto a carrier, for standard commercial shipment.

13. Quality Assurance

13.1 When the product is marked with this designation, F2720, the manufacturer affirms that the product was manufactured, inspected, sampled, and tested in accordance with this specification and has been found to meet the requirements of this specification.

SUPPLEMENTARY REQUIREMENTS

This requirement applies whenever a regulatory authority or user calls for the product to be used to convey or to be in contact with potable water.

S1. Potable Water Requirement

S1.1 Products intended for contact with potable water shall be evaluated, tested, and certified for conformance with ANSI/NSF Standard No. 61 or the health effects portion of NSF

Standard No. 14 by an acceptable certifying organization when required by the regulatory authority having jurisdiction.

SUMMARY OF CHANGES

Committee F17 has identified the location of selected changes to this standard since the last issue (F2720/F2720M-08) that may impact the use of this standard.

- (1) Addition of new **Table 3a**.
- (2) Renumbering to **Table 3b** and revision of title to existing **Table 3**.
- (3) Addition of new **Table 4a**, **Table 4b**, **Table 4c**, and **Table 4d**.

- (4) Renumbering and revised titles of existing tables **Table 4a**, **Table 4b**, **Table 4c**, **Table 4d** to **Table 4e**, **Table 4f**, **Table 4g**, and **Table 4h**.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>