

INTERNATIONAL
STANDARD

ISO
19953

First edition
2004-07-15

**Footwear — Test methods for heels —
Resistance to lateral impact**

*Chaussures — Méthodes d'essai relatives aux talons — Résistance
aux chocs latéraux*



Reference number
ISO 19953:2004(E)

© ISO 2004

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

© ISO 2004

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 19953 was prepared by the European Committee for Standardization (CEN) in collaboration with Technical Committee ISO/TC 216, *Footwear*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Throughout the text of this document, read “...this European Standard...” to mean “...this International Standard...”.

Contents

	page
Foreword.....	v
1 Scope	1
2 Apparatus and material	1
2.1 General	1
2.2 Lateral impact tester	1
2.3 Metal mounting trays	3
2.4 Metal alloy	3
3 Sampling and conditioning	3
4 Test method	3
4.1 Principle	3
4.2 Procedure	4
5 Expression of results	4
6 Test report	4

Foreword

This document (EN ISO 19953:2004) has been prepared by Technical Committee CEN /TC 309, "Footwear", the secretariat of which is held by AENOR, in collaboration with ISO/TC 216 "Footwear".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2005, and conflicting national standards shall be withdrawn at the latest by January 2005.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

11

1 Scope

This European Standard specifies a test method for determining the impact strength of the heels of ladies' shoes. The result provides an assessment of the liability to failure under the occasional heavy blows received during wear.

NOTE While the test method is applicable to all types of high heels, of whatever construction, it is particularly useful for injection-moulded plastics heels which incorporate a steel dowel reinforcement, giving information on the suitability of the dowels' hardness or softness. Normally, heels which by virtue of their shape have a high lateral impact resistance do not need to be tested in this way.

2 Apparatus and material

2.1 General

The following apparatus and material shall be used.

2.2 Lateral impact tester

2.2.1 General

An example of a suitable apparatus is being shown in Figure 1. The apparatus is clamped either onto a solid built-in bench, or onto a rigid free-standing frame anchored to the floor.

The lateral impact tester shall include the following.


2.2.2 Pendulum, consisting of a circular steel bob of diameter (108 ± 1) mm and thickness (49 ± 2) mm, which is fixed by a circular steel shaft of diameter $(25 \pm 0,5)$ mm to a hub, on the bearing axle of diameter (75 ± 1) mm. The distance from the centre of the bob to the centre of the hub is (432 ± 2) mm. The moment of the pendulum when it is held horizontally is $(17,3 \pm 0,2)$ N·m.

2.2.3 Striker head, consisting of a strip of metal $(6,0 \pm 0,5)$ mm thick, $(25,0 \pm 0,5)$ mm wide and (35 ± 2) mm long with the striking edge rounded to a radius of $(3,0 \pm 0,5)$ mm. The head is fixed rigidly to the pendulum bob so that the striker tip and centre of the bob lie on the same circle of swing of the pendulum and are (89 ± 2) mm apart.

2.2.4 Energy scale for the pendulum, calibrated in increment of 0,68 J, from 0 J to 18,3 J. A marker attached to the pendulum moves over this scale and enables the pendulum to be set up to the desired energy of blow.

2.2.5 Base clamp, for holding the metal mounting tray (3.2) and for adjusting it vertically and horizontally to achieve correct alignment of the heel tip.

NOTE If the apparatus is not firmly mounted there is partial loss of energy on impact, thereby producing false results.

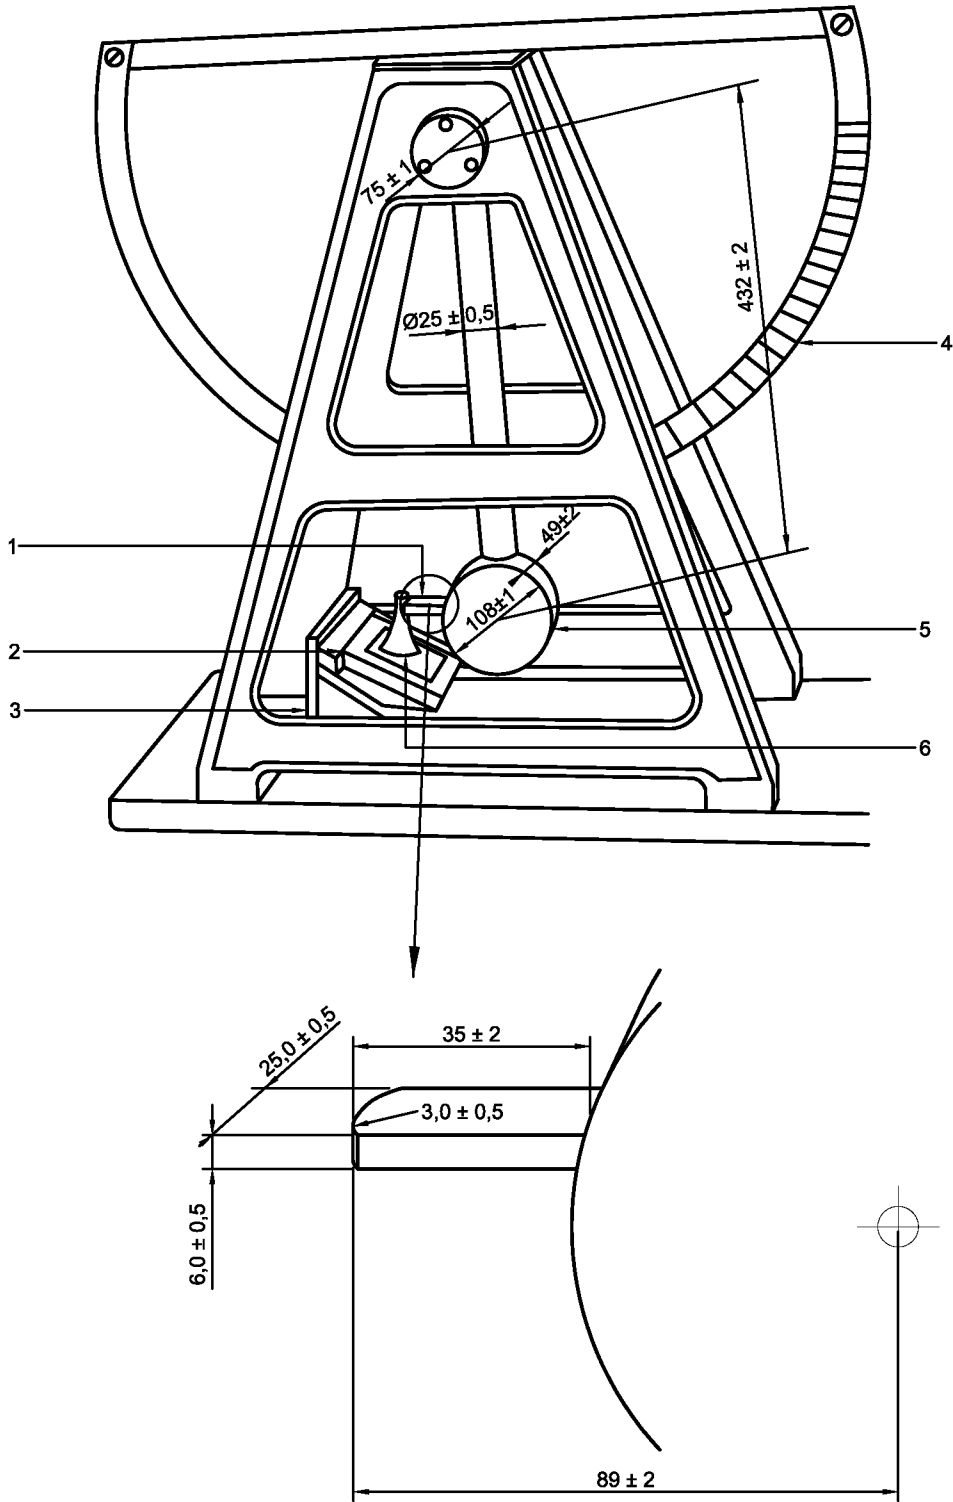

Key

- | | | | |
|---|--------------|---|---------------|
| 1 | Striker head | 4 | Energy scale |
| 2 | Heel tray | 5 | Pendulum |
| 3 | Base clamp | 6 | Test specimen |

Figure 1 — Lateral impact tester

2.3 Metal mounting trays

An example of a suitable apparatus is shown in Figure 2. Each to contain a heel set in metal alloy of melting point between 100° C and 150° C.

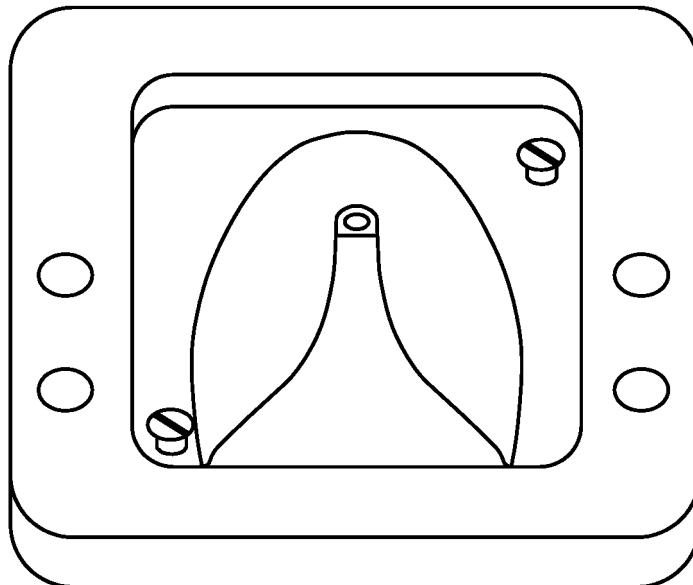


Figure 2 — Metal mounting tray with heel in position before addition of molten alloy

2.4 Metal alloy

Melting point between 100° C and 150° C.

3 Sampling and conditioning

3.1 Take free heels and set each heel in a dry metal mounting tray (3.2), using the procedure described in 3.2 or, for very short heel (usually those below 40 mm in height), the procedure described in 3.3, to obtain a test specimen assembly.

3.2 Place the heel centrally in the tray so that the seat breast edge is against a flat end of the tray and the heel tip points upwards (see Figure 2). Heat the metal alloy (3.3) until it is at the lowest temperature at which it will flow into all parts of the tray, filling the space around the heel to within 3 mm from the top. Allow the alloy to cool and set thereby providing a rigid mounting for the heel.

3.3 Since some very short heels cannot be struck correctly by the striker if mounted in accordance with 4.2 (because the bottom of the pendulum catches the base clump assembly), a different method of mounting is necessary. In such cases mount the heel with the rear of the heel seat against a flat end of the tray. Cut a small amount from the rear of the heel so as to set the heel further towards the rear of the mounting tray if this allows the striker to strike the heel correctly.

4 Test method

4.1 Principle

A heel, clamped with the tip uppermost and the stem approximately vertical, is subjected repeatedly to measured blows from a pendulum striker, the energy of the blows increasing successively until the heel fails.

4.2 Procedure

4.2.1 Position the test specimen assembly in the lateral impact tester (2.2) sliding the assembly up the inclined plane of the base clamp (2.1.5) as far as possible and locking into position with the back of the heel facing the pendulum. Set the test specimen assembly at a suitable angle to the horizontal so that the blow will be applied at right angles to the heel stem. Adjust the clamp so that the heel just contacts the striker when the pendulum is vertical, with the tip of the heel 6 mm above the striker tip.

4.2.2 Lift the pendulum to the 0,68 J position and release, so that the striker (2.1.3) falls against the heel stem. Catch the pendulum on its rebound to prevent a second blow. Repeat this procedure, increasing the impact energy at each blow by 0,68 J either until the heel stem breaks, until it bends and the pendulum jams, or until an impact energy of 18,3 J has been applied. Record total number of blows delivered.

4.2.3 Damage involving fracture or cracking of the heel at the point of impact of the striker is regarded as invalid in this test, since it is due to the effect of the striker acting as a chisel rather than fracture of the heel due to impact of the heel as in wear. If such damage occurs, report it together with this explanation.

4.2.4 Repeat the test with the other two test specimen assemblies by following the same procedure.

5 Expression of results

Express the result for each test specimen assembly as follows:

- a) the number of blows to failure (or that no failure occurred after 27 blows) and the energy, in J, of the last blow;
- b) the type of failure, as described in 4.2.2, or the fact that damage involving fracture or cracking of the heel at the point of the impact occurred, as described in 4.2.3.

6 Test report

The test report shall include the following information:

- a) result for each heel, expressed in accordance with clause 5;
- b) full description of the samples tested, including commercial styles codes, colours, nature, etc.;
- c) reference to this method of test;
- d) date of testing;
- e) any deviation from this test method.

ICS 61.060

Price based on 4 pages